



Home About Login Register Categories Search Current Archives Announcements Publication Ethics

Home > Journal Syifa Sciences and Clinical Research

Journal Syifa Sciences and Clinical Research

Frequency : Triannually (3 issues per year)
Language : English (preferable), Indonesia
DOI : <https://dx.doi.org/10.37311/jsscr>
OAI Address : <http://ejurnal.ung.ac.id/index.php/jsscr/oai>

Journal Syifa Sciences and Clinical Research (JSSCR), established in 2019, is an international, open-access, peer-reviewed journal published triannually by the Department of Pharmacy, State University of Gorontalo, in collaboration with the [Indonesian Pharmacist Association \(Ikatan Apoteker Indonesia, IAI\)](#). The journal serves as a scientific platform for researchers, academics, and practitioners in the field of pharmaceutical sciences to disseminate high-quality research findings and foster scholarly communication.

JSSCR is indexed in several reputable databases, including [Sinta](#), [Google Scholar](#), [Dimensions](#), [Scilit](#), [Crossref](#) and [Garuda](#). The journal is committed to promoting excellence in pharmaceutical research and innovation, with the following areas of focus: Pharmaceutical Technology and Pharmaceutics, Pharmaceutical Analysis, Medicinal Chemistry, Pharmacology and Toxicology, Pharmaceutical Biology, Community Pharmacy, and Clinical Pharmacy.

The journal welcomes original research articles, review papers, and short communications that contribute to the advancement of pharmaceutical sciences and clinical practices.

Online ISSN: 2656-9612

Print ISSN: 2656-8187

ANNOUNCEMENTS

ANNOUNCEMENT ON THE RESTORATION OF META DATA FOR THE JOURNAL SYIFA SCIENCES AND CLINICAL RESEARCH (JSSCR)

Following a malware virus attack carried out by unauthorized parties, which resulted in the loss of all meta data uploaded after February 2025, we would like to inform all authors and readers that the missing meta data has been successfully restored, starting from the publications of February to May 4, 2025.

We kindly ask all authors and readers to review their submitted articles or publications and ensure that the meta data has been updated correctly. We understand that this disruption may have caused inconvenience, and we sincerely apologize for this. We are also committed to enhancing our security systems to prevent similar incidents in the future. For further inquiries, please contact us at info.jsscr@ung.ac.id, muhtauipik@ung.ac.id, or via phone at +6281547458537.

Sincerely,

The Editorial Team of Journal Syifa Sciences and Clinical Research

Pengumuman Pemulihan Meta Data pada Journal Syifa Sciences and Clinical Research

Sehubungan dengan serangan virus malware yang dilakukan oleh pihak yang tidak bertanggung jawab, yang mengakibatkan hilangnya seluruh meta data yang diunggah setelah Februari 2025, kami ingin menginformasikan kepada seluruh penulis dan pembaca bahwa meta data yang hilang telah berhasil dipulihkan, mulai dari publikasi bulan Februari hingga 4 Mei 2025.

Kami mengimbau kepada seluruh penulis dan pembaca untuk memeriksa kembali artikel atau publikasi yang telah dikirimkan dan memastikan bahwa meta data telah diperbarui dengan benar. Kami menyadari bahwa gangguan ini dapat menyebabkan ketidaknyamanan, dan kami mohon maaf atas hal tersebut. Kami juga berkomitmen untuk meningkatkan sistem keamanan kami guna mencegah terjadinya insiden serupa di masa mendatang. Untuk pertanyaan lebih lanjut, silakan menghubungi kami di info.jsscr@ung.ac.id, muhtauipik@ung.ac.id, atau melalui telepon di +6281547458537.

Hormat kami,

Tim Redaksi Journal Syifa Sciences and Clinical Research

Focus and Scope

Editorial Board

Peer Reviewer

Copyright Notice

Author Guideline

Online Submission

Author Fees

This journal has been published by Department of Pharmacy, State University of Gorontalo collaboration with IAI (Ikatan Apoteker Indonesia)



Template :



User

Username
 Password
☐ Remember me

Indexed By :





[Home](#) [About](#) [Login](#) [Register](#) [Categories](#) [Search](#) [Current](#) [Archives](#) [Announcements](#) [Publication Ethics](#)

[Home](#) > [About the Journal](#) > [Editorial Team](#)

Editorial Team

ADVISORY BOARD

[Prof. Dr. Ishak Isa, M.Si](#), Department of Chemistry, Universitas Negeri Gorontalo, Indonesia

EDITOR IN CHIEF

[Dr. Teti Sutriyati Tuloli, M.Si, Apt](#), Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

MANAGING EDITOR

[Muhammad Taupik](#), [Scopus ID: 57220203768] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

EDITORIAL BOARD

[Ardi Nugroho](#), [Scopus ID: 56205658600] Department of Pharmacy, Universitas Islam Indonesia, Yogyakarta, Indonesia

[Ricky Andi Syahputra](#), [Scopus ID: 57219301149] Department of Chemistry, Universitas Negeri Medan, Indonesia

[Andrian Saputra](#), [Scopus ID: 56826230200], Department of Chemistry, Universitas Lampung, Indonesia

[Fajar Nugraha](#), [Sinta ID : 6721412] Department of Pharmacy, Universitas Tanjungpura, Pontianak, Indonesia

[Endah Nurrohanta Djuwarno](#), [Sinta ID : 6748551] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Mahdalena Sy. Pakaya, M.Si, Apt](#), Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[A. Muthi Andy Suryadi, M.Farm., Apt](#), Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Juliyanty Akuba, M.Sc., Apt](#), Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

REVIEWERS BOARD

[Suharjono Suharjono](#), [Scopus ID: 57188994112] Department of Pharmacy, Universitas Airlangga, Indonesia

[Dr. Widy Susanti Abdul Kadir, M.Si, Apt](#), [Scopus ID : 56609230200] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Yusran Yusran](#), [Scopus ID: 57188746955] Department of Chemistry, Jilin University, China

[Susi Ari Kristina](#), [Scopus ID: 56626120200] Department of Pharmacy, Universitas Gadjah Mada, Indonesia

[Yandi Syukri](#), [Scopus ID: 57190751925] Department of Pharmacy, Universitas Islam Indonesia, Indonesia

[Dr. Iyan Sopyan, M.Si, Apt.](#), [Scopus ID: 55981715600] Department of Pharmacy, Universitas Padjajaran, Indonesia

[Dr. Ni Putu Eka Leliqia, M.Si, Apt.](#), [Scopus ID: 55681974200] Department of Pharmacy, Universitas Udayana, Bali, Indonesia

[Lina Winarti](#), [Scopus ID: 56780209500] Department of Pharmacy, Universitas Jember, Indonesia

[Liza Pratiwi](#), [Scopus ID: 57190685776] Department of Pharmacy, Universitas Tanjungpura, Pontianak, Indonesia

[Nur Ain Thomas](#), [Scopus ID : 57208779422] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Mohammad Adam Mustapa, M.Sc.](#), [Scopus ID : 57202789689] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Robert Tungadi](#), [Scopus ID : 56609263400] Department of Pharmacy, Universitas Negeri Gorontalo, Indonesia

[Willy Tirza Eden, S. Farm., M.Sc., Apt.](#), [Scopus ID: 57201144791] Program Studi Farmasi, Jurusan Kimia, Fakultas Matematika dan Ilmu Pengetahuan Alam, Universitas Negeri Semarang, Indonesia

TRANSLATOR

[Abdul Kadir Ismail](#), Tadris Bahasa Inggris, FITK IAIN Sultan Amai

LAYOUT EDITOR

[Rusdi Rusdi](#), Universitas Negeri Makassar, Indonesia

ADMINISTRATIVE STAFF

[Rionaldi Yahya](#), Fakultas Olahraga dan Kesehatan, Universitas Negeri Gorontalo

EDITORIAL OFFICE OF JOURNAL SYIFA SCIENCES AND CLINICAL RESEARCH

Department of Pharmacy, Gorontalo State University

Jl. Jenderal Sudirman No.6, Kota Gorontalo, Provinsi Gorontalo 96128, Indonesia

Email: info.jsscr@ung.ac.id

Google Scholar : [JOURNAL SYIFA SCIENCES AND CLINICAL RESEARCH](#)



Journal Syifa Sciences and Clinical Research (JSSCR) is licensed under a [Creative Commons Attribution-ShareAlike 4.0 International License](#).

Focus and Scope

Editorial Board

Peer Reviewer

Copyright Notice

Author Guideline

Online Submission

Author Fees

This journal has been published by
Department of Pharmacy, State University of
Gorontalo collaboration with IAI (Ikatan
Apoteker Indonesia)



Template :



User

Username

Password

☐ Remember me

Login

Indexed By :





Home About Login Register Categories Search Current Archives Announcements Publication Ethics

Home > Archives > Vol 7, No 2 (2025)

Vol 7, No 2 (2025)

Volume 7 Edisi 2 2025

DOI: <https://doi.org/10.37311/jsscr.v7i2>

TABLE OF CONTENTS

ARTICLES

[In Silico Study of *Acmella uliginosa* Leaf Compounds Interaction with Human Glucosidase](#)

DOI : [10.37311/jsscr.v7i2.30890](https://doi.org/10.37311/jsscr.v7i2.30890) | Abstract views : 228 times
Nia Marlina Kurnia, Doctoral Program of Pharmaceutical Sciences, Faculty of Pharmacy, Pancasila University, Jakarta 1264, Indonesia, Indonesia

PDF
88-97

[The Impact of Nutrition Education Intervention on Parental Knowledge to Prevent Child Stunting](#)

DOI : [10.37311/jsscr.v7i2.30531](https://doi.org/10.37311/jsscr.v7i2.30531) | Abstract views : 245 times
Gusti Ayu Putu Laksmi Puspa Sari, Faculty of Pharmacy, Mahasaraswati University Denpasar, Denpasar, Indonesia, Indonesia
I Gusti Agung Ari Kusuma Yana, Clinical and Community Pharmacy Programme, Institut Teknologi dan Kesehatan Bali, Denpasar, Indonesia, Indonesia
Yosi Irawati Wibowo, Centre for Medicines Information and Pharmaceutical Care (CMIPC), Faculty of Pharmacy, Universitas Surabaya, Surabaya 60293, Indonesia, Indonesia

PDF
98-103

[A Literature Review of Zingiberaceae Plant Utilisation in Ethnomedicine Across Five Major Indonesian Islands](#)

DOI : [10.37311/jsscr.v7i2.30865](https://doi.org/10.37311/jsscr.v7i2.30865) | Abstract views : 320 times
Jessica Ayu Trisianna, Department of Biology Education, Faculty of Biology, Satya Wacana Christian University, Jl. Diponegoro no. 52-60 Salatiga, 50711, Indonesia, Indonesia
Putri Indrianasari, Department of Biology, Faculty of Biology, Satya Wacana Christian University, Jl. Diponegoro no. 52-60 Salatiga, 50711, Indonesia, Indonesia
Wellinus Lepi, Department of Biology Education, Faculty of Biology, Satya Wacana Christian University, Jl. Diponegoro no. 52-60 Salatiga, 50711, Indonesia, Indonesia
Sri Kasmiyati, Department of Biology, Faculty of Biology, Satya Wacana Christian University, Jl. Diponegoro no. 52-60 Salatiga, 50711, Indonesia, Indonesia
Elizabeth Betty Elok Kristiani, Department of Biology, Faculty of Biology, Satya Wacana Christian University, Jl. Diponegoro no. 52-60 Salatiga, 50711, Indonesia, Indonesia

PDF
104-113

[Harnessing Chitosan-Stabilized Silver Nanoparticles in *Cymbopogon citratus* Nanocomposites: A Promising Antibacterial Solution Against *Streptococcus mutans*](#)

DOI : [10.37311/jsscr.v7i2.31165](https://doi.org/10.37311/jsscr.v7i2.31165) | Abstract views : 184 times
Khansa Amira, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Komariah Komariah, Department of Oral Biology, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Rezky Anggraeni, Department of Oral Biology, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Monica Dewi Ranggaini, Department of Oral Biology, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Johni Halim, Department of Oral Biology, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Didi Nugroho, Department of Oral Biology, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia
Selviana Wulansari, Department of Conservative Dentistry, Faculty of Dentistry, Trisakti University, Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia, Indonesia

PDF
114-124

[Literature Review: Factors Influencing Knowledge and Compliance in Taking Blood Supplements Among Pregnant Women](#)

DOI : [10.37311/jsscr.v7i2.29913](https://doi.org/10.37311/jsscr.v7i2.29913) | Abstract views : 169 times
Cyntia Wulandari, Department of Pharmacy, Faculty of Mathematics and Natural Sciences, Pakuan University, Jl. Pakuan, Tegallega, Bogor City, West Java, Indonesia, Indonesia
Dewi Kania Putri Pamungkas, Department of Pharmacy, Faculty of Mathematics and Natural Sciences, Pakuan University, Jl. Pakuan, Tegallega, Bogor City, West Java, Indonesia, Indonesia

PDF
125-135

[Evaluation of Maja Leaf *Simplisia* \(*Aegle marmelos* L.\) for Herbal Standardization: Physicochemical and Microbial Testing](#)

DOI : [10.37311/jsscr.v7i2.31220](https://doi.org/10.37311/jsscr.v7i2.31220) | Abstract views : 160 times
Arista Wahyu Ningsih, Department of Pharmaceutical Biology, Faculty of Health, Anwar Medika University, Jl. Raya By Pass Krian KM. 33 Balongbendo Sidoarjo 61263, Indonesia, Indonesia
Zahrotul Maulidivah, Department of Pharmacv. Faculty of Health. Anwar Medika University. Jl. Rava By Pass Krian

PDF
136-145

Focus and Scope

Editorial Board

Peer Reviewer

Copyright Notice

Author Guideline

Online Submission

Author Fees

This journal has been published by Department of Pharmacy, State University of Gorontalo collaboration with IAI (Ikatan Apoteker Indonesia)



Template :



User

Username
 Password
☐ Remember me

Indexed By :



KM. 33 Balongbendo Sidoarjo 61263, Indonesia, Indonesia

Khoirun Nisyak, Department of Pharmaceutical Chemistry, Faculty of Health, Anwar Medika University, Jl. Raya By Pass Krian KM. 33 Balongbendo Sidoarjo 61263, Indonesia, Indonesia

Antiproliferative Activity of *Borassus flabellifer* L. Seed Coat Extracts on Oral Carcinoma Cells

DOI : [10.37311/jsscr.v7i2.31570](https://doi.org/10.37311/jsscr.v7i2.31570) |  Abstract views : 32 times

Pretty Trisfilha, Department of Oral & Maxillofacial Pathology, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No. 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Janti Sudiono, Department of Oral & Maxillofacial Pathology, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No. 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Komariah Komariah, Department of Oral Biology sub-division of Histology, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No. 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Celine Chelsea Hartono, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Namita Namita Prayorina Nugroho, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Raynita Rosalinda Angeline, Faculty of Dentistry, Universitas Trisakti, Jl. Kyai Tapa No 260 Grogol, Jakarta Barat, Indonesia, Indonesia

Impact of Knowledge on Analgesic Self-Medication Practices Among Pharmacy Students

DOI : [10.37311/jsscr.v7i2.31576](https://doi.org/10.37311/jsscr.v7i2.31576) |  Abstract views : 23 times

Lidya Pratiwi Afri Tjaja, S1 Clinical and Community Pharmacy Study Programme, Widya Dharma Husada College of Health Sciences, Jl. Pajajaran No. 1, South Pamulang, South Tangerang City 15417, Indonesia, Indonesia

Fahrida Nuraziza Supandi, Nursing Study Programme, Widya Dharma Husada College of Health Sciences, Jl. Pajajaran No. 1, South Tangerang City 15417, Indonesia, Indonesia

Gina Aulia, D3 Pharmacy Study Programme, Widya Dharma Husada College of Health Sciences, Jl. Pajajaran No. 1, South Pamulang, South Tangerang City 15417, Indonesia, Indonesia

Annisa Septiyana Putri, S1 Clinical and Community Pharmacy Study Programme, Widya Dharma Husada College of Health Sciences, Jl. Pajajaran No. 1, South Pamulang, South Tangerang City 15417, Indonesia, Indonesia

EDITORIAL OFFICE OF JOURNAL SYIFA SCIENCES AND CLINICAL RESEARCH

Department of Pharmacy, Gorontalo State University

Jl. Jenderal Sudirman No.6, Kota Gorontalo, Provinsi Gorontalo 96128, Indonesia

Email: info.jsscr@ung.ac.id

Google Scholar : [JOURNAL SYIFA SCIENCES AND CLINICAL RESEARCH](https://scholar.google.com/citations?hl=id&user=JOURNAL-SYIFA-SCIENCES-AND-CLINICAL-RESEARCH)



Journal Syifa Sciences and Clinical Research (JSSCR) is licensed under a [Creative Commons Attribution-ShareAlike 4.0 International License](https://creativecommons.org/licenses/by-sa/4.0/).

Tools :



zotero

Viewers:

JSSCR Visitors

 ID 220,453	 MY 212
 US 3,509	 JP 193
 SG 1,697	 TL 187
 IN 498	 RU 144
 PH 224	 CN 143

Pageviews: 516,996

Flags Collected: 109



Visitor :

00509377

[View My Stats](#)

Journal Content

Search

Search Scope

All 

Search

Browse

» [By Issue](#)

» [By Author](#)

» [By Title](#)

» [Other Journals](#)

» [Categories](#)

Notifications

» [View](#)

» [Subscribe](#)

[Open Journal Systems](#)

[Journal Help](#)

Harnessing Chitosan-Stabilized Silver Nanoparticles in *Cymbopogon citratus* Nanocomposites: A Promising Antibacterial Solution Against *Streptococcus mutans*

Khansa Amira¹, Komariah^{2*}, Rezky Anggraeni³, Monica Dewi Ranggaini⁴, Johni Halim⁵, Didi Nugroho⁶, Selviana Wulansari⁷

¹ Faculty of Dentistry, Trisakti University,

Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia

^{2,3,4,5,6} Department of Oral Biology, Faculty of Dentistry, Trisakti University,

Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia

⁷ Department of Conservative Dentistry, Faculty of Dentistry, Trisakti University,

Jl. Kyai Tapa No. 1 Grogol Petamburan, West Jakarta 11440, Indonesia

* Author Correspondence. Email: komariah@trisakti.ac.id

ABSTRACT

Nanotechnology explores materials at the nanometer scale and has broad applications, including dentistry. One of the emerging innovations is nanocomposites. Nanocomposites consist of two or more materials, including filler materials and stabilizing agents, and possess antimicrobial activity. Meanwhile, silver nanoparticles (AgNPs) synthesized using lemongrass leaf extract (*Cymbopogon citratus*) through a green method have potential as antibacterial agents, particularly against oral cavity bacteria. However, AgNPs tend to aggregate, necessitating the use of stabilizing agents such as chitosan. This study evaluated the antibacterial efficacy of AgCh nanocomposites with *C. citratus* against *S. mutans*. The study employed the disc diffusion method to test the antibacterial effectiveness of nanocomposites at concentrations of 6.25 mg/mL, 12.5 mg/mL, 15 mg/mL, 25 mg/mL, and 50 mg/mL, along with 0.2% chlorhexidine as the positive control and acetic acid and distilled water as negative controls. Observations at 24, 48, and 72 hours revealed that no inhibition zones formed at 24 hours. However, inhibition zones began to form at 48 and 72 hours, with higher nanocomposite concentrations resulting in larger inhibition zones. The 50 mg/mL concentration produced the largest inhibition zone. This study demonstrates that AgChCc nanocomposites demonstrated significant antibacterial activity, with the optimal concentration for highest effectiveness against *S. mutans* being 50 mg/mL.

Copyright © 2025 Jsscr. All rights reserved.

Keywords:

Silver nanoparticles (AgNPs); *Cymbopogon citratus*; Chitosan; Antibacterial activity; *Streptococcus mutans*

Received:
2025-04-15

Accepted:
2025-05-08

Online:
2025-05-15

1. Introduction

Nanotechnology explores matter at the nanometer scale and has revolutionized fields like medicine and dentistry. With the ability to control and manipulate matter at the nanometer-scale level, nanotechnology has paved the way for the development of various applications that have great potential in various fields, such as electronics, medicine, food industry, and others. One of the emerging nanoscale technologies is nanocomposites. Nanocomposites are composite materials that have nanometer-sized components, promising significant improvements in function and performance

compared to materials with larger particle sizes [1]. In dentistry, nanotechnology addresses limitations of conventional materials, such as chlorhexidine's side effects. Nanocomposite materials in dentistry can be used as mouthwash. The commonly used mouthwash is chlorhexidine 0.2%, but chlorhexidine has side effects of tooth discoloration, impaired taste perception, and increased calculus formation in supragingival [2], therefore an alternative material derived from natural materials is needed such as the use of nanocomposites in mouthwash. Nanocomposites consist of two or more materials, namely *filler* material and stabilizing agent. Commonly used stabilizing agents are *titanium dioxide*, *zinc dioxide*, *silicon dioxide*, *polyvinyl alcohol*, *cellulose acetate*, and *chitosan* [3].

Chitosan is obtained from the deacetylation of chitin, which is a major component in the shells of crustaceans, fungi, and insects such as the horned beetle *Xylotrupes gideon* (*X. gideon*). Chitosan has become a very instrumental material in the manufacture of nanocomposites. Chitosan has biocompatible, *biodegradable*, and non-toxic properties, which have antimicrobial, antioxidant, anti-inflammatory, and anticancer activities. The mechanism of antimicrobial action of chitosan involves interaction with the microbial cell membrane, leading to cell leakage and cell death. These properties make chitosan an ideal candidate for applications in dentistry [4].

Filler material in a nanocomposite is a component that is added to the main material to improve its properties. The *filler* material is the result of synthesizing silver particles with *Cymbopogon citratus* which produces AgNPs that are more effective and more environmentally friendly [5]. The synthesis of AgNPs using ethanol extract of *C. citratus*, which has been carried out in previous studies, is used as a bioreductor to convert Ag^+ ions into Ag^0 . This green synthesis process is considered safer, environmentally friendly, and economical compared to chemical-physical synthesis which is expensive and causes environmental pollution [6]. AgNP synthesis using *C. citratus* can be a safer and more environmentally friendly alternative to produce AgNPs that are effective in inhibiting bacterial growth [7].

C. citratus, which has long been used in traditional medicine, is known to have various therapeutic properties, including the ability to fight bacteria. *C. citratus* leaf extract has been known to have good antibacterial activity against several types of bacteria, one of which is *Streptococcus mutans*. *S. mutans* is a Gram-positive bacterium as one of the main causes of dental caries. *S. mutans* has the ability to form *biofilms* and produce an acidic environment through carbohydrate fermentation, which is one of the main causes of dental caries [8]. Nanocomposite is a synthesis of $AgNO_3$ with *C. citratus* extract stabilized with chitosan. Chitosan can be used as an effective reducing agent in the synthesis of AgCh nanoparticles. *C. citratus* leaf extract can help increase the surface area of AgCh particles. Therefore, the use of *C. citratus* leaf extract in the synthesis of AgCh chitosan nanocomposites can enhance the antibacterial activity of the resulting nanocomposites [9].

Research on AgNP synthesis with *C. citratus* has been shown to inhibit the growth of *Salmonella paratyphi*, *Shigella flexneri*, *Vibrio cholerae*, *Bacillus cereus*, and *Escherichia coli* bacteria [10]. Synthesis of AgNPs with natural materials has low stability and is able to easily undergo aggregation into a larger size, so a stabilizing material is needed, namely chitosan [11]. However, no research has been conducted using chitosan as a stabilizing agent against bacteria in the oral cavity. Therefore, this study aims to synthesize AgNPs with *C. citratus* and the use of horn beetle chitosan as a stabilizing agent (AgChCc) in increasing antibacterial activity against *S. mutans* bacteria using the diffusion method.

2. Methods

Materials and tools used in this study are: AgNO_3 0.1 M (Sigma Aldrich), distilled water, acetic acid, *S. mutans* bacteria (microbiology laboratory, Faculty of Medicine, YARSI University), *C. citratus* extract (BPSI TROA), chitosan *X. gideon* (chemistry laboratory, Faculty of Marine and Fisheries, IPB), chlorhexidine 0.2% (Minosep, Indonesia), 70% ethanol solution (SAE Alcohol 70%, Indonesia), BA (*Blood Agar*) media obtained from the Faculty of Yarsi University, BHI media, stirring rod, Petri dish, glassware, measuring cup, incubator, vernier, paper discs, Erlenmeyer flask, *magnetic stirrer*, micro pipette, tweezers, test tube rack, marker pen, and test tube.

Ethical approval for this study was obtained from the Health Research Ethics Committee of Faculty of Dentistry Universitas Trisakti, with approval number 800/S1/KEPK/FKG/6/2024.

Preparation of *C. citratus* ethanol extract

The process of making ethanol extract from *C. citratus* starts with drying the leaves for two weeks. Next, extraction was carried out using the maceration method. Dried *C. citratus* was soaked with 70% ethanol in a ratio of 1:10 for 72 hours at room temperature. In the maceration process, the solution was shaken manually for 15 minutes at every multiple of eight hours for three days. The solution obtained was filtered using Whatman number one filter paper. The liquid was put into a *rotary evaporator* at 50-60°C to evaporate, thus obtaining *the crude extract* [12].

Preparation of AgCh nanocomposite

The preparation of AgCh nanocomposites began by dissolving 1.7 g of AgNO_3 (Sigma Aldrich) into 100 mL of distilled water to produce a concentration of 0.1 M AgNO_3 solution. A total of 100 mL of the solution was mixed with two grams of *C. citratus* extract, then the mixture was heated at 40°C for 30 minutes. AgNP solution was formed, then add 1.5% (b/v) chitosan solution, by weighing 1.5 g chitosan powder dissolved in acetic acid and adding distilled water up to 100 mL. The mixture was heated at 40°C for 30 minutes. Next, let stand for 24 hours to produce nanocomposites. The resulting nanocomposite solution was centrifuged at room temperature at 9000 rpm for three minutes. Then, washed three times using distilled water and centrifuged again at the same speed. After the precipitate was obtained, dilutions were made using distilled water at concentrations of 6.25; 12.5; 15; 25; and 50 mg/mL [13], [14].

Preparation of AgCh nanocomposite

To test the antibacterial activity in this study, we started by taking bacterial culture from BA media culture. Next, the bacterial suspension was adjusted to the McFarland 0.5 standard, which is equivalent to the number of bacterial suspensions of 1.5×10^8 CFU/mL. A bacterial suspension of 200 μL was taken using a micropipette, and leveled on BA media with the *spread plate* method using a sterile *cotton swab* [15]. Take a paper disk with a diameter of 6 mm using sterile tweezers and place it on the surface of BA media. Then, 20 μL of test material concentrations of 6.25; 12.5; 15; 25; and 50 mg/mL were dripped on the disc paper [16]. Then, put the agar medium into a jar to eliminate oxygen, then incubate for 24, 48, and 72 hours at 37°C. Observe the formation of the inhibition zone by measuring the clear area on the BA medium using a digital caliper. The formula used to determine the inhibition zone is [17]:

$$L = \frac{(D1-D3)+(D2-D3)}{2} \quad (1)$$

Description:

L : Width of zone of inhibition

D1 : Diameter of horizontal inhibition area (mm)

D2 : Diameter of vertical inhibition area (mm)

D3 : Disc paper diameter (mm)

Data analysis

The results of the observations that have been made are compiled in Excel format. Statistical software SPSS version 2.3 was used to analyze the data. Then the Shapiro-Wilk test was used to perform the normality test. If the p value was >0.05, a parametric test was performed, namely *one-way analysis of variance* (ANOVA). If significant differences were found ($p < 0.05$), further testing was carried out using *Tukey's post hoc* test.

3. Results and Discussion

Inhibition zone observation at 24 hours

Research on the antibacterial activity of AgChCc nanocomposite towards the formation of inhibition zone of *S. mutans* at concentrations of 6.25; 12.5; 15; 25; and 50 mg/mL observed at 24, 48 and 72 hours. The results of observations made at 24 hours showed no inhibition zone formation (**Figure 1**).

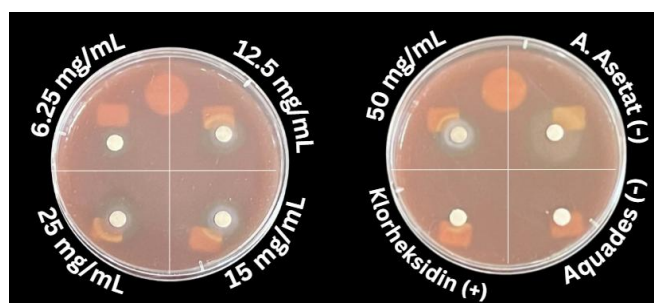


Figure 1 . Zone of inhibition of *S. mutans* at 24 hours

Inhibition zone observation at 48 hours

The observation results were analyzed using the Shapiro-Wilk normality test. Tests were carried out on 48 and 72 hour observations, the results obtained a value of $P > 0.05$ which indicates normally distributed data. The results of the Shapiro-Wilk test can be seen in **Table 1**.

Table1 . Normality test of zone of inhibition at 48 and 72 hours

Group	Shapiro Wilk (48 hours)			Shapiro Wilk (72 hours)		
	Statistic	df	Sig.	Statistic	df	Sig.
Positive control	1.000	3	1.000	1.000	3	1.000
Composite 6.25 mg/mL	1.000	3	0.978	1.000	3	0.987
12.5 mg/mL Composite	1.000	3	0.964	0.993	3	0.843
15 mg/mL Composite	1.000	3	1.000	1.000	3	1.000
25 mg/mL Composite	1.000	3	1.000	1.000	3	1.000
50 mg/mL Composite	1.000	3	1.000	1.000	3	0.962

The statistical test results from the 48-hour observation were normally distributed, then continued with parametric tests using *One Way Anova*. The test results showed a value of $P < 0.05$, indicating a significant difference in the test group, so further tests were carried out with *post hoc Tukey*. The results of the inhibition zone observation after 48 hours can be seen in **Figure 2**.

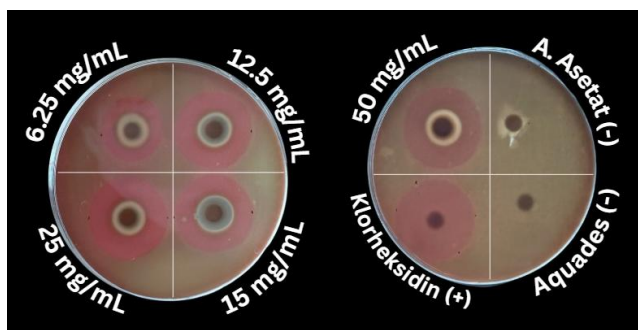


Figure 2 . Zone of inhibition of *S. mutans* at 48 hours

The results of further testing of the inhibition zone of *S. mutans* at 48 hours showed a significant difference with a value of $P < 0.05$. In the AgChCc nanocomposite group, the concentrations of 6.25; 12.5; 15; and 25 mg/mL showed significant differences ($P < 0.05$) with the positive control group. The difference in the inhibition zone formed in the AgChCc 6.25; 12.5; 15; and 25 mg/mL groups showed a smaller inhibition zone compared to the control group. While the 50 mg/mL AgChCc concentration group did not show a significant difference in P value = 0,986 with the control group, although the 50 mg/mL AgChCc concentration did not show a significant difference, the inhibition zone formed in the 50 mg/mL AgChCc concentration was higher than the control. The zone of inhibition at 48 hours observation from the smallest to the largest in order were concentrations of 6.25; 15; 12.5; 25 mg/mL, and 50 mg/mL. The results of the average zone of inhibition in each group can be seen in **Table 2**.

Table2 . Zone of inhibition of *S. mutans*

Group	Zone of Inhibition (mm) $\pm$ SD		<i>P</i> value Anova
	48 hours	72 hours	
Positive control	23.74 $\pm$ 0,76 ^a	24.4 $\pm$ 0.27 ^a	$P < 0.05$
Nanocomposite 6.25 mg/mL	13.96 $\pm$ 0,25 ^c	14.18 $\pm$ 0.42 ^c	
Nanocomposite 12.5 mg/mL	19.74 $\pm$ 0.15 ^b	19.62 $\pm$ 0.03 ^b	
Nanocomposite 15 mg/mL	18.84 $\pm$ 1.9 ^b	19.05 $\pm$ 1.93 ^b	
Nanocomposite 25 mg/mL	20.8 $\pm$ 0.02 ^b	20.98 $\pm$ 0.34 ^b	
50 mg/mL Nanocomposite	24.18 $\pm$ 0.34 ^a	24.45 $\pm$ 0.14 ^a	

^{a-c} in the same column indicates significant differences

Inhibition zone observation at 72 hours

The observation of the inhibition zone at 72 hours showed a significant difference ($p < 0.05$) between the 6.25; 12.5; 15; and 25 mg/mL groups and the control group, with the formation of a lower inhibition zone compared to the control. While the 50 mg/mL AgChCc group was not significantly different ($p > 0.05$) compared to the control group. The AgChCc group at 72 hours observation showed the formation of inhibition zones from the smallest to the largest successively from the AgChCc 6.25; 15; 12.5; 25; and 50 mg/mL groups. The results of the inhibition zone observation at 72 hours can be seen in Figure 4.

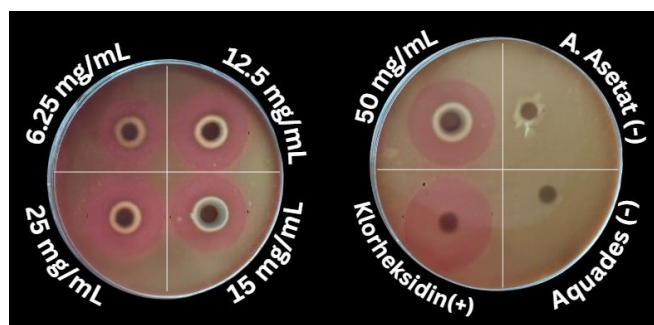


Figure 3. Zone of inhibition of *S. mutans* at 72 hours

Nanocomposite is a material formed from a combination of two or more materials [4]. In this study, the nanocomposite uses a combination of three materials, namely AgNO_3 , *C. citratus*, and chitosan, each of which has antibacterial activity. The results of the antibacterial activity test showed that at the 24-hour observation AgChCc was unable to inhibit the growth of *S. mutans* by not forming an inhibition zone. The results of this study are supported by previous research which states that *S. mutans* requires an incubation time of more than 24 hours to adapt to new environments such as changes in pH [18], nutrient availability, and oxidative stress [19]. The 48 and 72 hour observations showed the formation of inhibition zones directly proportional to the concentration used, the inhibition zone formed was getting bigger as the concentration increased.

The results of the observation of the diameter of the inhibition zone at 48 and 72 hours fell into the classification of strong and very strong inhibition zones. Classification of antibacterial activity based on inhibition zone according to Davis and Stout criteria, divided into: 1) no inhibition zone; 2) weak, i.e. inhibition zone less than 5 mm; 3) moderate, i.e. inhibition zone 5-10 mm; 4) strong, i.e. inhibition zone 11-20 mm; and 5) very strong, i.e. inhibition zone 21-30 mm [20].

The AgChCc composite has stronger antibacterial activity than the individual materials. The AgChCc composite formed by ionic gelation method produces AgChCc in the form of nanoparticles with cross-links between the three materials in the stirring process using a *magnetic stirrer*. Materials in the form of nanocomposites can facilitate the controlled release of antibacterial agents and increase contact with bacterial cells, so that the bacterial cell wall is damaged [21], [22], [23]

The incorporation of three materials into a composite, consisting of AgNO_3 , *C. citratus*, and chitosan has synergy to form a bond. AgNO_3 is reduced by active compounds in *C. citratus* such as saponins, alkaloids, flavonoids, and tannins which are

known to have antibacterial activity [24], [25]. *The active compounds contained in *C. citratus* act as bio reductants by donating electrons contained in the active compounds to convert Ag ions into Ag⁰ by phenolic compounds [6].

The active flavonoid compounds contained in *C. citratus* can inhibit nucleic acid synthesis and damage the permeability of bacterial cell walls, microsomes, and lysosomes through interactions with bacterial DNA [26]. Saponins have the potential as bacterial inhibitors with a mechanism that disrupts the permeability of bacterial cell membranes, causing cell death. This disruption of the cell membrane can trigger damage that results in the release of cell components, such as nucleic acids, proteins, and nucleotides, which ultimately causes lysis of bacterial cells [27]. In addition, polyphenol and phenolic compounds are known to disrupt cytoplasmic function and membrane permeability, damage DNA, and inhibit nucleic acid synthesis in bacterial cells [28].

The synthesized AgNPs are not stable, so a stabilizer such as chitosan is needed. Chitosan contains amine (-NH₂) and hydroxyl (-OH) groups that are not only able to act as reducers by donating ions, but also able to stabilize the synthesized AgNPs so that aggregation does not occur. The formation of AgChCc nanocomposites consisting of three materials, each of which has antibacterial activity with different mechanisms. The mechanism that inhibits bacterial growth occurs through cell wall damage by antibacterial active substances. This damage results in disruption of the integrity of cellular components, so that the process of bacterial respiration cannot take place [24].

AgNPs as an antibacterial starts by AgNPs accumulating on the surface of the bacterial membrane until they enter the bacterial cell. This changes the permeability of the bacteria, damages the DNA, and ultimately kills the bacteria. The size, shape and surface parameters of silver nanoparticles affect the damage to the bacterial membrane. Due to their small size, AgNPs can interact with the peptidoglycan that protects bacteria more easily [29],[30].

Chitosan has antibacterial activity against *S. mutans* because it is a Gram-positive bacterium that has a higher peptidoglycan and lipid content than Gram-negative bacteria. The amine group possessed by the polycationic nature of chitosan allows interaction with lipids in the cell wall, thus damaging the bacterial defense. In addition, the presence of negative charge and acidic nature of teichoic acid in the cell wall of Gram-positive bacteria interact with chitosan, which ultimately damages the structure of the bacterial cell wall [31]. Each of the ingredients that make up the nanocomposite has good antibacterial activity and the synergy of the three ingredients can increase its activity as an antibacterial with the formation of strong and very strong inhibition zones against *S. mutans*.

Inhibition zone observations at 48 and 72 hours showed that several concentration groups showed an increase in the inhibition zone at 72 hours observation compared to 48 hours but at a concentration of 12.5 mg/mL showed a decrease in the inhibition zone. The increase in the inhibition zone in many nanocomposite groups indicates the potential as a bacteriocide at that concentration, while the decrease in the inhibition zone at 72 observations indicates the potential of the concentration is only bacteriostatic. Observation of the inhibition zone from the results of the study cannot conclude the nature of the AgChCc nanocomposite against the growth of *S. mutans* bacteria whether it is bacteriostatic or bactericidal because the zones formed there are increasing and decreasing, so future studies should assess time-kill kinetics to confirm bactericidal vs. bacteriostatic effects.

The results of this study are in line with previous research which revealed that the active fraction of *C. citratus* has antibacterial activity against *S. mutans* bacteria with

the higher the concentration, the greater the diameter of the inhibition zone formed [24]. Previously, research on AgCh nanocomposites synthesized with *Azadirachta indica* was shown to have antimicrobial activity against the growth of *S. mutans* and *Candida albicans* [32]. Furthermore, AgCh nanocomposites synthesized with *Officinale rhizome* showed inhibition of *P. aeruginosa* growth [33]. AgCh nanocomposites synthesized with *Annona squamosa* also proved effective in inhibiting the growth of *E. coli*, *B. subtilis*, *X. campestris*, and *S. aureus* [34]. Another study mentioned that the synthesis of AgNPs with *C. citratus* proved effective in inhibiting the growth of *Bacillus cereus*, *Escherichia coli*, *Salmonella paratyphi*, *Shigella flexneri*, and *Vibrio cholerae* [11].

At 48 and 72 hours of observation, the inhibition zone produced by the positive control was classified as very strong. This is because the positively charged chlorhexidine molecule has the ability to bind strongly with bacterial molecules which are mostly negatively charged. This interaction results in significant adhesion between chlorhexidine and the bacterial cell membrane. Chlorhexidine then disrupts the permeability of the cell membrane, allowing the escape of cytoplasm and low molecular weight cell components through the membrane. As a result, the bacteria experience death [35]. The antibacterial activity test on the negative control using distilled water did not produce an inhibition zone because distilled water is a neutral compound that cannot inhibit bacterial cell growth [36]. Another negative control used is acetic acid, although acetic acid has antibacterial activity, when used as a negative control it does not form an inhibition zone. This can be caused by insufficient concentration to inhibit bacterial growth or the absence of synergistic effects of other active compounds that can affect the antibacterial effect of acetic acid [37].

AgCh nanocomposites synthesized with *C. citratus* potentially have antibacterial activity against *S. mutans* by forming a zone of inhibition that is as large as the positive control at 48 and 72 hours of observation. AgCh nanocomposites can be used as an alternative mouthwash.

This study has several limitations. First, the antibacterial evaluation was conducted *in vitro* against planktonic cultures of *S. mutans*, which may not fully replicate the complex biofilm environment in clinical settings. Second, while the nanocomposite demonstrated concentration-dependent activity, cytotoxicity assessments on human oral cells were not performed, leaving its biocompatibility profile unclear for dental applications. Third, the characterization of nanoparticle size distribution and long-term stability in the composite was limited; advanced techniques like TEM or XRD could provide deeper mechanistic insights. Fourth, the study focused solely on *S. mutans* without evaluating other cariogenic pathogens (e.g., *Lactobacillus* spp.) commonly present in oral biofilms. Lastly, the 72-hour observation period may not reflect prolonged antibacterial efficacy required for clinical use.

4. Conclusion

The results showed that AgChCc nanocomposites have potential as antibacterial against *S. mutans*. The inhibition zone formed is getting bigger as the concentration of AgChCc nanocomposite increases, with a maximum concentration of 50 mg/mL. This nanocomposite shows promise as a natural alternative to chlorhexidine. Further studies with extended observation periods are needed to ensure the bacteriostatic or bactericidal properties of nanocomposites. In addition, further testing is needed to determine the best concentration of nanocomposites as antibacterial agents. Furthermore, antibacterial activity tests need to be carried out against other pathogenic bacteria found in the oral cavity.

Acknowledgments:

The authors would like to express their sincere gratitude to the Faculty of Dentistry, Trisakti University, for providing the essential laboratory facilities and technical support throughout the course of this research. Special thanks are extended to the Department of Oral Biology, Subdivision of Histology, for their invaluable guidance and assistance in the preparation and analysis of the nanocomposites used in this study.

Conflicts of Interest:

The authors declare no conflict of interest regarding the publication of this article.

References

- [1] Malik S, Muhammad K, Waheed Y. *Nanotechnology: A Revolution in modern industry*. Molecules 2023;28. <https://doi.org/10.3390/molecules28020661>.
- [2] Kaur S, Kour K. *Short term side effects of 0.2% and 0.12% chlorhexidine mouthwash*. IP International Journal of Periodontology and Implantology 2020;4:138-140. <https://doi.org/10.18231/j.ijpi.2019.029>.
- [3] Al-Mutairi NH, Hussain Mehdi A, Kadhim J. *Nanocomposites materials definitions, types and some of their applications: A review*. European Journal of Research Development and Sustainability 2022;3
- [4] Ardean C, Davidescu CM, Nemeş NS, et al. *Factors influencing the antibacterial activity of chitosan and chitosan modified by functionalization*. Int J Mol Sci 2021;22. <https://doi.org/10.3390/ijms22147449>.
- [5] Dwina S, Arzi HA, Wisnuwardhani R. *Literature review of silver nanoparticle synthesis using plant extracts as bioreductors and their applications*. 2020;6. <https://doi.org/10.29313/v6i2.23041>.
- [6] Qurraatayun S, Rifai Y, Rante H. *Green synthesis of silver nanoparticles (AgNPs) using lemongrass (Cymbopogon citratus) leaf extract as bioreductor*. Original Article MFF 2022;26:124-128. <https://doi.org/10.20956/mff.v26i3.21047>.
- [7] Suryadi Y, Susilowati DN, Samudra IM-. *Biosynthesis of silver nanoparticles (AgNPs) using Bacillus firmus E65 and its activity against pathogenic microbes*. Agrotek: Journal of Agricultural Industry Technology 2022;16:204-212. <https://doi.org/10.21107/agrotek.v16i2.10785>.
- [8] Kriswandini IL, Diyatri I, Tantiana, et al. *The formation of bacteria biofilm from Streptococcus mutans and Aggregatibacter actinomycetemcomitans as a marker for early detection in dental caries and periodontitis*. Infect Dis Rep 2020;12. <https://doi.org/10.4081/idr.2020.8722>.
- [9] Kawengian SAF, Wuisan J, Leman MA, et al. *Inhibition test of lemongrass leaf extract (Cymbopogon citratus L) against the growth of Streptococcus mutans*. vol. 5. 2017.
- [10] Rakib-Uz-Zaman SM, Hoque Apu E, Muntasir MN, et al. *Biosynthesis of silver nanoparticles from Cymbopogon citratus leaf extract and evaluation of their antimicrobial properties*. Challenges 2022;13-18. <https://doi.org/10.3390/challe13010018>.
- [11] Istatik Badi'ah H. *Chitosan as capping agent for silver nanoparticles*. Indonesian Journal of Chemical Research Indo J Chem Res 2021;9:21-5. <https://doi.org/10.30598>.
- [12] Felicia F, Komariah K, Kusuma I. *Antioxidant potential of lemongrass (Cymbopogon citratus) leaf ethanol extract in HSC-3 cancer cell line*. Tropical Journal of Natural Product Research 2022;6:520-528. <https://doi.org/10.26538/tjnpr/v6i4.10>.
- [13] Melkamu WW, Bitew LT. *Green synthesis of silver nanoparticles using Hagenia abyssinica (Bruce) J.F. Gmel plant leaf extract and their antibacterial and anti-oxidant activities*. Heliyon 2021;7. <https://doi.org/10.1016/j.heliyon.2021.e08459>.

- [14] Prasetyaningtyas T, Prasetya AT, Widiarti N. *Indonesian journal of chemical science synthesis of chitosan-modified silver nanoparticles with basil leaf extract (Ocimum basilicum L.) bioreductor and its activity test as antibacterial*. Vol. 9. 2020
- [15] Hainil S, Sammulia SF, Adella A. *Antibacterial activity of Staphylococcus aureus and Salmonella thypi methanol extract of sea grape (Caulerpa racemosa)*. Jurnal Surya Medika 2022;7:86-95. <https://doi.org/10.33084/jsm.v7i2.3210>.
- [16] Takele E, Feyisa Bogale R, Shumi G, et al. *Green synthesis, characterization, and antibacterial activity of CuO/ZnO nanocomposite using Zingiber officinale Rhizome Extract*. J Chem 2023. <https://doi.org/10.1155/2023/3481389>.
- [17] Magvirah T, Ardhani F. *Inhibition test of Staphylococcus aureus bacteria using tahongai (Kleinhovia hospita L.) leaf extract*. 2019;2.
- [18] Li M, Huang R, Zhou X, et al. *Effect of nicotine on cariogenic virulence of Streptococcus mutans*. Folia Microbiol (Prague). 2016;61:505-512. <https://doi.org/10.1007/s12223-016-0465-8>.
- [19] Syafriza D, Sutadi H, Primasari A, et al. *Spectrophotometric analysis of Streptococcus mutans growth and biofilm formation in saliva and histatin-5 relation to pH and viscosity*. Pesqui Bras Odontopediatria Clin Integr 2021;21. <https://doi.org/10.1590/pboci.2021.004>.
- [20] Mangindaan RJ, Mintjelungan CN, Pangemanan DHC. *Inhibition test of squid ink extract (Loligo sp) against the growth of Streptococcus mutans bacteria*. Journal of E-Biomedicine (EBm) 2019;7:84.
- [21] Abdallah Y, Liu M, Ogunyemi SO, et al. *Bioinspired green synthesis of chitosan and zinc oxide nanoparticles with strong antibacterial activity against rice pathogen Xanthomonas oryzae pv. oryzae*. Molecules 2020;25:4795. <https://doi.org/10.3390/molecules25204795>.
- [22] Ghasemzadeh H, Mahboubi A, Karimi K, et al. *Full polysaccharide chitosan-CMC membrane and silver nanocomposite: synthesis, characterization, and antibacterial behaviors*. Polym Adv Technol 2016;27:1204-10. <https://doi.org/10.1002/pat.3785>.
- [23] Hartati H, Subaer S, Hasri H, et al. *Microstructure and antibacterial properties of chitosan-Fe3O4-AgNP nanocomposite*. Nanomaterials 2022;12:3652. <https://doi.org/10.3390/nano12203652>.
- [24] Erlyn P. *Antibacterial effectiveness of lemongrass (Cymbopogon citratus) active fraction against Streptococcus mutans bacteria*. vol. 6. 2016.
- [25] Yuliningtyas AW, Santoso H, Syauqi A. *Test of active compound content of lemongrass ginger drink (Zingiber officinale and Cymbopogon citratus)*. Scientific Journal of Bioscience. 2019;4:1-6.
- [26] Fitri Yeni L, Wahyuni ES, Mandasari J, et al. *Inhibition test of Cymbopogon citratus and Alpinia purpurata extracts against the growth of Shigella sonnei n.d.*;5:20-81.
- [27] Kurniawati PD. *Antimicrobial activity test of ethanol extract of glodokan tiang (Polyalthia longifolia) leaves*. 2021.
- [28] Lobiuc A, Pavál NE, Mangalagiu II, et al. *Future antimicrobials: Natural and functionalized phenolics*. Molecules 2023;28. <https://doi.org/10.3390/molecules28031114>.
- [29] Mariani H, Mahdi N, Umam K. *Biosynthesis of silver nanoparticles (AgNPs) with zeolite-impregnated kirinyuh (Chromolaena odorata) leaf extract in inhibiting acne-causing bacteria*. Journal of Biosilampari: Journal of Biology 2023;5:187-198. <https://doi.org/10.31540/biosilampari.v5i2.1833>.
- [30] Notriawan D, Nesbah, Ernis G, et al. *Antibacterial activity of chitosan/silver nanoparticle nanocomposite membrane*. Alchemy: Journal Of Chemistry 2021;9:26-31.

- [31] Susanti G, Cahyaningrum SE. *Characterization and effectiveness test of Aloe vera combination chitosan gel as Staphylococcus aureus Antibacterial*. Vol. 11. 2022.
- [32] Dhevishri S, Devi Parameswari B, Hariharan A, et al. *Antimicrobial properties of green synthesized silver and chitosan nanocomposites*. *Bioinformation* 2023;19:745-748. <https://doi.org/10.6026/97320630019745>.
- [33] Wahab S, Muhammad Ali H, Khan M, et al. *Green synthesis and antibacterial assessment of chitosan/silver nanocomposite conjugated with tobramycin against antibiotic resistant Pseudomonas aeruginosa*. *Arabian Journal of Chemistry* 2024;17:105458. <https://doi.org/10.1016/j.arabjc.2023.105458>.
- [34] Kolekar Y, Tamboli F, Gaikwad D, et al. *Biosynthesis of silver nanoparticles using annona squamosa L Seed and Leaves Extract: Evaluation of the Anti-inflammatory, Antifungal, and Antibacterial Potency*. *International Journal Of Pharmaceutical Quality Assurance* 2023;14:377-387. <https://doi.org/10.25258/ijpqa.14.2.23>.
- [35] Azzahra F, Hayati M. *Activity test of Centella asiatica (L). Urb) against the growth of Streptococcus mutans*. *Journal of B-Dent* 2018;5:9-19.
- [36] Sangadji T, Niwele A, Intan D, et al. *Antibacterial activity test of 70% ethanol extract of mangkokan leaves (Nothopanax scutellarium Merr.) against Propionibacterium acne bacteria using the pitting diffusion method*. *JIKKI* 2022;2:145-52.
- [37] Anggraini AC, Retnaningrum E. *Effectiveness and quality of kombucha fermented product with combination of bread fruit leaf tea (Artocarpus altilis (Parkinson) Fosberg) and lemon (Citrus limon (L.) Burm. f.) substrates*. *Food Processing* 2023;8:97-106.