



International Journal of
**Innovation in
Mechanical
Engineering
and
Advanced
Materials**

COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA

W. Dahani^{1}, R. Sundari², S. Subandrio¹, I. Marwanza¹, and Ivetta¹*

¹Department of Mining Engineering, Faculty of Earth Technology and Energy, Universitas Trisakti, Jakarta, INDONESIA

²Department of Mechanical Engineering, Universitas Mercu Buana, Jakarta, INDONESIA

Abstract

Extraction of heavy metals from mineral concentrate applying leaching acids is a major issue due to simple, fast, and economical process. This article aims to present the application of acetic acid and sulfuric acid for lead (Pb) extraction from galena concentrate applying roasting (600°C and 60 min.) and peroxide oxidant (0.5 M) for 60 min. leaching process. Nowadays, lead has been broadly applied for batteries, besides for PVC tubes, chemicals, paint color, and alloys for joint. The peroxide increases the percentage of Pb extraction. This study shows the effect of acid concentrations (1.0 M, 1.5 M, and 2.0 M), temperatures (30, 50, and 70°C), and stirring speed (200, 400, and 600 rpm) on Pb extraction from galena. A particle size of galena ≤ 200 mesh after roasting has been used for leaching process. AAS has been used to determine Pb concentration in solution after leaching process. This study shows that acetic acid is a better leaching agent rather than sulfuric acid due to lead sulfate precipitation. Optimization result shows leaching with acetic acid achieved 35.64 ppm Pb extraction using 2.0 M acetic acid, 50°C, and stirring speed of 200 rpm. This study used low-cost acids as leaching agent for Pb recovery that can be viewed as a preliminary breakthrough in heavy metal recovery. The simple leaching technique looks promising for future application on heavy metal separation from mining mineral.

Keywords: Acetic Acid, Galena Concentrate, Lead Extraction, Sulfuric Acid, AAS.

*Corresponding author: Tel. +62 21 566 3232; Fax +62 21 567 3001
E-mail address: wiwik_d@trisakti.ac.id; rita.sundari@mercubuana.ac.id

DOI: 10.22441/ijimeam.v4i2.17135

1. Introduction

Galena is a mineral with its chemical formula as PbS (lead sulfide). Galena ores are usually in association with other minerals like sphalerite, marcasite, pyrite, chalcopyrite, and other hydrothermal minerals[1]. Galena is found as veins in metamorphic deposit due to hydrothermal process. In general, mineralization of galena is related to sedimentation process of upper limestone formation, volcanic rock, granite igneous rock, and alluvial deposit[2]. Exploitation of galena mineral generally uses dump-truck and backhoe heavy equipment to excavate galena after blasting.

Galena is the main source to extract Pb from its concentrate[3]. Fig. 1 shows the galena mineral found in several rocks. Due to its corrosive resistance, up to date, lead has broadly applied for many purposes especially for lead batteries. Besides,

lead is used as an isolator for PVC (polyvinyl chloride) tubes, as alloy for joining lines, pigments, lead glass crystal, ammunition, and as protecting material for nuclear reactor. Since galena is found in many places, lead has been used in many industries due to economic reason.

Ongoing with the extraction process of Pb from galena, many previous works reported pyrometallurgy and hydrometallurgy routes[1,4-6,7-8].



Fig. 1. Galena mineral

Previous investigations concerned with several factors such as environmental problems with dust, SO₂, and volatile lead liquid applying pyrometallurgical process[6], and expensive and toxic leaching agent applied in hydrometallurgical process[4,8-9]. Besides the two routes mentioned above, electrometallurgical route has also been applied to produce metal from its mineral concentrate using electrical energy as the metal ion reduced at the cathode in electrolysis[10]. Mubarok[8] studied the effect of acetic acid concentrations on Pb leaching using shrinkage core model. Dessy[5] and Anugrah[4] applied fluorosilicic acid and peroxide to extract Pb from galena concentrate to study the parameter effects (leaching time, leaching temperature, acid concentration, particle size, and stirring speed) on Pb leaching process. Suryana[1] studied the effect of peroxide and lead oxide cathode from used batteries on Pb leaching. Moreover, Feng[11] conducted separation of galena and pyrite applying serpentine as depressant, while Feng[12] reported separation of galena and chalcopyrite applying highly efficient, non-toxic, biodegradable hydroxyethyl cellulose as depressant and H₂O₂ in flotation process, and Wang[7] separated galena from sphalerite using flotation through chelation with different nitrogen functional groups.

Ongoing with metal recovery from some mineral wastes that induced major issue in mining field, previous studies[13–15] reported some investigations on other metal recovery using leaching acids. Agatzini[13] reported titanium recovery from bauxite mineral applying diluted sulfuric acid at atmospheric pressure, while Barakat[14] reported indium recovery from wire scrap using H₃PO₄ leaching and precipitated as indium phosphate. Other study on tin recovery from copper waste was reported by Nurul[15] using HCl and the result found almost 60% tin dissolved in 2 M HCl at 80°C and 8h leaching. Considering the pollution effect, toxic and expensive leaching agents, this study attempts to use low cost and less toxic acids (acetic acid and sulfuric acid) separately as

comparative study using peroxide (H₂O₂) oxidant with galena roasting treatment prior to leaching process. The work investigates the effects of acid concentrations (1.0 M, 1.5 M, and 2.0 M), leaching temperatures (30, 50, and 70°C), and stirring speed (200 rpm, 400 rpm, and 600 rpm) on Pb leaching from galena concentrate. The AAS (atomic absorption spectrophotometer) will be used for determination of Pb extraction.


2. Experimental and Procedures

2.1 Material and Apparatus

The chemicals applied in this study were 1.0–2.0 M acetic acid (CH₃COOH), 1.0–2.0 M sulfuric acid (H₂SO₄), and 0.5 M hydrogen peroxide (H₂O₂). This study used beaker glass, measured glass, filter paper, stirrer, analytical balance, hot plate, thermometer, muffle furnace, AAS and XRF equipment.

2.2 Roasting

The galena ores were obtained from a flotation plant of galena in West Java Province, Indonesia. The roasting process of galena ores was conducted at about 500–700°C for 60 min. until a dark brown sample yielded. The chemical reaction (1) during roasting is as follows:



During roasting, the galena was undergone oxidation to form lead oxide and toxic SO₂ gas. The roasting process was done in a chamber provided with an exhauster in order to remove the toxic SO₂ gas resulted from the chemical reaction above to avoid chamber pollution. After roasting and drying, a sieve shaker was used to filter the mineral powder to obtain the desired particle size, i.e., ≤ 200 mesh. Then, the galena concentrates in powder form obtained from rusting process with given particle size was prepared for leaching process to extract Pb. Fig. 2 shows the galena concentrate in powder form.



Fig. 2. Galena concentrate in powder form after roasting process

2.3 Leaching

The leaching procedure is given as follows: 5g galena concentrate from roasting dissolved in acetic acid. A 0.5 M hydrogen peroxide was added to galena concentrate in acetic acid in a beaker glass. The leaching process of Pb from galena concentrate using acetic acid is a modified process from earlier study[8]. This procedure was repeated for galena concentrate in sulfuric acid. The given acid concentration was made following the simple dilution rule. i.e.

$$V_1 \times C_1 = V_2 \times C_2 \quad (2)$$

where:



V_1 = initial acid volume (ml)

C_1 = initial acid concentration (ppm)

V_2 = final acid volume (ml)

C_2 = final acid concentration (ppm)

During leaching process, the chemical reaction (3) referred to reaction of galena concentrate with acetic acid (CH_3COOH), while the chemical reaction (4) referred to reaction of galena concentrate with sulfuric acid (H_2SO_4). The flow diagram of this comparative study applying acetic acid and sulfuric acid as leaching agent for Pb extraction is shown in Fig. 3.



The leaching process was used to examine the effect of acid concentrations (1.0 M, 1.5 M, and 2.0 M), leaching temperatures (30, 50, 70°C), and stirring speed (200, 400, and 600 rpm).

2.4 AAS examination

An Analytik Jena with acetylene/nitrous oxide flame for atomizer of atomic absorption spectrophotometer was used to determine Pb concentrations in leaching solutions using acetic acid and sulfuric acid leaching agents. The lamp current of hollow cathode HCl lamp is set to be 2–20 mA,

2.5 XRF examination

A PANalytical, type Minipal 4 XRF (X-Ray Fluorescence) Spectrophotometer was used to analyze qualitatively and quantitatively chemical composition of galena ore.

3. Results and Discussion

3.1 Pb extraction from galena concentrate

Table 1 shows the data of Pb extract in terms of type of leaching acid, acid concentration, leaching temperature, and stirring speed. The Pb concentrations have been determined by AAS.

Table 1 Pb extraction with respect to leaching acid, temperature, and stirring speed. H_2O_2 oxidant. AAS assay

Acetic acid conc. molar	Temp. °C	Stirring speed rpm	Pb conc. ppm
1 M	50	200	19.66
1.5 M	50	200	29.63
2M	50	200	35.64
1 M	30	200	13.90
1 M	50	200	L8.09
1 M	70	200	23.92
1 M	50	200	19.66
1 M	50	400	25.97
1 M	50	600	30.74
Sulfuric acid conc. molar	Temp. °C	Stirring speed rpm	Pb conc. ppm
1 M	50	200	7.18
1.5 M	50	200	11.46
2 M	50	200	17.63
1 M	30	200	5.16
1 M	50	200	7.18
1 M	70	200	11.21
1 M	50	200	5.67
1 M	50	400	5.93
1 M	50	600	7.18

3.2 Effect of acid concentration on Pb leaching

As shown in Fig. 4, acetic acid as leaching agent gives more effect on Pb leaching from galena compared to that of sulfuric acid. The AAS assayed Pb concentration in the leaching solution. Pb(II) ion and sulfate ion may form Pb-sulfate deposit or precipitate, therefore, less Pb(II) ion existence in leaching solution. In general, Table 1 shows that increase concentration of both leaching acids from 1.0 M to 2.0 M yielding increased Pb concentration in leaching solution. It is reasonable since the acid may withdraw the Pb from galena matrix to yield salt of Pb in the form of Pb acetate and Pb sulfate and therefore, the Pb in the form of Pb(II) ion. Furthermore, increase of leaching temperature from 50°C to 70°C causes increased Pb extraction for both acids at constant acid concentration and constant stirring speed. It is not surprising since increased temperature causes increased solubility of Pb(II) ion in leaching solution. Moreover, Table 1 shows increased stirring speed from 200 rpm to 600 rpm

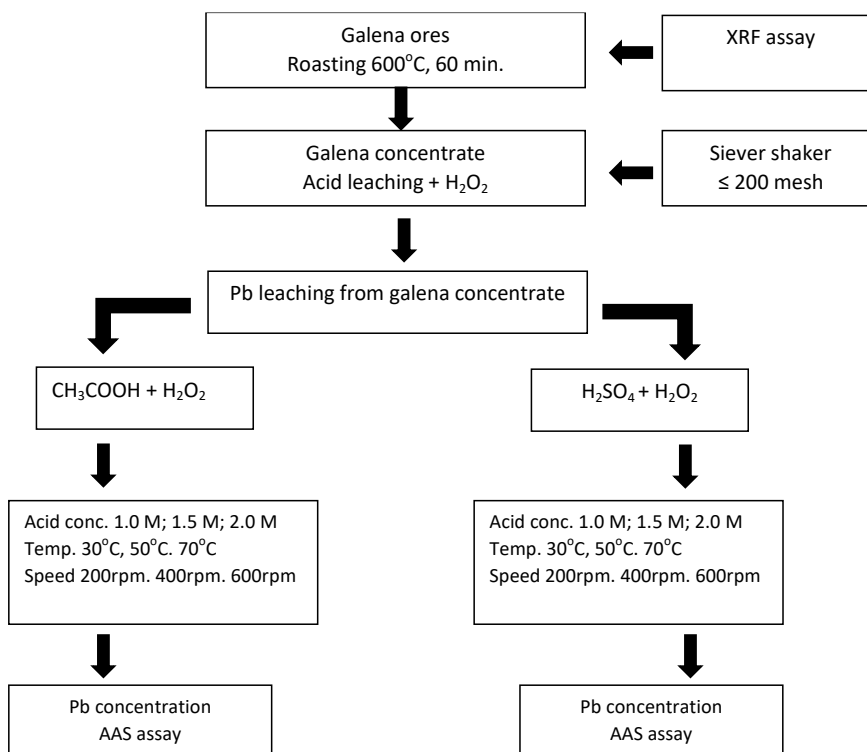


Fig. 3. The flowchart diagram of Pb leaching from galena concentrate in this study

causes increased Pb extraction for both acids, however, the increment is not too significant for sulfuric acid as leaching agent compared to that of acetic acid. It seems that thermal effect (temperature) is more dominant rather than mechanical effect (stirring speed) addressing to Pb extraction from galena matrix.

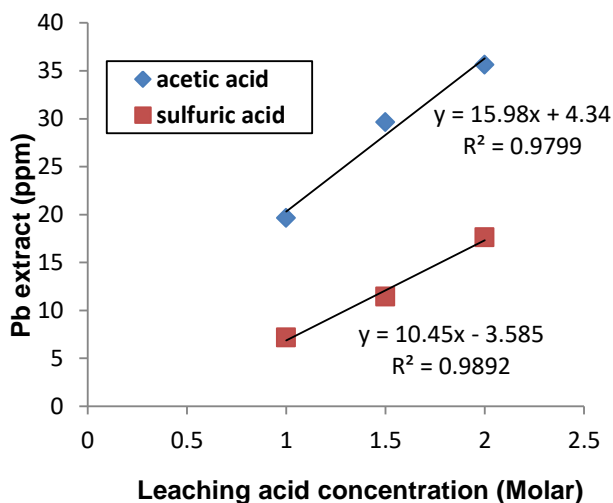


Fig. 4. Pb extraction from galena using acetic and sulfuric acids. 50°C. 200 rpm. H₂O₂ oxidant. AAS assay

The temperature effect (Fig. 5) gives less influence

on Pb extraction from galena compared to the effect of acid concentration (Fig. 4). With regard to acetic acid on Pb leaching, an increase of Pb concentration from about 20 ppm to almost 40 ppm as shown by Fig. 4, while an increase of Pb concentration from about 15 ppm to about 25 ppm as shown by Fig. 5. The effect of acid concentration on Pb leaching almost doubled the effect of temperature with respect to acetic acid.

3.3 Effect of leaching temperature on Pb leaching

The Pb leaching effect using acetic acid due to both increase of acid concentration (Fig. 4) and temperature (Fig. 5) is greater than the leaching effect with sulfuric acid. As already mentioned above, the formation of Pb sulfate deposit caused lower concentration of Pb(II) ion in leaching solution applying sulfuric acid leaching.

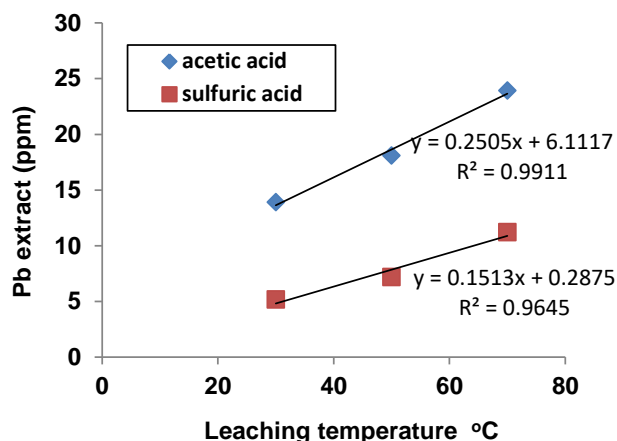


Fig. 5. Pb extraction from galena using acetic and sulfuric acids. Acid concentration 1.0 M, 200 rpm. H_2O_2 oxidant. AAS assay.

As shown by Fig. 4 and Fig. 5, the trend of Pb leaching from galena concentrate at given varied acid concentrations (1.0 M, 1.5 M, and 2.0 M) and given leaching temperature (30°C, 50°C, and 70°C) show almost linearly. The range of linearity (Fig. 4 and Fig. 5) in the range of R^2 of 0.96–0.99, which is moderately linear both for given acid concentration and temperature effects on Pb extraction. The upper limit of acid concentration was made to be 2.0 M on the reason of chemical safety, while the temperature was limited to 70°C due to energy reason. There is a consistence between concentrations of Pb extract and both effects of acid concentration and temperature applying either acetic acid or sulfuric acid as leaching agent.

3.4 Effect of stirring speed on Pb leaching

This article has also investigated the effect of stirring speed (200 rpm, 400 rpm, and 600 rpm) on Pb leaching applying acetic and sulfuric leaching acids, as shown by Fig. 6. Furthermore, Fig. 6 shows that effect of given varied stirring speed on Pb leaching from galena is not too significant particularly using sulfuric acid as leaching agent. As shown by other effects earlier (acid concentration and leaching temperature), the effect of stirring speed on Pb leaching from galena concentrate shows that acetic acid leaching extracted more Pb(II) ion from galena rather than leaching by sulfuric acid. This phenomenon is due to the formation of Pb sulfate precipitate. According to the rule of solubility, the solubility product (K_{sp}) of Pb sulfate is much smaller than that one of Pb acetate at given range of temperature. The linearity of stirring speed effect particularly for sulfuric acid leaching shows no significant effect on Pb extraction with varied

given stirring speed (200, 400, and 600 rpm).

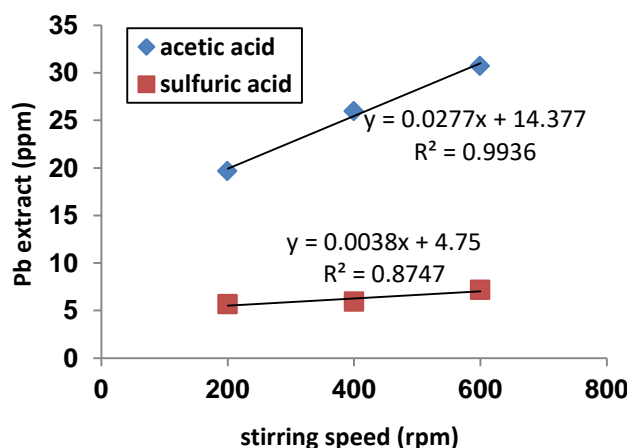


Fig. 6. Pb extraction from galena using acetic and sulfuric acids. Acid concentration 1.0 M, 50°C. H_2O_2 oxidant. AAS assay.

3.5 XRF examination of galena ore

As mentioned earlier, galena mineral is commonly found with other minerals such as sphalerite, marcasite, pyrite, chalcocopyrite[1,7]. Sphalerite is a sulfide mineral with chemical formula as $(Zn, Fe)S$ that is commonly called as zinc blende. Table 2 shows that the result of XRF examination reported Fe (32.8%) and Zn (26.6%) together with Pb (13.9%) as transition elements in galena ores. Marcasite and pyrite, both are sulfide minerals with same chemical formula, i.e., FeS_2 , however, they have different crystal structure. Marcasite has orthorhombic structure, while pyrite has cubic crystal structure. In addition, marcasite is less dense and lighter than pyrite, therefore, marcasite is more brittle. Chalcocopyrite is a copper iron sulfide mineral (Cu_5FeS_4).

Several studies reported the flotation separation of galena from pyrite using serpentine depressant[11], isolation of galena from chalcocopyrite using HEC depressant[12], and separation of galena from sphalerite using nitrogen functional groups[7]. Table 2 reported copper as 3.29% and sulfur as 4.8% related to the existence of chalcocopyrite in galena ore. Thus, there are the important minerals in galena ores based on their concentrations. Furthermore, it is apparently that transition elements look dominant in galena ores (Table 2). It should be noted that rare earth metals (lanthanum, europium, and ytterbium) are also detected in galena ore (Table 2). Fig. 6 shows the XRF spectra of galena ore before roasting treatment.

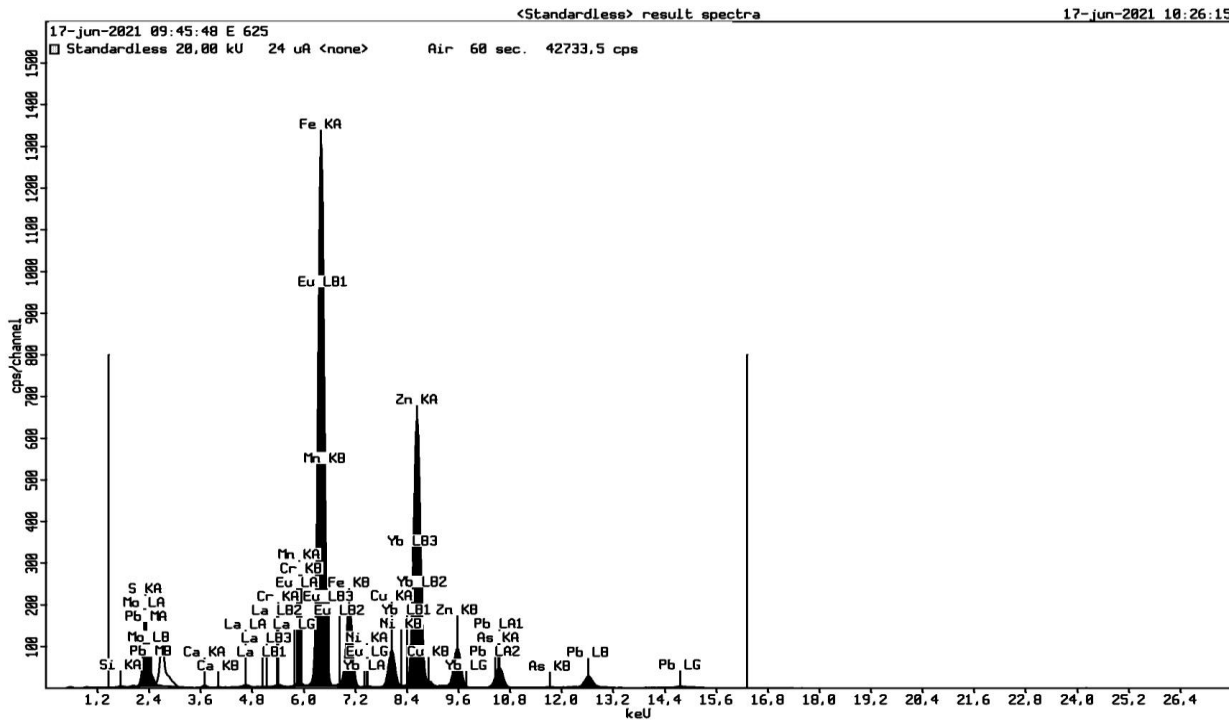


Fig. 6. XRF spectra of galena ore before roasting

Table 2. XRF examination of galena ores from West Java Province, Indonesia.

Chemical element	Content (%)
Si	1.0
S	4.8
Ca	0.28
Cr	0.095
Mn	0.13
Fe	32.8
Pb	13.9
Ni	0.05
Cu	3.29
Zn	26.6
As	0.78
Mo	16.0
La	0.03
Eu	0.3
Yb	0.1

4. Conclusions

Previous study reported Pb leaching from galena concentrate using expensive and toxic leaching agents. However, this study attempts to apply low-cost acids (acetic and sulfuric acids) as leaching agent for Pb extraction from galena concentrate. Further study needs modification on leaching parameters addressing to particle size, selection of oxidant, and leaching time to get results improvement.

5. Acknowledgements

The authors would like to thank all staff of

chemical laboratories to give support to this research project. A thankful acknowledgement is also addressed to the Head Department of Mining, Universitas Trisakti for contribution on facilities needed by this research. Acknowledgement is sent to PT. Galena Maju Karya Mandiri for preparing sample of galena concentrate and XRF facilitation.

References

- [1] Suryana, Anistasia, M. & Amreza, E. Pengaruh penambahan oksidator pada proses pelindian oksidatif konsentrat galena (Effect of oxidator addition on oxidative leaching process of galena concentrate), Department of Metallurgy Engineering, Universitas Sultan Tirtayasa, Banten, 2019.
- [2] Wang, C. Deng, J. Tao, L. Sun, W. Xiao, Q. & Gao, Z. Enhanced flotation of chalcopyrite particles by grinding with cylinder media. *Minerals Engineering*, 2022; 188: 107827.
- [3] Liu, Q. Li, H. Jin, G. Zheng, K. & Wang, L. Assessing the influence of humic acids on the weathering of galena and its environmental implications. *Ecotoxicology & Environmental Safety*, 2018; 158: 230 – 238.
- [4] Anugrah, R.I. Amalia, D. & Mubarak, M.Z. Parameters that affect the dissolution of Indonesian galena concentrate in fluorosilicic acid and hydrogen peroxide. *Indonesian Mining Journal*, 2018; 21: 89 – 97.

- [5] Amalia, D. Ramanda, Y. & Maryono. Extraction of lead from galena concentrates using fluosilicic acid and peroxide. *Indonesian Mining Journal*, 2017; 20: 69 – 80.
- [6] Golpayegani, M.H. & Abdollahadeh, H.H. Optimization of operating parameters and kinetics for chloride leaching of lead from melting furnace slag. *Transactions of Nonferrous Metals Society of China*, 2017; 27: 2704 – 2714.
- [7] Wang, J. Ji, Y. Cheng, S. Li, S. Cao, J. & Chen, P. Selective flotation separation of galena from sphalerite via chelation collectors with different nitrogen functional groups. *Applied Surface Science*, 2021; 568: 150956.
- [8] Mubarak, Z. Studi perilaku pelindian timbal dari bijih galena Nanggung, Kabupaten Bogor, dalam larutan asam asetat dan oksidator hydrogen peroksida (The study of lead leaching profile from galena ores in Nanggung, Bogor Residence, in acetic acid solution and hydrogen peroxide oxidator), Department of Metallurgy Engineering, Faculty of Mining and Petroleum Engineering, Institut Teknologi Bandung, 2014.
- [9] Nnanwube, I.A. & Onukwuli, O.D. Hydrometallurgical processing of a Nigerian galena ore in nitric acid: Characterization and dissolution kinetics. *Journal of Minerals and Materials Characterization and Engineering*, 2018; 6: 271 – 293.
- [10] Tarumingkeng, S. Termodinamika dalam memahami proses pengolahan mineral (The thermodynamics of understanding mineral treatment processing), Department of Physics, Faculty of Math and Science, Institut Teknologi Bandung, 2016.
- [11] Feng, B. Zhang, W. Guo, Y. Wang, T. Luo, G. Wang, H. & He, G. The flotation separation of galena and pyrite using serpentine as depressant. *Powder Technology*, 2019; 342: 486 – 490.
- [12] Feng, B. Jiao, X. Wang, H. Peng, J. & Yang, G. Improving the separation of chalcopyrite and galena by surface oxidation using hydroxyethyl cellulose as depressant. *Minerals Engineering*, 2021; 160: 106657.
- [13] Agatzini, L. Oustadakis, P. Tsakiridis, P. & Markopoulos, Ch. Titanium leaching from red mud by diluted sulfuric acid at atmospheric pressure. *Journal of Hazardous Materials*, 2008; 157: 579 – 586.
- [14] Barakat, M.A. Recovery of lead, tin and indium from alloy wire scrap. *Hydrometallurgy*, 1998; 49: 63 – 73.
- [15] Nurul, A.J. Suhaina, I. & Alif, N.A. Recovery of tin from copper dross by acid leaching. *IOP Conf. Series: Materials Science & Engineering*. 2019; 701(1): 012019.

COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA

by Wiwik Dahani

Submission date: 16-Feb-2023 11:24AM (UTC+0700)

Submission ID: 2015401711

File name: Artikel_Rita_Wiwik_IJIMEAM.pdf (425.42K)

Word count: 3757

Character count: 19610

COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA

W. Dahani^{1*}, R. Sundari², S. Subandrio¹, I. Marwanza¹, and Ivetta¹

¹Department of Mining Engineering, Faculty of Earth Technology and Energy, Universitas Trisakti, Jakarta, INDONESIA

²Department of Mechanical Engineering, Universitas Mercu Buana, Jakarta, INDONESIA

Abstract

Extraction of heavy metals from mineral concentrate applying leaching acids is a major issue due to simple, fast, and economical process. This article aims to present the application of acetic acid and sulfuric acid for lead (Pb) extraction from galena concentrate applying roasting (600°C and 60 min.) and peroxide oxidant (0.5 M) for 60 min. leaching process. Nowadays, lead has been broadly applied for batteries, besides for PVC tubes, chemicals, paint color, and alloys for joint. The peroxide increases the percentage of Pb extraction. This study shows the effect of acid concentrations (1.0 M, 1.5 M, and 2.0 M), temperatures (30, 50, and 70°C), and stirring speed (200, 400, and 600 rpm) on Pb extraction from galena. A particle size of galena ≤ 200 mesh after roasting has been used for leaching process. AAS has been used to determine Pb concentration in solution after leaching process. This study shows that acetic acid is a better leaching agent rather than sulfuric acid due to lead sulfate precipitation. Optimization result shows leaching with acetic acid achieved 35.64 ppm Pb extraction using 2.0 M acetic acid, 50°C, and stirring speed of 200 rpm. This study used low-cost acids as leaching agent for Pb recovery that can be viewed as a preliminary breakthrough in heavy metal recovery. The simple leaching technique looks promising for future application on heavy metal separation from mining mineral.

Keywords: Acetic Acid, Galena Concentrate, Lead Extraction, Sulfuric Acid, AAS.

*Corresponding author: Tel. +62 21 566 3232; Fax +62 21 567 3001
E-mail address: wiwik_d@trisakti.ac.id; rita.sundari@mercubuana.ac.id

DOI: 10.22441/ijimeam.v4i2.17135

1. Introduction

Galena is a mineral with its chemical formula as PbS (lead sulfide). Galena ores are usually in association with other minerals like sphalerite, marcasite, pyrite, chalcopyrite, and other hydrothermal minerals[1]. Galena is found as veins in metamorphic deposit due to hydrothermal process. In general, mineralization of galena is related to sedimentation process of upper limestone formation, volcanic rock, granite igneous rock, and alluvial deposit[2]. Exploitation of galena mineral generally uses dump-truck and backhoe heavy equipment to excavate galena after blasting.

Galena is the main source to extract Pb from its concentrate[3]. Fig. 1 shows the galena mineral found in several rocks. Due to its corrosive resistance, up to date, lead has broadly applied for many purposes especially for lead batteries. Besides,

lead is used as an isolator for PVC (polyvinyl chloride) tubes, as alloy for joining lines, pigments, lead glass crystal, ammunition, and as protecting material for nuclear reactor. Since galena is found in many places, lead has been used in many industries due to economic reason.

Ongoing with the extraction process of Pb from galena, many previous works reported pyrometallurgy and hydrometallurgy routes[1,4-6,7-8].




Fig. 1. Galena mineral

Previous investigations concerned with several factors such as environmental problems with dust, SO₂, and volatile lead liquid applying pyrometallurgical process[6], and expensive and toxic leaching agent applied in hydrometallurgical process[4,8-9]. Besides the two routes mentioned above, electrometallurgical route has also been applied to produce metal from its mineral concentrate using electrical energy as the metal ion reduced at the cathode in electrolysis[10]. Mubarak[8] studied the effect of acetic acid concentrations on Pb leaching using shrinkage core model. Dessy[5] and Anugrah[4] applied fluorosilicic acid and peroxide to extract Pb from galena concentrate to study the parameter effects (leaching time, leaching temperature, acid concentration, particle size, and stirring speed) on Pb leaching process. Suryana[1] studied the effect of peroxide and lead oxide cathode from used batteries on Pb leaching. Moreover, Feng[11] conducted separation of galena and pyrite applying serpentine as depressant, while Feng[12] reported separation of galena and chalcopyrite applying highly efficient, non-toxic, biodegradable hydroxyethyl cellulose as depressant and H₂O₂ in flotation process, and Wang[7] separated galena from sphalerite using flotation through chelation with different nitrogen functional groups.

Ongoing with metal recovery from some mineral wastes that induced major issue in mining field, previous studies[13–15] reported some investigations on other metal recovery using leaching acids. Agatzini[13] reported titanium recovery from bauxite mineral applying diluted sulfuric acid at atmospheric pressure, while Barakat[14] reported indium recovery from wire scrap using H₃PO₄ leaching and precipitated as indium phosphate. Other study on tin recovery from copper waste was reported by Nurul[15] using HCl and the result found almost 60% tin dissolved in 2 M HCl at 80°C and 8h leaching. Considering the pollution effect, toxic and expensive leaching agents, this study attempts to use low cost and less toxic acids (acetic acid and sulfuric acid) separately as

comparative study using peroxide (H₂O₂) oxidant with galena roasting treatment prior to leaching process. The work investigates the effects of acid concentrations (1.0 M, 1.5 M, and 2.0 M), leaching temperatures (30, 50, and 70°C), and stirring speed (200 rpm, 400 rpm, and 600 rpm) on Pb leaching from galena concentrate. The AAS (atomic absorption spectrophotometer) will be used for determination of Pb extraction.

2. Experimental and Procedures

2.1 Material and Apparatus

The chemicals applied in this study were 1.0–2.0 M acetic acid (CH₃COOH), 1.0–2.0 M sulfuric acid (H₂SO₄), and 0.5 M hydrogen peroxide (H₂O₂). This study used beaker glass, measured glass, filter paper, stirrer, analytical balance, hot plate, thermometer, muffle furnace, AAS and XRF equipment.

2.2 Roasting

The galena ores were obtained from a flotation plant of galena in West Java Province, Indonesia. The roasting process of galena ores was conducted at about 500–700°C for 60 min. until a dark brown sample yielded. The chemical reaction (1) during roasting is as follows:



During roasting, the galena was undergone oxidation to form lead oxide and toxic SO₂ gas. The roasting process was done in a chamber provided with an exhauster in order to remove the toxic SO₂ gas resulted from the chemical reaction above to avoid chamber pollution. After roasting and drying, a sieve shaker was used to filter the mineral powder to obtain the desired particle size, i.e., ≤ 200 mesh. Then, the galena concentrates in powder form obtained from rusting process with given particle size was prepared for leaching process to extract Pb. Fig. 2 shows the galena concentrate in powder form.



Fig. 2. Galena concentrate in powder form after roasting process

2.3 Leaching

The leaching procedure is given as follows: 5g galena concentrate from roasting dissolved in acetic acid. A 0.5 M hydrogen peroxide was added to galena concentrate in acetic acid in a beaker glass. The leaching process of Pb from galena concentrate using acetic acid is a modified process from earlier study[8]. This procedure was repeated for galena concentrate in sulfuric acid. The given acid concentration was made following the simple dilution rule. i.e.

$$V_1 \times C_1 = V_2 \times C_2 \quad (2)$$

where:



V_1 = initial acid volume (ml)

C_1 = initial acid concentration (ppm)

V_2 = final acid volume (ml)

C_2 = final acid concentration (ppm)

During leaching process, the chemical reaction (3) referred to reaction of galena concentrate with acetic acid (CH_3COOH), while the chemical reaction (4) referred to reaction of galena concentrate with sulfuric acid (H_2SO_4). The flow diagram of this comparative study applying acetic acid and sulfuric acid as leaching agent for Pb extraction is shown in Fig. 3.



The leaching process was used to examine the effect of acid concentrations (1.0 M, 1.5 M, and 2.0 M), leaching temperatures (30, 50, 70°C), and stirring speed (200, 400, and 600 rpm).

2.4 AAS examination

An Analytik Jena with acetylene/nitrous oxide flame for atomizer of atomic absorption spectrophotometer was used to determine Pb concentrations in leaching solutions using acetic acid and sulfuric acid leaching agents. The lamp current of hollow cathode HCl lamp is set to be 2–20 mA,

2.5 XRF examination

A PANalytical, type Minipal 4 XRF (X-Ray Fluorescence) Spectrophotometer was used to analyze qualitatively and quantitatively chemical composition of galena ore.

3. Results and Discussion

3.1 Pb extraction from galena concentrate

Table 1 shows the data of Pb extract in terms of type of leaching acid, acid concentration, leaching temperature, and stirring speed. The Pb concentrations have been determined by AAS.

Table 1 Pb extraction with respect to leaching acid, temperature, and stirring speed. H_2O_2 oxidant. AAS assay

Acetic acid conc. molar	Temp. °C	Stirring speed rpm	Pb conc. ppm
1M	50	200	19.66
1.5 M	50	200	29.63
2M	50	200	35.64
1M	30	200	13.90
1M	50	200	18.09
1M	70	200	23.92
1M	50	200	19.66
1M	50	400	25.97
1M	50	600	30.74

Sulfuric acid conc. molar	Temp. °C	Stirring speed rpm	Pb conc. ppm
1M	50	200	7.18
1.5 M	50	200	11.46
2 M	50	200	17.63
1M	30	200	5.16
1M	50	200	7.18
1M	70	200	11.21
1M	50	200	5.67
1M	50	400	5.93
1M	50	600	7.18

3.2 Effect of acid concentration on Pb leaching

As shown in Fig. 4, acetic acid as leaching agent gives more effect on Pb leaching from galena compared to that of sulfuric acid. The AAS assayed Pb concentration in the leaching solution. Pb(II) ion and sulfate ion may form Pb-sulfate deposit or precipitate, therefore, less Pb(II) ion existence in leaching solution. In general, Table 1 shows that increase concentration of both leaching acids from 1.0 M to 2.0 M yielding increased Pb concentration in leaching solution. It is reasonable since the acid may withdraw the Pb from galena matrix to yield salt of Pb in the form of Pb acetate and Pb sulfate and therefore, the Pb in the form of Pb(II) ion. Furthermore, increase of leaching temperature from 50°C to 70°C causes increased Pb extraction for both acids at constant acid concentration and constant stirring speed. It is not surprising since increased temperature causes increased solubility of Pb(II) ion in leaching solution. Moreover, Table 1 shows increased stirring speed from 200 rpm to 600 rpm



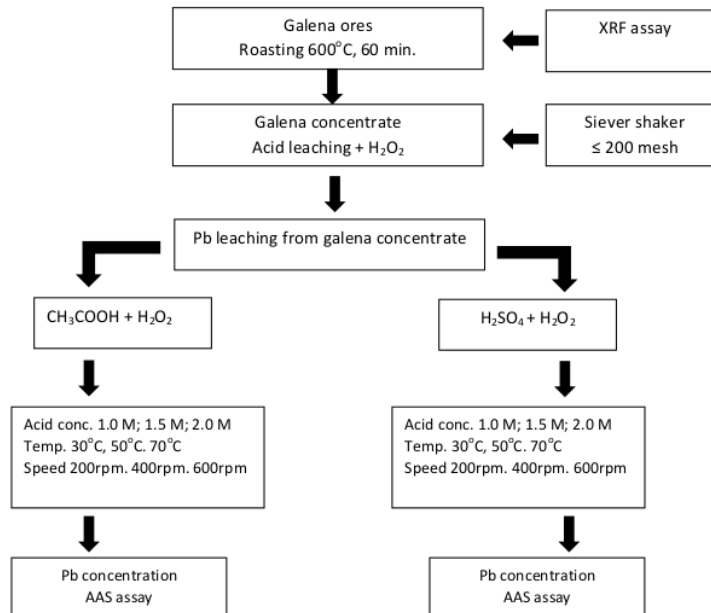


Fig. 3. The flowchart diagram of Pb leaching from galena concentrate in this study

causes increased Pb extraction for both acids, however, the increment is not too significant for sulfuric acid as leaching agent compared to that of acetic acid. It seems that thermal effect (temperature) is more dominant rather than mechanical effect (stirring speed) addressing to Pb extraction from galena matrix.

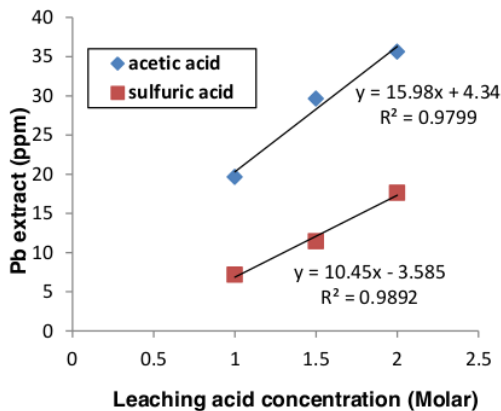


Fig. 4. Pb extraction from galena using acetic and sulfuric acids. 50°C. 200 rpm. H₂O₂ oxidant. AAS assay

The temperature effect (Fig. 5) gives less influence

on Pb extraction from galena compared to the effect of acid concentration (Fig. 4). With regard to acetic acid on Pb leaching, an increase of Pb concentration from about 20 ppm to almost 40 ppm as shown by Fig. 4, while an increase of Pb concentration from about 15 ppm to about 25 ppm as shown by Fig. 5. The effect of acid concentration on Pb leaching almost doubled the effect of temperature with respect to acetic acid.

3.3 Effect of leaching temperature on Pb leaching

The Pb leaching effect using acetic acid due to both increase of acid concentration (Fig. 4) and temperature (Fig. 5) is greater than the leaching effect with sulfuric acid. As already mentioned above, the formation of Pb sulfate deposit caused lower concentration of Pb(II) ion in leaching solution applying sulfuric acid leaching.

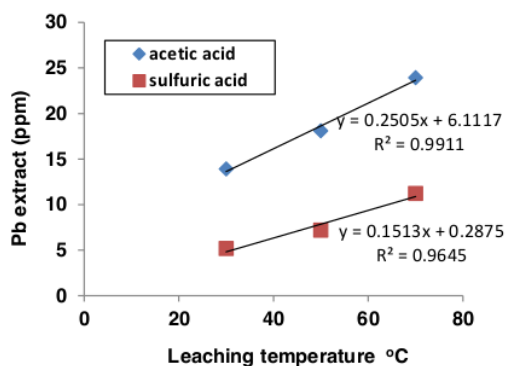


Fig. 5. Pb extraction from galena using acetic and sulfuric acids. Acid concentration 1.0 M, 200 rpm. H₂O₂ oxidant. AAS assay.

As shown by Fig. 4 and Fig. 5, the trend of Pb leaching from galena concentrate at given varied acid concentrations (1.0 M, 1.5 M, and 2.0 M) and given leaching temperature (30°C, 50°C, and 70°C) show almost linearly. The range of linearity (Fig. 4 and Fig. 5) in the range of R² of 0.96–0.99, which is moderately linear both for given acid concentration and temperature effects on Pb extraction. The upper limit of acid concentration was made to be 2.0 M on the reason of chemical safety, while the temperature was limited to 70°C due to energy reason. There is a consistence between concentrations of Pb extract and both effects of acid concentration and temperature applying either acetic acid or sulfuric acid as leaching agent.

3.4 Effect of stirring speed on Pb leaching

This article has also investigated the effect of stirring speed (200 rpm, 400 rpm, and 600 rpm) on Pb leaching applying acetic and sulfuric leaching acids, as shown by Fig. 6. Furthermore, Fig. 6 shows that effect of given varied stirring speed on Pb leaching from galena is not too significant particularly using sulfuric acid as leaching agent. As shown by other effects earlier (acid concentration and leaching temperature), the effect of stirring speed on Pb leaching from galena concentrate shows that acetic acid leaching extracted more Pb(II) ion from galena rather than leaching by sulfuric acid. This phenomenon is due to the formation of Pb sulfate precipitate. According to the rule of solubility, the solubility product (K_{sp}) of Pb sulfate is much smaller than that one of Pb acetate at given range of temperature. The linearity of stirring speed effect particularly for sulfuric acid leaching shows no significant effect on Pb extraction with varied

given stirring speed (200, 400, and 600 rpm).

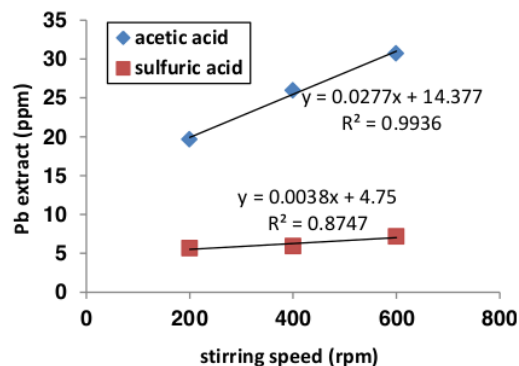


Fig. 6. Pb extraction from galena using acetic and sulfuric acids. Acid concentration 1.0 M, 50°C. H₂O₂ oxidant. AAS assay.

3.5 XRF examination of galena ore

As mentioned earlier, galena mineral is commonly found with other minerals such as sphalerite, marcasite, pyrite, chalcocopyrite[1,7]. Sphalerite is a sulfide mineral with chemical formula as (Zn, Fe) S that is commonly called as zinc blende. Table 2 shows that the result of XRF examination reported Fe (32.8%) and Zn (26.6%) together with Pb (13.9%) as transition elements in galena ores. Marcasite and pyrite, both are sulfide minerals with same chemical formula, i.e., FeS₂, however, they have different crystal structure. Marcasite has orthorhombic structure, while pyrite has cubic crystal structure. In addition, marcasite is less dense and lighter than pyrite, therefore, marcasite is more brittle. Chalcocopyrite is a copper iron sulfide mineral (Cu₅FeS₄).

Several studies reported the flotation separation of galena from pyrite using serpentine depressant[11], isolation of galena from chalcocopyrite using HEC depressant[12], and separation of galena from sphalerite using nitrogen functional groups[7]. Table 2 reported copper as 3.29% and sulfur as 4.8% related to the existence of chalcocopyrite in galena ore. Thus, there are the important minerals in galena ores based on their concentrations. Furthermore, it is apparently that transition elements look dominant in galena ores (Table 2). It should be noted that rare earth metals (lanthanum, europium, and ytterbium) are also detected in galena ore (Table 2). Fig. 6 shows the XRF spectra of galena ore before roasting treatment.



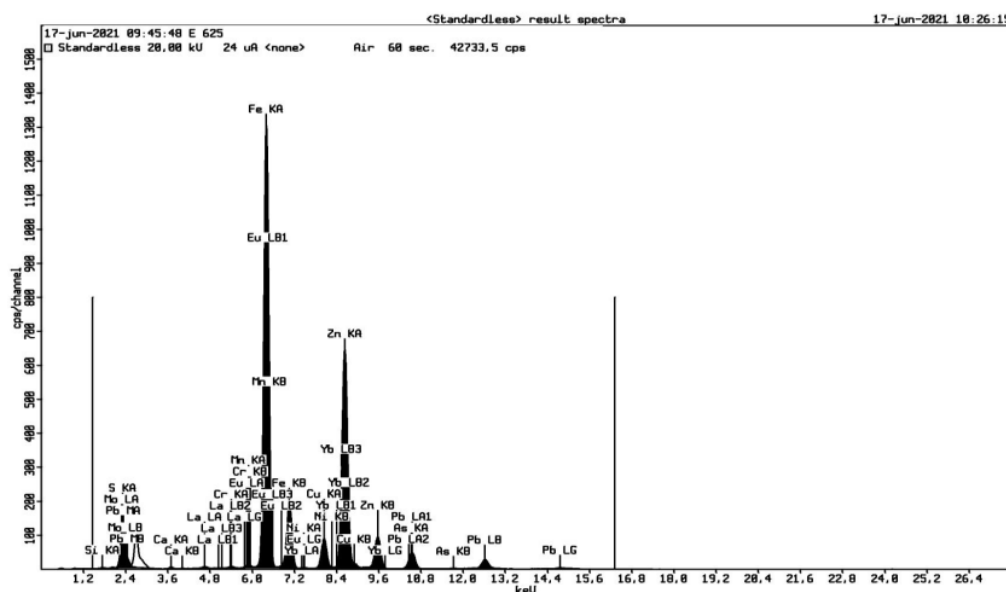


Fig. 6. XRF spectra of galena ore before roasting

Table 2. XRF examination of galena ores from West Java Province, Indonesia.

Chemical element	Content (%)
Si	1.0
S	4.8
Ca	0.28
Cr	0.095
Mn	0.13
Fe	32.8
Pb	13.9
Ni	0.05
Cu	3.29
Zn	26.6
As	0.78
Mo	16.0
La	0.03
Eu	0.3
Yb	0.1

4. Conclusions

Previous study reported Pb leaching from galena concentrate using expensive and toxic leaching agents. However, this study attempts to apply low-cost acids (acetic and sulfuric acids) as leaching agent for Pb extraction from galena concentrate. Further study needs modification on leaching parameters addressing to particle size, selection of oxidant, and leaching time to get results improvement.

5. Acknowledgements

The authors would like to thank all staff of

chemical laboratories to give support to this research project. A thankful acknowledgement is also addressed to the Head Department of Mining, Universitas Trisakti for contribution on facilities needed by this research. Acknowledgement is sent to PT. Galena Maju Karya Mandiri for preparing sample of galena concentrate and XRF facilitation.

References

- [1] Suryana, Anistasia, M. & Amreza, E. Pengaruh penambahan oksidator pada proses pelindian oksidatif konsentrat galena (Effect of oxidator addition on oxidative leaching process of galena concentrate), Department of Metallurgy Engineering, Universitas Sultan Tirtayasa, Banten, 2019.
- [2] Wang, C. Deng, J. Tao, L. Sun, W. Xiao, Q. & Gao, Z. Enhanced flotation of chalcopyrite particles by grinding with cylinder media. *Minerals Engineering*, 2022; 188: 107827.
- [3] Liu, Q. Li, H. Jin, G. Zheng, K. & Wang, L. Assessing the influence of humic acids on the weathering of galena and its environmental implications. *Ecotoxicology & Environmental Safety*, 2018; 158: 230 – 238.
- [4] Anugrah, R.I. Amalia, D. & Mubarok, M.Z. Parameters that affect the dissolution of Indonesian galena concentrate in fluorosilicic acid and hydrogen peroxide. *Indonesian Mining Journal*, 2018; 21: 89 – 97.



- [5] Amalia, D. Ramanda, Y. & Maryono. Extraction of lead from galena concentrates using fluosilicic acid and peroxide. *Indonesian Mining Journal*, 2017; 20: 69 – 80.
- [6] Golpayegani, M.H. & Abdollahadeh, H.H. Optimization of operating parameters and kinetics for chloride leaching of lead from melting furnace slag. *Transactions of Nonferrous Metals Society of China*, 2017; 27: 2704 – 2714.
- [7] Wang, J. Ji, Y. Cheng, S. Li, S. Cao, J. & Chen, P. Selective flotation separation of galena from sphalerite via chelation collectors with different nitrogen functional groups. *Applied Surface Science*, 2021; 568: 150956.
- [8] Mubarak, Z. Studi perilaku pelindian timbal dari bijih galena Nanggung, Kabupaten Bogor, dalam larutan asam asetat dan oksidator hydrogen peroksida (The study of lead leaching profile from galena ores in Nanggung, Bogor Residence, in acetic acid solution and hydrogen peroxide oxidator), Department of Metallurgy Engineering, Faculty of Mining and Petroleum Engineering, Institut Teknologi Bandung, 2014.
- [9] Nnanwube, I.A. & Onukwuli, O.D. Hydrometallurgical processing of a Nigerian galena ore in nitric acid: Characterization and dissolution kinetics. *Journal of Minerals and Materials Characterization and Engineering*, 2018; 6: 271 – 293.
- [10] Tarumingkeng, S. Termodinamika dalam memahami proses pengolahan mineral (The thermodynamics of understanding mineral treatment processing), Department of Physics, Faculty of Math and Science, Institut Teknologi Bandung, 2016.
- [11] Feng, B. Zhang, W. Guo, Y. Wang, T. Luo, G. Wang, H. & He, G. The flotation separation of galena and pyrite using serpentine as depressant. *Powder Technology*, 2019; 342: 486 – 490.
- [12] Feng, B. Jiao, X. Wang, H. Peng, J. & Yang, G. Improving the separation of chalcopyrite and galena by surface oxidation using hydroxyethyl cellulose as depressant. *Minerals Engineering*, 2021; 160: 106657.
- [13] Agatzini, L. Oustadakis, P. Tsakiridis, P. & Markopoulos, Ch. Titanium leaching from red mud by diluted sulfuric acid at atmospheric pressure. *Journal of Hazardous Materials*, 2008; 157: 579 – 586.
- [14] Barakat, M.A. Recovery of lead, tin and indium from alloy wire scrap. *Hydrometallurgy*, 1998; 49: 63 – 73.
- [15] Nurul, A.J. Suhaina, I. & Alif, N.A. Recovery of tin from copper dross by acid leaching. *IOP Conf. Series: Materials Science & Engineering*. 2019; 701(1): 012019.



COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA

ORIGINALITY REPORT

8%

SIMILARITY INDEX

6%

INTERNET SOURCES

7%

PUBLICATIONS

6%

STUDENT PAPERS

PRIMARY SOURCES

1	Submitted to Universitas Mercu Buana Student Paper	2%
2	Submitted to Universitas Bangka Belitung Student Paper	2%
3	doaj.org Internet Source	1%
4	Nenden Juliasih, Sri Nurhayati, Nandang Rukanda. "The Efforts of the Family Welfare Empowerment Driving Team in Increasing Entrepreneurial Motivation for Family Welfare Empowerment Cadres during the COVID-19 Pandemic", Society, 2022 Publication	1%
5	Submitted to Rutgers University, New Brunswick Student Paper	1%
6	I. Marwanza, M. A. Azizi, C. Nas, A. Anugrahadi, W. Dahani, S. Subandrio, D. K.	<1%

Salim, A. Prima. "The determination of information point distribution and classification of confidence level estimation of geotechnic solid rock kriging estimation parameter based on variogram analysis", AIP Publishing, 2020

Publication

7

Ikechukwu A. Nnanwube, Okechukwu D. Onukwuli. "Characterization and Kinetics of Alumina Leaching from Calcined Akpugo Kaolinite for Potential Aluminum Recovery", South African Journal of Chemical Engineering, 2022

Publication

<1 %

Exclude quotes Off

Exclude matches < 15 words

Exclude bibliography On

COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA

GRADEMARK REPORT

FINAL GRADE

/0

GENERAL COMMENTS

Instructor

PAGE 1

PAGE 2

PAGE 3

PAGE 4

PAGE 5

PAGE 6

PAGE 7

EDITORIAL TEAM

EDITOR IN CHIEF

1. Prof. (em.) Dr.-Ing. Ir. Darwin Sebayang, Universitas Mercu Buana, Indonesia

MANAGING EDITORS (MAIN HANDLING EDITORS)

1. Dafit Feriyanto, Ph.D, Universitas Mercu Buana, Indonesia
2. Dr. Sagir Alva, Universitas Mercu Buana, Indonesia
3. Andi Firdaus Sudarma, M.Sc, Universitas Mercu Buana, Indonesia
4. Dr. Ignatius Agung Wibowo, Universitas Mercu Buana, Indonesia

EDITORIAL BOARD

1. Assoc. Prof. Dr. Muhaimin Ismoen, Institut Teknologi Brunei, Brunei Darussalam
2. Jonny Herwan, Ph.D, National Institute of Advanced Industrial Science & Technology (AIST), Japan
3. Dr. Ali Rinaldi Bin Anand, King Fahd University of Petroleum and Minerals (KFUPM), Saudi Arabia
4. Eldwin Djajadiwinata, Ph.D, King Abdullah City for Atomic and Renewable Energy (K.A.CARE), Energy Research and Innovation Center at Riyadh, Saudi Arabia
5. Assoc. Prof. Dr. Ajay Dattu Jagadale, Sastra Deemed University, India
6. Samir Sani Abdulmalik, Ph.D, Nigerian Army University, Nigeria
7. Dr. Eng. Surachai Karnjanakom, Rangsit University, Thailand
8. Prof. Dr. Erry Yulian Triblas Adesta, Islamic International University Malaysia, Malaysia
9. Prof. Dr.-Ing. Yupiter HP Manurung, Universiti Teknologi MARA, Malaysia
10. Assoc. Prof. Dr. Anika Zafiah binti Mohd Rus, Universiti Tun Hussein Onn Malaysia, Malaysia
11. Assoc. Prof. Dr. Jumril Yunas, Universiti Kebangsaan Malaysia, Malaysia
12. Assoc. Prof. Dr. Edy Herianto Majlan, Universiti Kebangsaan Malaysia, Malaysia
13. Assoc. Prof. Dr. Abdul Mutalib bin Leman, Universiti Tun Hussein Onn Malaysia, Malaysia
14. Prof. Dr.-Ing. Ir . Nasruddin, M.Eng, Universitas Indonesia, Indonesia
15. Prof. Dr. Dahyunir Dahlan, Universitas Andalas, Indonesia
16. Prof. Ir. Meilana Dharma Putra, Ph.D, Universitas Lambung Mangkurat, Indonesia
17. Alfian Noviyanto, Ph.D, Nano Center Indonesia, Indonesia
18. Dr.-Ing. Pudji Untoro, Universitas Surya, Indonesia
19. Dr. Arbi Dimiyati, National Nuclear Energy Agency of Indonesia (BATAN), Indonesia
20. Ir. Feri Adriyanto, Ph.D, Universitas Sebelas Maret, Indonesia
21. Rd. Rohmat Saedudin, Ph.D., Telkom University, Indonesia

REVIEWERS

1. DR. Abdul Hamid, Universiti Tun Hussein Onn Malaysia, Malaysia
2. Jouvan Chandra Pratama Putra, University of Agder, Norway
3. Fajar Anggara, Universitas Mercu Buana, Indonesia
4. Dr. Eng. Afdhal Kurniawan Mainil, ST., MT., Universitas Bengkulu, Indonesia
5. Mr Alief Avicenna Luthfie, Program Studi Teknik Mesin, Fakultas Teknik, Universitas Mercu Buana. Jl. Meruya Selatan No. 01, Jakarta Barat 11650, Indonesia
6. Dianta Ginting, Ph.D, Kyung Hee University, Korea, Republic of
7. Ir . Sulisty, Ph.D, Universitas Diponegoro, Indonesia
8. Teddy Sjafrizal, B.Eng(Hons.), M.Sc., Ph.D, Telkom university, Indonesia
9. Dr. Tika Hafzara Siregar, Universitas Ibn Khaldun Bogor, Indonesia
10. Mr Dony Hidayat, BRIN, Indonesia
11. Diswandi Nurba, Universitas Syiah Kuala, Indonesia
12. Rino Andias Anugraha, Telkom University, Indonesia
13. Kusnanto Mukti Wibowo, M.Eng., Universitas Muhammadiyah Purwokerto, Indonesia
14. Sopyan Ali Rohman, M.Eng, Universitas Teknologi Sumbawa, Indonesia

VOL 4, NO 2 (2022)

DOI: <http://dx.doi.org/10.22441/ijimeam.v4i2>

The articles in this issue were authored/co-authored by Authors from Indonesia

TABLE OF CONTENTS

EDITORIALS

Message from Editor in Chief

[PDF](#)

ARTICLES

[THE EFFECT OF ADDITION GREEN INHIBITOR D-GALACTOSE ON CORROSION RATE OF ALUMINUM ALLOY 5052 IN SULFURIC ACID \(H₂SO₄\) MEDIA](#)

[10.22441/ijimeam.v4i2.16610](http://dx.doi.org/10.22441/ijimeam.v4i2.16610)

Muhajirin Muhajirin, I. G. A. Arwati, S. Hartati, H. Hakim, Alfian Noviyanto, Arramel Arramel, T. Zakly

[PDF](#)
30-37

[MECHANICAL STUDY OF 9CR-316SS-1MO FOR NUCLEAR POWER REACTOR FUEL CLADDING MATERIALS](#)

[10.22441/ijimeam.v4i2.16832](http://dx.doi.org/10.22441/ijimeam.v4i2.16832)

Mayda Purnama, Usman Sudjadi

[PDF](#)
38-45

[MORPHOLOGICAL AND PROPERTIES OF PORTLAND-COMPOSITE CEMENTS WITH CLASS C FLY ASH](#)

[10.22441/ijimeam.v4i2.17036](http://dx.doi.org/10.22441/ijimeam.v4i2.17036)

Andrie Harmaji, A. Fadillah

[PDF](#)
46-50

[COMPARATIVE STUDY USING LOW COST ACETIC AND SULFURIC ACIDS ON ROASTING AND PEROXIDE FOR LEACHING PROCESS TO EXTRACT PB FROM GALENA](#)

[10.22441/ijimeam.v4i2.17135](http://dx.doi.org/10.22441/ijimeam.v4i2.17135)

Wiwik Dahani, Rita Sundari, Subandrio Somali, Irfan Marwanza, Ivetta Ivetta

[PDF](#)
51-57

[ANALYSIS OF OIL ABSORPTION AND FRICTION COEFFICIENT OF BAMBOO POWDER, COCONUT POWDER, GLASS POWDER, AND COPPER POWDER COMPOSITES FOR CLUTCH PADS](#)

[10.22441/ijimeam.v4i2.18235](http://dx.doi.org/10.22441/ijimeam.v4i2.18235)

Iqbal Risyuma, Muhamad Fitri