

The Effects of Austenitizing Process to Mechanical Properties of Thin Wall Ductile Iron Connecting Rod

by Rianti D. Sulamet-ariobimo

Submission date: 30-Mar-2021 07:46PM (UTC+0700)

Submission ID: 1546324863

File name: 2020_i-SENAMM_5.0016141.pdf (1.7M)

Word count: 3310

Character count: 17034

The effects of austenitizing process to mechanical properties of thin wall ductile iron connecting rod

Cite as: AIP Conference Proceedings 2262, 060006 (2020); <https://doi.org/10.1063/5.0016141>

Published Online: 17 September 2020

R. D. Sulamet-Ariobimo, J. R. Santoso, M. Fadhlán, T. Yasin, T. Sukarnoto, Y. Mujalis, and Y. Oktaviano



View Online



Export Citation

ARTICLES YOU MAY BE INTERESTED IN

[Effect of variation concentration and soaking time on API 5L steel grade B in 3.5% NaCl media using avocado seed extract inhibitors](#)

AIP Conference Proceedings 2262, 050011 (2020); <https://doi.org/10.1063/5.0016525>

[Deposition and post heat treatment of Ni-Al/Ni-20Cr on AISI 4140 using twin wire arc spray method](#)

AIP Conference Proceedings 2262, 060008 (2020); <https://doi.org/10.1063/5.0015688>

[Analysis of flux type variations in the sintering process of limonitic laterite nickel ore](#)

AIP Conference Proceedings 2262, 070002 (2020); <https://doi.org/10.1063/5.0016067>



New

Your Qubits. Measured.

Meet the next generation of quantum analyzers

- Readout for up to 64 qubits
- Operation at up to 8.5 GHz, mixer-calibration-free
- Signal optimization with minimal latency

[Find out more](#)



The Effects of Austenitizing Process to Mechanical Properties of Thin Wall Ductile Iron Connecting Rod

R. D. Sulamet-Ariobimo^{1,a)}, J. R. Santoso¹, M. Fadhlan¹, T. Yasin¹, T. Sukarnoto¹,
Y. Mujalis¹ and Y. Oktaviano¹

¹*Mechanical Engineering Department, Faculty of Industrial Technology, Universitas Trisakti, Jakarta, Indonesia*

^{a)}riantariobimo@trisakti.ac.id

Abstract. Aluminium casting is lighter than cast iron, but cast iron has much more benefit. Especially when thin wall casting technology and austempering process applied in cast iron. Based on this, the shifting from cast iron to aluminium need further consideration. Thin wall casting technology will help cast iron in weight problem, while austempering process will improve the properties. Austempering process was carried out on thin wall ductile iron (TWDI) connecting rod component. The aim of this work is to analyse the effect of austenitizing time to mechanical properties of thin wall austempered ductile iron connecting rod. The process was applied to all connecting rods resulting from the vertical casting which is made in foundry scale. The austenitizing temperature was 9600C with various holding time of 15, 30, 45 and 60 minutes and the austempering temperature was 3500C with 35 minutes isothermal time. The process was held in fluidized bed furnace. Metallographic examination, tensile and compression stress-strain test were conducted directly to the connecting rod. The results showed that austenitizing time hold an important role in producing TWADI since austenitizing time responsible in producing the ausferrite.

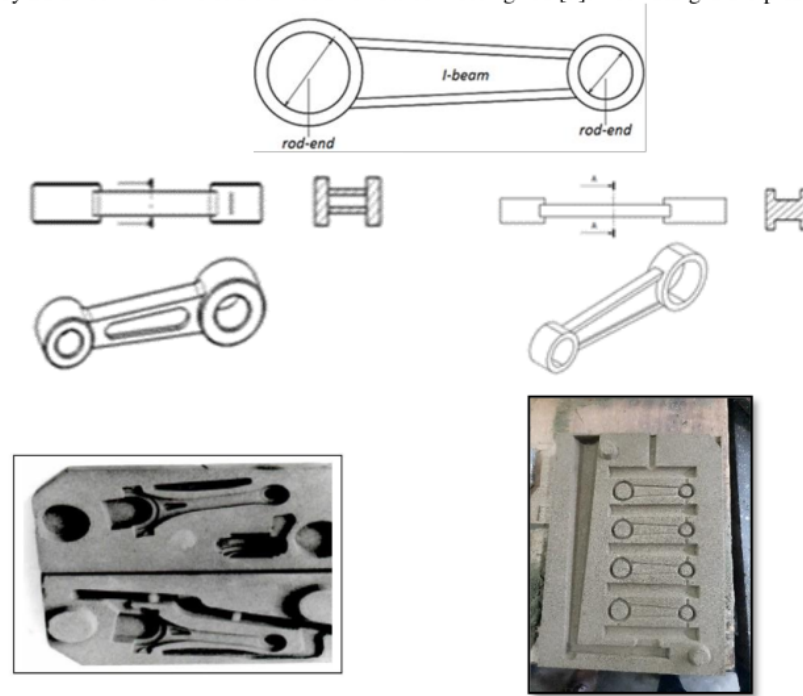
Keywords: TWADI, connecting rod, vertical casting, austenitizing time.

INTRODUCTION

Further considerations should be taken before replacing cast iron with aluminium casting. Aluminium casting indeed lighter than cast iron and has lower melting temperature with high thermal conductivity. But when it comes to mechanical property, energy consumption and production cost, cast iron is still superior to aluminium [1]. Especially when thin wall casting technology is applied during the manufacturing process. Thin wall casting technology will reduce the weight of the cast iron. When thin wall casting technique was applied to connecting rod, the design presented by Martinez et al. could reduce its weight to 33% [2], while the design used by Sulamet-Ariobimo et al. could reach the number of 27% [3]. The superiority of cast iron is more increasing when austempering process applied to Thin Wall Ductile Iron (TWDI). Austempering process on ductile iron was able to improve its properties to be similar or even higher than forged steel [2,4] and known as Thin Wall Austempered Ductile Iron (TWADI).

Studies regarding the application of austempering process in TWDI to produce TWADI were conducted. But most of these studies used plate as the casting product. Its application to automotive components was started by Martinez

et al. by producing TWADI hollow connecting rod for Vespa PX150 [2]. This worked was then followed by Franš et al. which produced TWADI and TWADI of cantilevers and control arm [1]. Sulamet-Ariobimo et al. followed the work of Martinez et al. and Franš et al. in producing TWADI components. Based on the work of Martinez et al., Sulamet-Ariobimo et al. produced thin wall austempered connecting rod for Vespa PX150. The TWADI connecting rod developed by Sulamet-Ariobimo et al. is not a hollow connecting rod [3]. Both designs are presented in Fig. 1.



a. Design of Martinez et al. [2]

b. Design of Sulamet-Ariobimo et al. [3]

Figure 1. TWADI Connecting Rod

In general, austempering parameter consist of austenitizing temperature, austenitizing time, austempering temperature and austempering time. Mourad et al. studied the effect of austempering temperatures. They used plate sample 200 mm x 100 mm with the various thickness of 2, 4, 6, and 8 mm. The austenitizing temperature was 900°C for 30 minutes and austempering temperature of 350°C and 400°C with isothermal time of 10 minutes for 2- and 4-mm thicknesses and 30 minutes for 6- and 8-mm thicknesses. The result showed that optimal result was obtained by austempering temperature of 350°C [5]. While Franš et al. studied TWADI plate of 20 mm x 28 mm with the thickness of 2 mm. The austenitizing temperature was 880°C for 20 minutes time and austempering temperature of 400°C with various holding time of 5, 15, 30 and 90 minutes. The result showed that it is possible to produce austempered ductile iron castings of with a wall thickness of 2.0 mm and high mechanical properties using only 50 minutes as a total heat treatment time. Other finding from this studied was based on the dimension of plate and other research parameters, isothermal time for austempering process can be limited to 5 to 10 minutes [6]. Soedarsono et al applied austenitizing temperature of 960°C for 30 minutes and austempering temperature of 350°C for 10 minutes in their studied to make thin wall austempered ductile iron (TWADI) plate of 150 mm x 75 mm x 1 mm which increased the UTS between 44 to 309% and elongation between 50 to 100% [4]. Savićević et al. studied the effect of austempering temperature from 250 to 420°C. They started at 260°C with an increase every 20 degree. The austenitizing temperature was 850°C for 45 minutes and the austempering time of 60 minutes. They found out that tensile strength decreases as the increasing of austempering temperature [7].

Austempering process for TWADI component is more complicated compare to TWADI plate, since components has more shape and dimension to consider than plates. Franš et al. applied the result of their previous studied to make

cantilevers and control arms from TWADI [1]. While Sulamet-Ariobimo et al. applied the result of their studied to make connecting rod [8].

All the studied in ADI and TWADI focused on austempering process and austenitizing temperature. While, it is hard to find study about the effect of austenitizing time. Whereas, austenitizing time affects the homogeneity of the forming microstructure. The objective of this study is to analyze the effect of austenitizing time to mechanical properties of thin wall austempered ductile iron connecting rod.

MATERIALS AND METHODS

Modification was applied to connecting rod of Vespa PX150 by reducing the thickness of I-beam from 4 mm in the original part, Fig. 1, to 3 mm as shown in Fig. 2. This reduction will reduce the weight of the component to 25% [3].

The modified connecting rods, which produced in industrial foundry, were all austenitized at 9600C for varied duration, which is 15, 30, 45 and 60 minutes, and then quenched in fluidized bed furnace which was held at 3500C for 35 minutes. After that they were cooled in the air. Fluidized bed furnace was chosen as isothermal quench media replacing salt bath since it is more environmentally friendly.

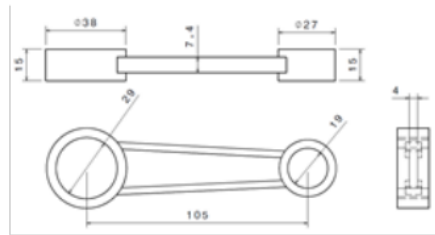


Figure 2. Original Dimension of Connecting Rod [3]

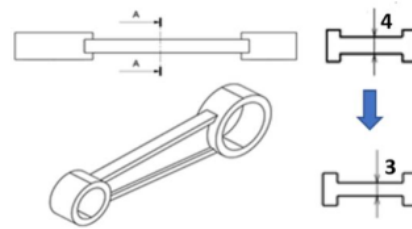


Figure 3. Thickness reduction in I-beam area [3,8].


Table 1. Chemical Composition of TWADI

Element	ASTM Standard (% weight)	Foundry Standard (% weight)	Testing Result (% weight)	
			Pouring – 1	Pouring – 2
Carbon (C)	3.60 – 3.80	3.50 – 3.90	3.67	3.63
Silicon (Si)	1.80 – 2.80	2.40 – 2.80	2.78	2.49
Manganese (Mn)	0.15 – 1.00	0.30 – 0.50	0.35	0.43
Magnesium (Mg)	0.03 – 0.06	0.03 min.	0.04	0.04
Phosphor (P)	< 0,30		0.01	0.01
Sulfur (S)	< 0,02	0.015 max.	0.01	0.02
Copper (Cu)	0.015 – 1.00	0.15 max.	0.22	0.22
Chromium (Cr)	0.03 – 0.07		0.06	0.04
Nickel (Ni)	0.05 – 2.00	0.02 min.	0.04	0.01
Molybdenum (Mo)	0.01 – 0.10		0.01	0.01
CE – 1	5 %C + 0,31%Si		4,53	4,40
CE – 2	%C + 0,31%Si +0,55%P-0,027%Mn+0,4%S		4,53	4,40
CE – Test			4,59	4,47

All the modified rods were produced from vertical casting design [9]. Each mold of the casting design produced 4 connecting rods and 4 molds were produced in one pouring. This study used 2 pouring. Two molds of the first pouring were directly characterized and the other two molds together with the second pouring were austempered. Since all process happened in industrial foundry, all the liquid metal used in this research is industrial liquid metals produced

by the foundry for their commercial products. The chemical compositions were presented in Table 1. The codes for all connecting rods and their process were presented in Table 2.

Table 2. Samples Coding

	Pouring 1 – TWADI (CE = 4,59)		Pouring 2 – TWADI (CE = 4,47)	
	Code	Condition	Code	Condition
	0'	TWADI	15'	TWADI – Austenitizing Holding Time 15 minutes (Tensile Specimen)
	45'	TWADI – Austenitizing Holding Time 45 minutes	30'	TWADI – Austenitizing Holding Time 30 minutes (Tensile Specimen)
	60'	TWADI – Austenitizing Holding Time 60 minutes	45'	TWADI – Austenitizing Holding Time 45 minutes (Compression Specimen)
			60'	TWADI – Austenitizing Holding Time 60 minutes (Compression Specimen)

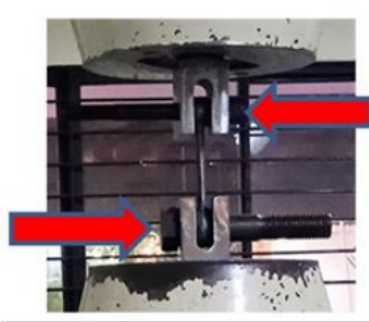


Figure 4. Special holder for tensile and compression test [3]

After austempering process, all the connecting rods were subjected to mechanical testing which cover tensile and compression test. The test was run directly to the connecting rod. Special holder, as presented in Figure 4, was used during the test to hold the connecting rod. Universal Testing Machine (UTM) Shimadzu EHP-EB20186838 was used for tension testing. The maximum load was 20 ton and testing speed was 0.05 mm/mm/minute with level of confidence 95%. Gotech AI – 7000 LA10 Servo Control Computer System Universal Tensile Machine with the maximum capacity of 1000 kg was used for compression test. Calculation for compression strength was based on the area of the I-beam since modification was applied only to that area as shown by Figure 3. Tensile strengths were not calculated because the break point happened in rod area as presented by Figure 5. The I-beam area calculation for compression were presented in Table 3.

Samples for metallography examination were taken from the cross section of the connecting rods which have been tested in tensile and compression. The metallography samples were taken from I-beam and end rod area as presented in Figure 7.

Table 3. Area of I-beam

Rod Position	I-beam Area – in mm ²							
	Pouring 1				Pouring 2			
	A	B	C	D	A	B	C	D
1							84.92	93.05
2							74.40	71.27
3			76.00	98.27			79.00	79.13
4			76.01	85.52			98.30	90.68



Figure 5. Break point during tensile test.



Figure 6. Result of Compression Test





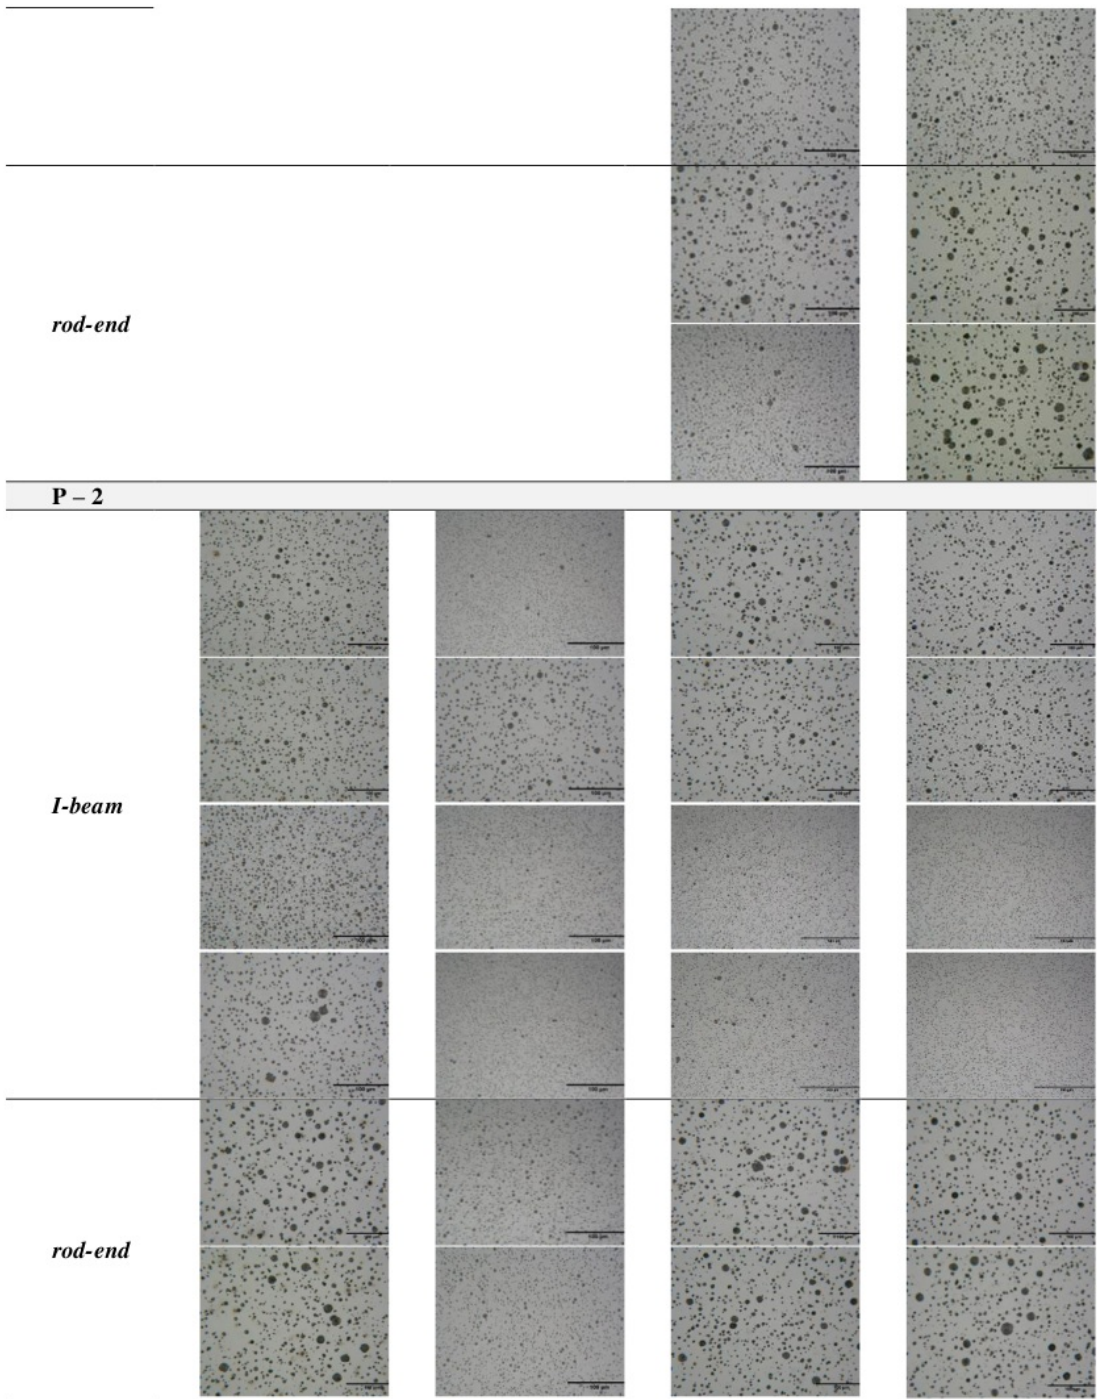
Figure 7. Metallography samples

RESULTS AND DISCUSSION

The result of used liquid metal chemical composition showed that all elements are beyond the limit of ASTM standard for both pouring except for nickel. Nickel content in the first pouring is 20% below the minimum level and 80% for second one. The aim of nickel addition in ductile iron is to increase hardenability of austempered ductile iron. In austempering temperature below 350°C, nickel will slightly reduce tensile strength but increases ductility and fracture toughness. The austempering temperature used in this work was 350°C. So, the effect of nickel deficiency for tensile strength, ductility and fracture toughness will not be seen. As for hardenability, the effect will be seen clearly in the second pouring.

Carbon equivalent (CE) of both pouring are calculated using two type of equation as shown in Table 1. The result for both calculations showed that no noticeable differences between the result of both equations. When these results compared to experiment, it was found 0.06 and 0.07 % differences for each pouring. The CE values are considered similar since the differences is not significant. CE comparison between the first and second pouring revealed the difference of 0.13% for calculation and 0.12% for experiment. Although the gap is quite broad but both CE are still inside the standard recommended CE of 4.4 to 4.6 [2]. Based on the CE values which are all below 4.67 the matrix of the microstructure will not be 100% ferrite [10,11].

TWADI				
	15'	30'	45'	60'
P- 1				
<i>I-beam</i>				



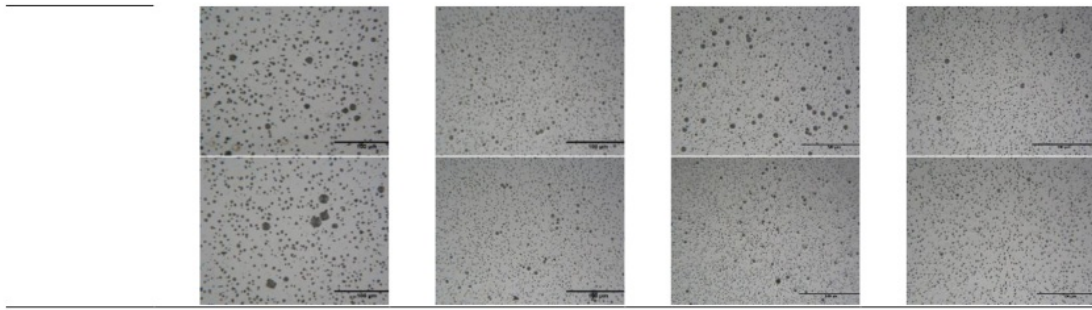


















Figure 8. Un-etched microstructures of TWADI

TWADI	15'	30'	45'	60'
P-1				
<i>I-beam</i>				
				
<i>rod-end</i>				
				
P-2				
<i>I-beam</i>				
				

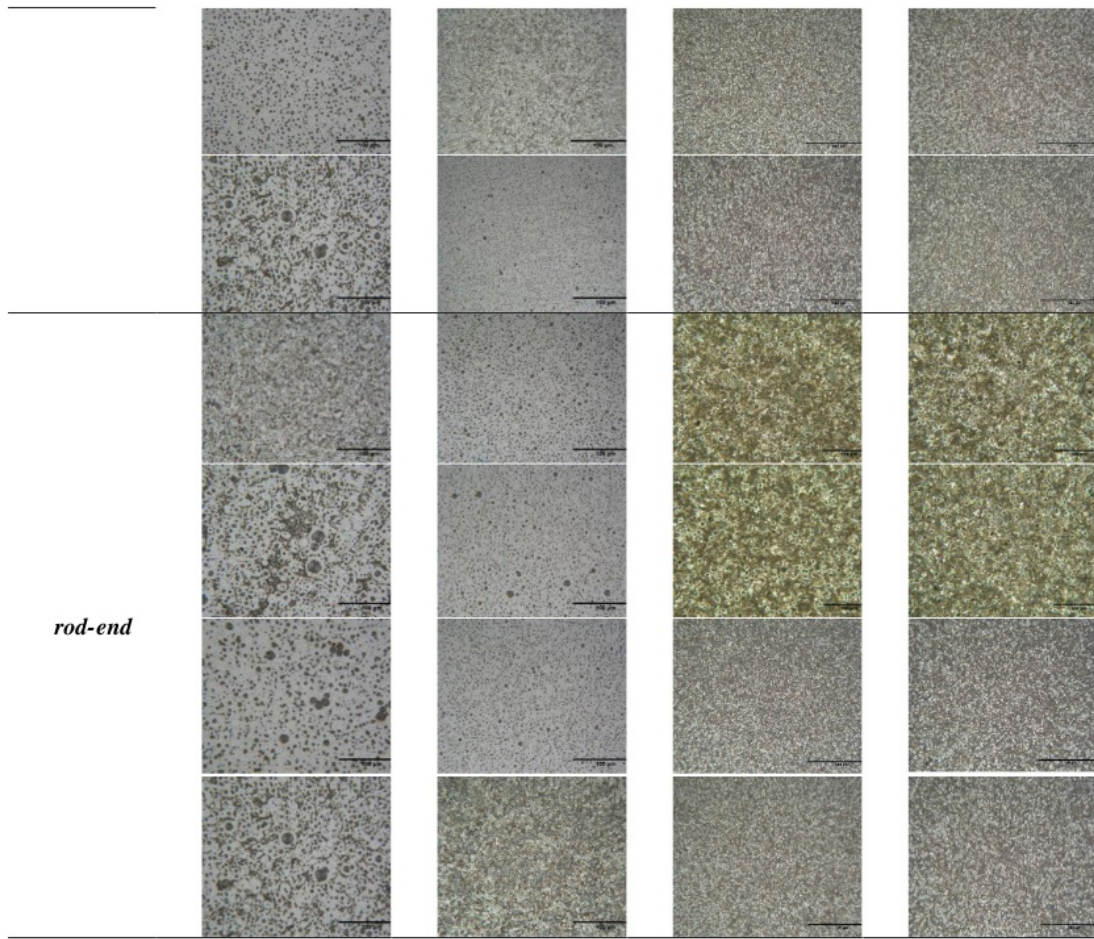


Figure 9. Etched microstructures of TWADI

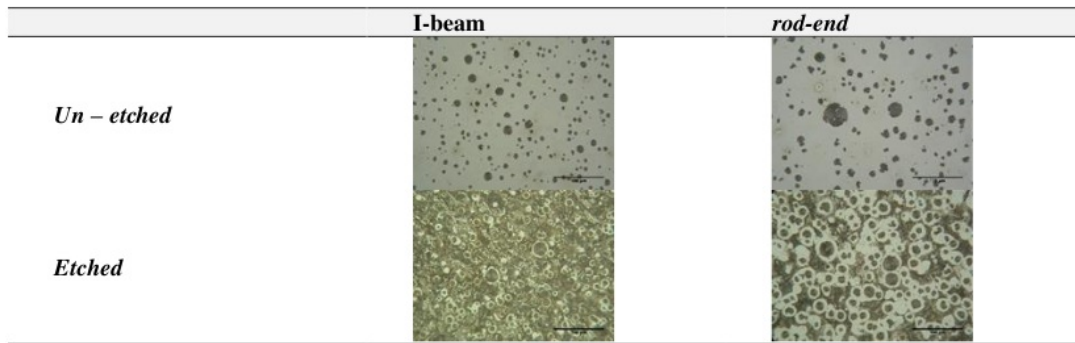


Figure 10. Microstructures of TWADI [8]

Fig. 8 shows the un-etched microstructure of TWADI. Nodules graphite distribute evenly in all condition and primary graphite is formed in both I-beam and rod-end area. The etched microstructure in Fig. 9 shows the matrix of TWADI is changing following the austenitizing time. Austenitizing time of 15 and 30 minutes are associated to full

ferrite and combination of ferrite – pearlite matrix. Whilst, austenitizing time of 45 and 60 minutes are associated to full pearlite. All the matrix revealed in this study shows that the austempering process is either not complete or exceeded. The austenitizing time tends to homogenize the microstructure in I-beam area and rod-end.

Compared to TWADI (Fig. 10), the matrix that are formed in TWADI is look alike with the microstructure of I-beam (etched). This finding supports the previous analysis concerning austempering process. Mourad et al. in their research using 10 minutes austenitizing time for plates thickness of 2 mm and 4 mm. Franš et al. suggested 5 to 10 minutes for 2 mm thickness. While Sulamet-Ariobimo et al. applied 30 minutes for 1 mm thickness. They all can produce ausferrite. In austempering components, Franš et al used 20 minutes for their austenitizing time, while Sulamet-Ariobimo et al. used 35 minutes. Franš et al succeeded in forming ausferrite while Sulamet-Ariobimo et al. managed to homogenized the microstructure in its I-beam and rod-end. They gained 100% pearlite.

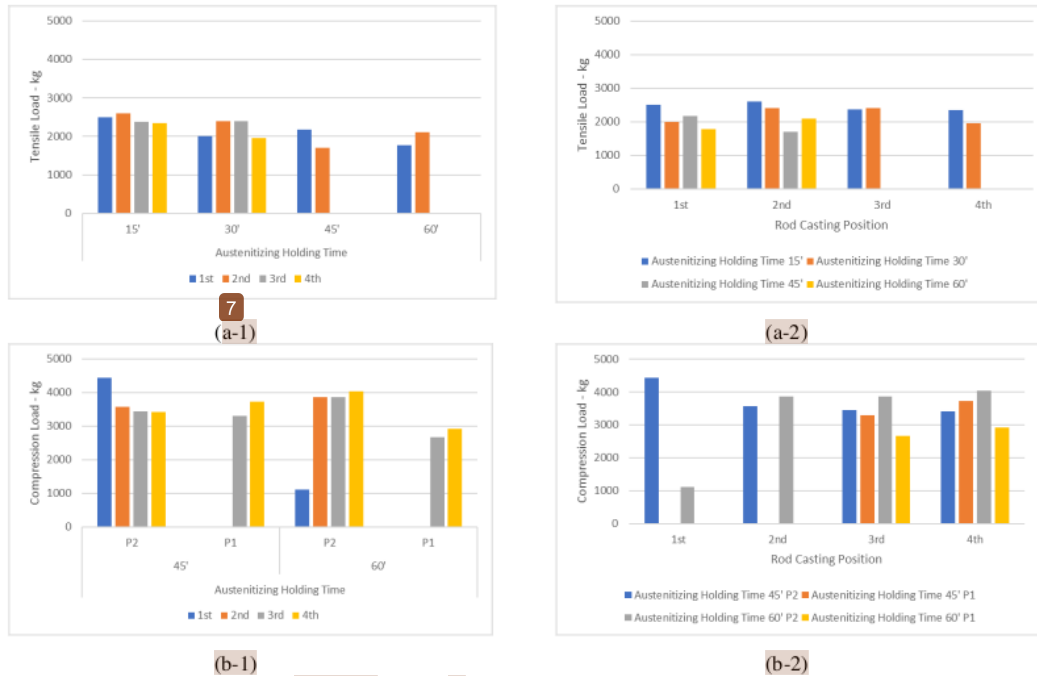


Figure 11. Result of mechanical testing of TWADI

(a-1) Tensile Load in kg to Austenitizing Time & (a-2) Tensile Load in kg to Casting Position
 (b-1) Compression Load in kg to Austenitizing Time & (b-2) Compression Load in kg to Casting Position

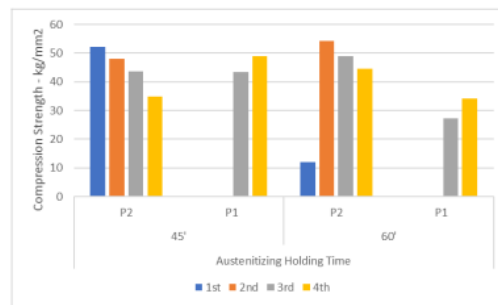


Figure 12. Compression Strength

The result of tensile and compression tests was shown in Fig. 11. Generally, the tensile load range between 1700 to 2600 kg. The difference is 42% to average tensile load. The curve trend tends to decrease as the austenitizing holding time increase. The highest is found in 15 minutes. As for the rod casting position, tensile load tends to fluctuated following the austenitizing holding time, but the highest is still obtained from 15 minutes holding time.

As mention previously, the austenitizing holding time applied for compression test was only 45 and 60 minutes. Special notice should be taken for connecting rod with the first casting position with 60 minutes austenitizing holding time since the data seems to be out layered. It is suspect that there is defect inside the rod and further investigation should be done. By ignoring the out-layer data, the range of the compression loads were 3416 to 4437 kg (29%) for P2, while for P1 were 2675 to 3725 kg (30%)

In contrast with tensile strength, compression strength (Fig. 12) was calculated to determine the ability of TWADI connecting rod to meet the design needs. Compression strength needed by the design for connecting rod is 15 kg/mm². The compression strengths of TWADI connecting rod calculated based on I-beam area are between 27 to 52 kg/mm². Based on the compression strength, the TWADI connecting rod can fulfill the needs of the design.

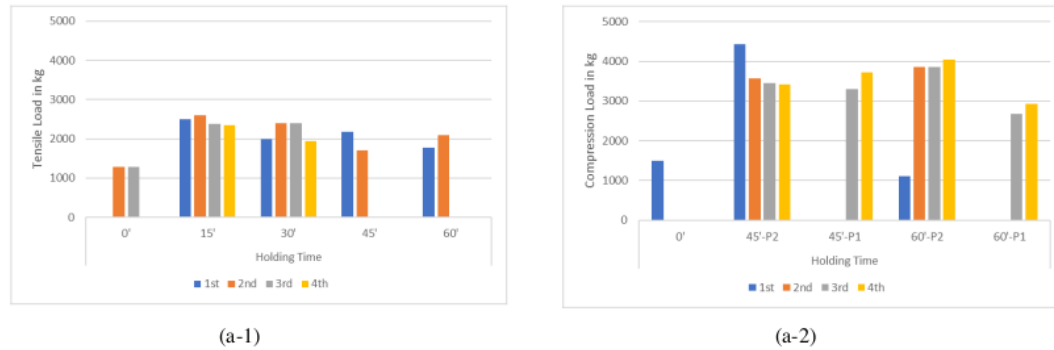


Figure 13. Result of mechanical testing of TWDI & TWADI

(a-1) Tensile Load in kg to Austenitizing Time & (a-2) Compression Load in kg to Austenitizing Time

The result of both tensile and compression load show that the tensile and compression load of TWADI is higher than TWDI (Holding Time = 0'). This result indicates that the austempering process is running and change in microstructure occur.

CONCLUSIONS

The liquid metal used in this work fulfilled the CE requirements for TWDI and TWADI. Nickel deficiency give no effect since the austempering temperature is 350⁰C.

Austempering process is running and has changed the microstructure of TWDI. The differences seen clearly in rod-end. The matrix of rod-end changes from ferrite-pearlite to 100% pearlite. Austenitizing times used in this work have not able to produce ausferrite matrix, but they turned the matrix in rod-end to match the I-beam.

The tensile loads for austenitizing time of 15, 30, 45 and 60 minutes show that the highest load is found in austenitizing time of 15 minutes. While in compression load and strength for austenitizing time of 45 and 60 minutes show the highest load and strength is in 45 minutes. Based on this austenitizing time should be shorten.

Based on the calculation of compression strength using I-beam area, the TWADI connecting rod can be used as substitute to the Vespa New PX 150 which is 15 kg/mm².

ACKNOWLEDGEMENTS

The authors wish to show their attitude to Faculty of Industrial Engineering Universitas Trisakti, PT. Geteka Founindo, PT. ASSAB Indonesia, Department of Metallurgy and Material Faculty of Engineering Universitas Indonesia and Dr. Endang Juwana for their support.

References

1. Fraš E, Górný, M., Lopez H. Thin wall ductile iron castings as substitutes for Aluminium Alloy Castings. *Arch Metall Mater*. 2014; 59(2): 459-65.
2. Martinez RA, Boeri RE, Sikora JA. Application of ADI in high strength thin wall automotive parts. Proc. of 2002 World Conference on ADI. 2002:143-9
3. Sulamet-Ariobimo RD, Yudha G, Sukarnoto T, Mujalis Y, Oktaviano Y. Thin wall austempered ductile iron connecting rod for lighter automotive component – Production of thin wall ductile iron connecting rod. JSAE 20179125/SAE 2017-32-0125. 2017.
4. Soedarsono JW, Soemardi TP, Suharno B, Sulamet-Ariobimo RD, Damanik EZ, Haryono D. Effect of the austempering process on thin wall ductile iron. JMSE. 2011; 1(2):236-42
5. Mourad MM, Ibrahim KM, Ibrahim MM, Nofal AA. Optimizing the properties of thin wall austempered ductile iron. Proc. of 68th World Foundry Congress. 2008:161-166.
6. Fraš E, Górný, M. Thin wall austempered ductile iron. Arch. Foundry Eng. 2009; 9(3):45-48.
7. Savičević S, Avdušinović H, Gigović-Gekić A, Jurković Z, Vukčević M, Janjić M. Influence of austempering temperature on the tensile strength of the austempered ductile iron (ADI) samples. Metabk. 2017; 56(1-2):149-152.
8. Sulamet-Ariobimo, RD, Fadhlan M., Kamili S., Sukarnoto T., Mujalis Y., Oktaviano Y. Effects of austempering process to mechanical properties of thin wall ductile iron connecting rod. IOP Conf, Ser.: Mater.Sci.Eng. 2019; 547:1-8.
9. Sulamet-Ariobimo RD., Gemilang Y., Dhaneswara D., Soedarsono JW, Suharno B. Casting design modification to improve casting yield in producing thin wall ductile iron plate. Adv Mat Res. 2018; 929: 10-17.
10. Soedarsono JW, Suharsono B, Sulamet-Ariobimo RD. Effect of casting design to microstructure and mechanical properties of 3 mm TWDI plate. Adv Mat Res. 2012; 415-417:831-37.
11. Sulamet-Ariobimo RD, Soedarsono JW, Suharno B. Effect of casting design to microstructure and mechanical properties of 4 mm TWDI plate. Adv Mat Res. 2013; 702:269-74.

The Effects of Austenitizing Process to Mechanical Properties of Thin Wall Ductile Iron Connecting Rod

ORIGINALITY REPORT

4%

SIMILARITY INDEX

2%

INTERNET SOURCES

3%

PUBLICATIONS

0%

STUDENT PAPERS

PRIMARY SOURCES

1

doaj.org

Internet Source

1%

2

C Lin. "Influence of microstructure on the fatigue properties of austempered ductile irons—II. Low-cycle fatigue", *International Journal of Fatigue*, 1996

Publication

1%

3

Soedarsono, Johnny Wahyuadi, Vita Astini, Fahmi Fazri, Adji Kawigraha, Rianti Dewi Sulamet-Ariobimo, Andi Rustandi, and Seto Tjahyono. "Effect of Carbon Content in Direct Reduction Process of Limonite Iron Oxide to Produce Pig Iron Substitute for Thin Wall Ductile Iron Process", *Advanced Materials Research*, 2014.

Publication

1%

4

I. Chakrabarty. "2.10 Heat Treatment of Cast Irons", Elsevier BV, 2017

Publication

<1%

5 Doru Michael Stefanescu. "Cellular and dendritic growth", Science and Engineering of Casting Solidification Second Edition, 2009 **<1%**
Publication

6 Zuldesmi Mansjur, Hendro Maxwel Sumual. "Enhancement of Mechanical Properties of Cast Beta-Type Titanium Alloy by Aging Treatment", Materials Science Forum, 2018 **<1%**
Publication

7 arxiv.org **<1%**
Internet Source

8 www.sciencepubco.com **<1%**
Internet Source

Exclude quotes On

Exclude matches < 10 words

Exclude bibliography On