

Jurnal
ASIIMETRIK
JURNAL ILMIAH REKAYASA DAN INOVASI

volume
6
nomor
1
JANUARI
2024

Redaksi Jurnal ASIIMETRIK
Fakultas Teknik Universitas Pancasila
Srengseng Sawah , Jagakarsa, Jakarta Selatan, 12640
021.789 4730 pst. 107
asiimetrik@univpancasila.ac.id



<http://journal.univpancasila.ac.id/index.php/asiimetrik/>



SINTA 3

SK Dirjendiktiristek, Nomor SK: 225/E/KPT/2022

p-ISSN 2655-1861

e-ISSN 2716-2923

Jurnal
ASIIMETRIK
JURNAL ILMIAH REKAYASA DAN INOVASI

volume

6

nomor

1

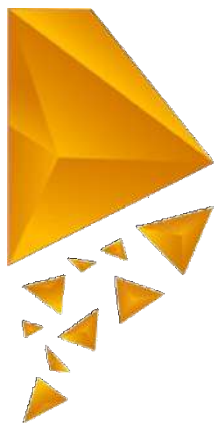
JANUARI

2024



<http://journal.univpancasila.ac.id/index.php/asiimetrik/>





SINTA 3

SK Dirjendiktiristek, Nomor: 225/E/KPT/2022

p-ISSN 2655-1861

e-ISSN 2716-2923

Jurnal
ASIIMETRIK
JURNAL ILMIAH REKAYASA DAN INOVASI

Redaksi Jurnal ASIIMETRIK

Srengseng Sawah, Jagakarsa, Jakarta Selatan, 12640

☎ 021.789 4730 ext. 107

🌐 <http://journal.univpancasila.ac.id/index.php/asiimetrik/>

✉ asiimetrik@univpancasila.ac.id



Volume 6 Nomor 1

JANUARI

2024

Editor-in-Chief:

- Dr. Agri Suwandi. ST., MT., CIAR., IPM.
ID Sinta: 258280 ; ID Scopus: 56267780300

Editorial Board:

- Prof. Ir. Djoko Wahyu Karmiadi, MSME, PhD., APU.
(Universitas Pancasila, Indonesia)
ID Sinta: 600737 ; ID Scopus: 57191582540
- Prof. Dr. Ir. Dwi Rahmalina, MT.
(Universitas Pancasila, Indonesia)
ID Sinta: 5975650 ; ID Scopus: 43261707900
- Dr. Muhammad Yusro, M.T.
(Universitas Negeri Jakarta, Indonesia)
ID Sinta: 5988066 ; ID Scopus: 54974407500
- Dr. Januar Parlaungan Siregar, IPM.
(Universiti Malaysia Pahang Al-Sultan Abdullah, Malaysia)
ID Scopus: 57189757307
- Prof. Ralf Förster
(Berliner Hochschule für Technik (BHT), Germany)
ID Scopus : 8637446600

Section Editor:

- Ir. Duta Widhya Sasmojo, MT.
- Ari Wibowo, S.Kom.

Assistant Editor:

- Catur Ria Kustianti., A.Md
- Risqi Putri Wulandari, S.Hum.



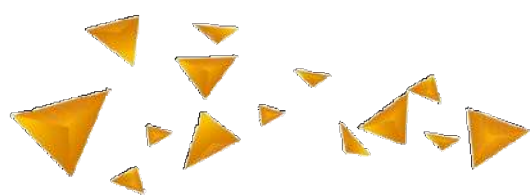
Publisher:

- Fakultas Teknik Universitas Pancasila
UP2M (Unit Penelitian dan Pengabdian kepada Masyarakat)

Editorial Address:

- 📍 Srengseng Sawah, Jagakarsa, Jakarta Selatan, 12640
- 📞 Telp. 021- 786 4730 ext. 107
- ✉️ asiimetrik@univpancasila.ac.id
- 🌐 <http://journal.univpancasila.ac.id/index.php/asiimetrik/>





SINTA 3

SK Dirjendiktiristek, Nomor: 225/E/KPT/2022

p-ISSN 2655-1861

e-ISSN 2716-2923

Jurnal **ASIIMETRIK**
JURNAL ILMIAH REKAYASA DAN INOVASI

REDAKSI



Volume **6** Nomor **1**

JANUARI

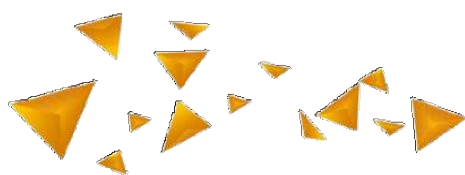
2024

Jurnal Asimetrik: Jurnal Ilmiah Rekayasa dan Inovasi is a national journal published by Faculty of Engineering Universitas Pancasila. It has been accredited "**Rank 3**" or **SINTA 3** by the Decree of the Director General of Higher Education, Research and Technology Number: 225/E/KPT/2022 and is registered with **p-ISSN 2655-1861 (print)** and **e-ISSN 2716-2923 (online)** and can be accessed via the website: <http://journal.univpancasila.ac.id/index.php/asiimetrik/>.

Jurnal Asimetrik: Jurnal Ilmiah Rekayasa dan Inovasi is published regularly every **two times a year**, in **January** and **July**. This journal publishes research-based scientific articles, case studies, review articles, engineering and innovations that cover both theoretical and practical as well as their development. The topics of scientific articles published cover the fields of Architecture, Civil Engineering, Industrial Engineering, Informatics Engineering, Mechanical Engineering and Electrical Engineering.

SUMMARY. **Alfarisi et al**, conducted a finite element analysis on the modification of the design of R22 car wheels made of aluminum to produce the best variant of the existing model. **Suhartono and Muin**, conducted research to determine the effects of seawater on reinforced concrete and the effects on reinforcement on corrosion rate and on concrete on compressive strength when inhibitors have been added. Meanwhile, **Ajiban et al.** analyzed the effect of air pressure and nozzle distance on the quality of water-based paint using a gravity feed spray gun. Research by **Hasan et al.** was conducted to determine the effect of heat flux on the frequency of bubble appearance in boiling pools. Pool boiling is a boiling process in which all fluid motion is caused by natural convection currents. **Abdulah et al.** in their research optimized the heat transfer performance using Response Surface Methodology-Central Composite Design (RSM-CCD) for nano-coolant (AL₂O₃+EG/W) in electric vehicle batteries. **Osman et al.** conducted a study to determine the performance of the machine and whether there was a significant difference from the grinding machining process. Control map analysis was used to determine the consistency of machine performance and comparison of feed rate to determine machine performance. **Syaka et al.** conducted a study to determine the effect of fuel pressure variations on the performance, especially torque and power, of a direct injection 2-stroke gasoline engine. **Nugraha et al.** conducted research on the design of a wind speed measurement system in a pitot tube-based wind tunnel. **Puspa et al**, conducted research on the characteristics of the Thermal Electric Generator (TEG) type SP1848 27145 SA with the aim of knowing the character of voltage output, power and Seebeck coefficient values in the SP1848 27145SA TEG system when temperature changes occur. **Waisal et al**, analyzed the mechanical properties and microstructure of aluminum and copper sheet welding results using the friction stir spot welding method. **Agustina et al**, analyzed the comparison

of rectifier performance in power plant applications. Meanwhile, **Suharyanto and Kurniawan** conducted research related to the effect of heat treatment temperature on the hardness of jaw implants produced by the EDM process. **Lukiano et al**, conducted research on the numerical analysis of the effect of gurney flaps on the aerodynamic performance of NACA 4415 airfoil. Another case with **Billad et al**, who conducted research to prove that the erosion effect can reduce and increase the value of NACA 0015 airfoil. While **Ulhakim et al**, through their research, evaluated the performance of using TiO₂ nanofluids made using ethylene glycol (EG) and distilled water as the base liquid, which was then called TiO₂-EG/W. **Nabil et al**, conducted research on public street lighting monitoring systems using telegram-based wireless sensor network applications. **Rimantho**, developed a waste management model using the Soft System Methodology (SSM) approach to assess the challenges of wood pellet production as a renewable energy source from biomass waste and possible solutions. While **Purwanto et al**, conducted architectural planning with natural lighting systems that can affect occupant productivity and energy efficiency.



SINTA 3

SK Dirjendiktiristek, Nomor: 225/E/KPT/2022

p-ISSN 2655-1861

e-ISSN 2716-2923

Jurnal **ASIMETRIK**

JURNAL ILMIAH REKAYASA DAN INOVASI

DAFTAR ISI



Volume **6** Nomor **1**

JANUARI

2024

Finite Element Analysis of Aluminum Based R22 Car Wheel Design Modification	1-10
<i>Salman Alfarisi, Riyan Ariyansah*, Dan Mugisidi</i>	
Effect of Adding Inhibitors from Dried Tea Leaf Powder and Calcium Nitrate to Concrete and Reinforcement on the Corrosion Rate of Reinforcement and Concrete Compressive Strength	11-18
<i>Suhartono*, Resmi Bestari Muin</i>	
The Effect of Air Pressure and Nozzle Distance on the Quality of Water-Based Painting Using a Gravity-Feed Spray Gun	19-28
<i>Mochammad Hildad Ajiban, Heru Arizal*, Rachmad Syarifudin Hidayatullah, Firman Yasa Utama</i>	
The Effect of Heat Flux on the Frequency of Bubble Appearance in a Boiling Pool	29-38
<i>Muhammad Hasan, Supriyadi, Larasati Rizky Putri, Sofia Debi Puspa, Sentot Novianto*</i>	
Optimization of Heat Transfer Performance Using Response Surface Methodology-Central Composite Design (RSM-CCD) for Nano-Coolant (Al₂O₃+EG/W) in Electric Vehicle Battery	39-48
<i>Amri Abdulah*, Dede Ardi Rajab, Iman Nurshahid, Sukarman, Khoirudin, Muhamad Taufik Ulhakim</i>	
Geometry Characterization of Products Results in the Finishing Process Using Centerless Belt Grinding Machine	49-60
<i>Jesika Erventy Osman, Sofia Debi Puspa*, Triyono, Hary Munandar</i>	
The Influence of Fuel Pump Pressure Variations on the Performance of 2-Stroke Gasoline Direct Injection Engines	61-68
<i>Darwin Rio Budi Syaka*, I Wayan Sugita, Nugroho Gama Yoga, Muhammad Riangga Widanarko</i>	
Design of Wind Speed Measurement System in Wind Tunnel Based on Pitot Tube	69-76
<i>Yudha Nurfauzi Nugraha, Erwin Erwin*, Slamet Wiyono</i>	
Study Characteristic Thermal Electric Generator (TEG) Type SP1848 27145 SA	77-88
<i>Sofia Debi Puspa*, I Putu Budi Dharma, Sentot Novianto, Supriyadi, M. Alfian Gibran</i>	
Analysis of Mechanical Properties and Microstructure of Aluminum and Copper Sheet Welding Using Friction Stir Spot Welding Method	89-102
<i>Adit Waisal, Hary Munandar*, Sofia Debi Puspa, Achdianto, Triyono</i>	
Comparative Analysis of a Rectifier Performance in Power Generation Applications	103-112
<i>Sri Agustina, Herlina Wahab*, Djulil Amri, Al Denton Mourzade</i>	
Effect of Heat Treatment Temperature on Hardness of Jaw Implant Produced from EDM Die-Sinking Process	113-120
<i>M. F. R. Suharyanto, Y. Kurniawan*</i>	

Numerical Analysis of Gurney Flap Impact on NACA 4415 Airfoil Aerodynamics Performance	121-132
<i>James Julian*, Mirza Fauzan Lukiano, Fitri Wahyuni, Waridho Iskandar, Nely Toding Bunga</i>	
Numerical Modelling of NACA 0015 Airfoil Under the Erosion Condition	133-142
<i>Rayhan Fariansyah Billad, James Julian*, Fitri Wahyuni, Waridho Iskandar, Nely Toding Bunga</i>	
Qualitative Stability and Thermal Properties Investigation of TiO₂-EG/W Nanofluids Through Experimental Validation	143-152
<i>Muhamad Taufik Ulhakim, Sukarman*, Khoirudin, Nazar Fazrin, Tomas Irfani, Amri Abdulah</i>	
Public Street Lighting Monitoring System Uses Telegram-Based Application Wireless Sensor Network	153-164
<i>Ilham Muhyidin Nabil*, Adnan Rafi Al Tahtawi, Supriyanto</i>	
Soft System Methodology Approach: Case Study of Renewable Energy Development of Wood Pellets as an Implementation of a Circular Economy	165-174
<i>Dino Rimantho*</i>	
Natural Lighting Study of the Smith Alam Sutra Building, Tangerang City	175-186
<i>Hendro Wahyu Purwanto, Samsu Hendra Siwi*, Eddy Supriyatna Marizar</i>	

*Corresponding Author

SERTIFIKAT

Direktorat Jendral Pendidikan Tinggi, Riset dan Teknologi
Kementerian Pendidikan, Kebudayaan, Riset dan Teknologi Republik Indonesia



Kutipan dari Keputusan Direktorat Jendral Pendidikan Tinggi, Riset, dan Teknologi
Kementerian Pendidikan, Kebudayaan, Riset dan Teknologi Republik Indonesia

Nomor: 225/E/KPT/2022

Peringkat Akreditasi Jurnal Ilmiah Periode IV Tahun 2022

Nama Jurnal Ilmiah:

Jurnal Asimetrik: Jurnal Ilmiah Rekayasa Dan Inovasi

E-ISSN: 27162923

Universitas Pancasila

Ditetapkan Sebagai Jurnal Ilmiah:

TERAKREDITASI PERINGKAT 3

Akreditasi Berlaku selama 5 (lima) Tahun, yaitu:
Volume 4 Nomor 2 Tahun 2022 sampai Volume 9 Nomor 1 Tahun 2027
Jakarta, 7 December 2022

Plt. Direktur Jendral Pendidikan Tinggi, Riset, dan Teknologi



Prof. Ir. Nizam, M.Sc., DIC, Ph.D., IPU, ASEAN Eng
NIP. 196107061987101001

TERAKREDITASI





Analysis of Mechanical Properties and Microstructure of Aluminum and Copper Sheet Welding Using Friction Stir Spot Welding Method

Analisis Sifat Mekanik dan Struktur Mikro Hasil Pengelasan Lembaran Aluminium dan Tembaga Menggunakan Metode Friction Stir Spot Welding

Adit Waisal, Hary Munandar*, Sofia Debi Puspa, Achdianto, Triyono

Mechanical Engineering Study Program, Faculty of Industrial Technology, Universitas Trisakti, Jakarta 11440, Indonesia

Article information:

Received:
07/10/2023
Revised:
06/11/2023
Accepted:
21/11/2023

Abstract

Welding aluminum and copper materials using friction stir spot welding (FSSW) is widely practiced. Although strong enough, it still produces keyhole and shoulder marks, which are quite large due to the large shoulder and pin sizes. This study investigates the joining of aluminum and copper panels using the FSSW technique using smaller shoulders and pins in different shoulder shapes. The study began by cutting aluminum and copper panels 150 mm long, 50 mm wide, and 5 mm thick. The joining process was carried out at rotational speeds of 900, 1200, and 1500 rpm with tools with several variations in pin length. Pin lengths of 0,5 and 7 mm with pin diameters made the same at 5 mm, shoulder diameter 20 mm. The connection was observed for macrostructure, microstructure, and hardness. Different tool geometries have the potential to be applied in FSSW joints, especially for sheets. The highest hardness value is found in Cu-Cu material welding, with an average hardness value of 101.63 HVN in the stir zone area. The lowest hardness value is located in the base metal of aluminum material, with an average hardness value of 48.37 HVN.

Keywords: FSSW, microstructure, mechanical, spot welding.

SDGs:



Abstrak

Penyambungan material aluminium dan tembaga dengan menggunakan metode *Friction Stir Spot Welding* (FSSW) telah banyak digunakan. Meski memiliki tenaga yang cukup besar, namun tetap menimbulkan lubang kunci dan bekas bahu yang cukup besar karena penggunaan ukuran bahu dan pin yang besar. Penelitian ini menyelidiki sambungan panel aluminium dan tembaga menggunakan teknik FSSW menggunakan bahu yang lebih kecil dan pin dengan bentuk bahu yang berbeda. Penelitian diawali dengan pemotongan panel aluminium dan tembaga dengan panjang 150 mm, lebar 50 mm, dan tebal 5 mm. Proses penyambungan dilakukan pada putaran 900, 1200, 1500 rpm dengan *tool* yang memiliki beberapa variasi panjang pin. Panjang pin 0, 5, dan 7 mm dengan diameter pin dibuat sama yaitu 5 mm, diameter shoulder 20 mm. Sambungan diamati struktur makro, struktur mikro dan kekerasan. Geometri *tool* yang berbeda berpotensi untuk dapat diaplikasikan dalam sambungan FSSW terutama untuk lembaran (*sheet*). Dan nilai kekerasan tertinggi terdapat pada saat pengelasan material Cu-Cu dengan nilai kekerasan rata-rata sebesar 101,63 HVN pada *brewing zone*. Nilai kekerasan terendah terdapat pada material logam dasar aluminium dengan nilai kekerasan rata-rata sebesar 48,37 HVN.

Kata Kunci: FSSW, mikrostruktur, mekanik, *spot welding*.

*Correspondence Author
email : hary.munandar@trisakti.ac.id



This work is licensed under a [Creative Commons Attribution-NonCommercial 4.0 International License](https://creativecommons.org/licenses/by-nc/4.0/)

1. INTRODUCTION

The technology known as Friction Stir Welding (FSW) is currently being utilized to weld different types of metals together. By joining dissimilar metals, like aluminum and steel, aluminum with magnesium, aluminum with copper, and steel with nickel, it is possible to maximize the strengths of both materials. This technique is beneficial in industries such as power generation, military, and electrical, where combining different materials can help reduce weight, improve corrosion resistance, and increase ductility. Fusion welding methods, which involve high heat and can lead to solidification defects and intermetallic compounds, are not ideal for dissimilar materials. However, FSW welding can reduce or eliminate these defects by utilizing a lower welding temperature than the melting point of the base metal (Esmaeili, Givi and Rajani, 2011).

During the welding process, aluminum welds can experience various welding defects like porosity, solidification, and liquidation cracking. These defects can also occur after the welding process. To overcome the lack of fusion welding, one can use friction-based solid-state welding methods such as Friction Stir Spot Welding (FSSW). FSSW replaces Resistance Spot Welding (RSW), challenging to implement on aluminum due to its high electrical conductivity, low electrical resistance, and an aluminum oxide layer on the surface with a high melting point. FSSW is a friction-based spot-welding method performed in a solid condition to avoid defects such as porosity, solidification, and liquidation cracking on the weld. This method is highly suitable for welding aluminum materials susceptible to melting (Tiwan, Iman, and Kusmono, 2021).

Friction Stir Spot Welding (FSSW) is a process that involves generating frictional heat through the interaction of the tool pin with the material. This causes the material to become pasty and extrude vertically. The tool shoulder then applies an upsetting action on the stirred material to form the weld nut. In the case of FSSW of thermoplastics, the process consists of four phases: plunging, stirring, solidifying, and retracting. The friction between the tool and the

plates generates the heat required to weld the plates (Benyerou *et al.*, 2021).

The FSSW process is a three-stage process that involves plunging, stirring, and drawing out. During the plunging stage, the rotating tool experiences high resistance from the workpiece. This resistance causes the workpiece to soften due to plastic deformation and frictional heat. In the dwell period, the heat generated by friction increases, allowing the material to flow in the weld zone. Finally, in the last stage, the rotating tool is drawn out from the weld zone. Overall, this process is a highly effective method for welding materials together, and it is widely used in various industries (Lewise and Dhas, 2022). The pinless friction stir spot welding (FSSW) process is similar to the conventional FSSW method. The welding process involves plunging the pinless tool slightly into the top sheet material, agitating it for a short dwell time, and then backing off (Li *et al.*, 2014). The tool retracts quickly and precisely once it reaches a specific depth and pause time (Venukumar *et al.*, 2014).

Research conducted by Çam *et al.* on advances in FSSW and FSSW plates of different Al alloys shows that applying the FSW/FSSW process on different Al alloys is relatively more accessible compared to FSW on various combinations of materials with different properties, such as alloys of Al with Mg or Al alloy with steel. The primary challenge in joining different Al alloys with FSW/FSSW is discontinuing the mechanical and technological properties (like high-temperature strength, plastic deformation capacity, viscosity, etc.) of the materials to be welded at the abutting surfaces. This discontinuity, along with the inherent asymmetry in heat generation and material flow in the FWS/FSSW process, leads to higher asymmetry in material flow behavior in different welding (Çam, Javaheri and Heidarzadeh, 2023).

A study was conducted by Andrade *et al.* on shoulder-related temperature thresholds in FSSW of aluminum alloys. The research results indicate that the temperature in FSSW can be regulated by using an appropriate combination of rotation speed and tool dimensions for aluminum alloys (Andrade *et al.*, 2021). The heat generation in aluminum alloy FSSW was assessed by producing

bead-on-plate spot welds with a pinless tool. The study tested coated and uncoated tools with varying diameters and rotation speeds. Heat-treatable (AA2017, AA6082, and AA7075) and non-heat-treatable (AA5083) aluminum alloys were welded to analyze the possible influence of base material properties on heat generation. The study found that for rotation speeds higher than 600 rpm, the tool diameter was the main process parameter governing heat generation.

Shen et al. researched refilling FSSW Al alloy to copper via a pure metallurgical joining mechanism. Defect-free Al/copper dissimilar welds were successfully created using backfilled FSSW. The process involved inserting a tool into the top Al alloy sheet. It identified two types of continuous and ultra-thin intermetallic compound (IMC) layers across the Al/copper interface. The local area also showed strong evidence of liquefaction and solidification. The peak temperature obtained at the center of the Al/copper interface during the penetration phase of the sleeve was 591 °C, and the heating rate reached up to 916 °C/s. The FSSW backfill process produced a softened weld area, visible through the W-shaped appearance of the hardness profile along the middle thickness of the upper Al alloy. The weld lap shear load was not sensitive to the welding conditions, and the load distribution was relatively small. Under external rotational shear loading, fracture paths exclusively propagated along the Cu₉Al₄ IMC layer. The fracture surface on the copper side showed the presence of both CuAl₂ and Cu₉Al₄. This study demonstrated that acceptable weld strength can be achieved via a purely metallurgical joining mechanism, which has significant potential for industrial applications (Shen et al., 2021).

As a relatively new welding technique, the current development of FSSW is still extensive in scope. The variables studied are very varied and exciting to develop. Aluminum (Al) and Copper (Cu) are two common materials that are widely used in the automotive and electrical industries, one of which was proposed by Mazda Motor Company Japan and then applied in its production (Shen, Ding and Gerlich, 2020). In making car bodies and batteries, several methods combine the material using welding, rivet, and adhesive

bonding technology to connect different materials. Utilizing this welding technology, researchers can find out the material's mechanical properties and the lifetime of the material so that it can be applied to the body and aircraft manufacturing industry. For this reason, researchers took the connection method with the Friction Stir Spot Welding process on aluminum material (Meschut, Janzen and Olfermann, 2014).

The connection process was tested at rotational speeds of 985, 1660, and 2350 rpm with two types of tooling (shoulder angle 0° and 5°). Research results showed that all joints had brittle fractures. As the shoulder angle of the tool rotation speed increases, the size of the welding spot and welding area increases, so the tensile load capacity increases to 2116 N (Nugroho, Saputra and Budiyanoro, 2019). A joint without hook defects showed a shear-tensile load of 12 kN, higher than 6.9 kN in a joint with hook defects (Li et al., 2014). Meanwhile, a study was also conducted from the use of Zn electroplating interlayer and gave optimal results in tensile testing on friction stir spot welding results of 3.8 kN while for the connection value without electroplating interlayer of 2.5 kN, as well as hardness testing which resulted in a more excellent value of 63 HV greater than without using electroplating interlayer (Saputra, Sukarno and Zulaehah, 2021). In previous research, the results of microstructure testing showed that the friction stir spot welding method could change the dimensions of the grains in the welding area (Sehono and Ardianto, 2021).

The focus of this research is to investigate the strength of welded joints made from different materials, specifically copper and aluminum. The research will involve measuring hardness and examining the microstructure. By using the FSSW process, we hope to determine how the joined material affects its mechanical properties and microstructure.

2. METHODOLOGY

2.1. Flowchart

The research flow chart is presented in Figure 1. This flow chart generally shows the steps

that will be taken in this research. From the literature study, determining the materials and machines to be used, the process parameters, and the number of samples to be used. Then, the sequence of implementation of the friction stir spot welding process is followed by taking complex test data and microstructure. The last stage is to analyze the data and discuss the results of this research.

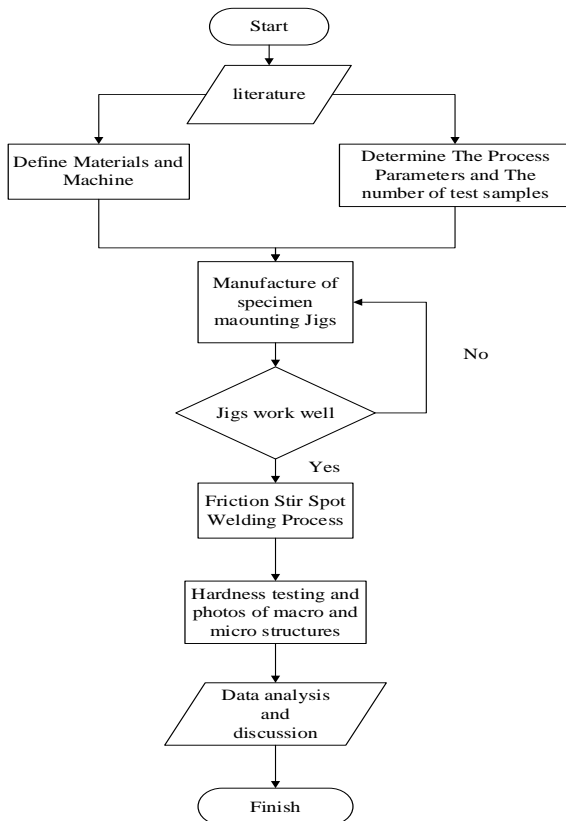


Figure 1. Research flowchart.

2.2. Research Location

In this research, the lathe and welding processes and data collection were conducted in the Production Process Laboratory and Physical Metallurgy Laboratory of the Department of Mechanical Engineering, Faculty of Industrial Technology, Trisakti University.

2.3. Research Equipment and Materials

2.3.1. Specifying Material

The materials to be welded were selected using Aluminum and Copper. Both sheets have dimensions of 150 mm x 50 mm x 5 mm in length. As for the specifications (Almaxco, 2015):

a) Aluminum:

- Material: Aluminum Alloy 1100-H14
- Density: 2.71 g/dm³
- Hardness: 23 (500 g load; 10 mm ball)
- Tensile Stress: 75-105 MPa (Ultimate), ≥ 20 Mpa (Yield)
- Elongation: 15-28%
- Modulus of Elasticity: 68.9 GPa
- Size: 150 mm x 50 mm x 5 mm

b) Copper:

- Material: Copper Alloy
- Purity: 98%
- Density: 89.6 g/cm³

Friction Stir Spot Welding requires tools, such as a Shoulder and Pin made of VCN steel material with specifications:

- Material: VCN 150 Steel
- Dimensions: ø20 mm (shoulder), 5 mm pin diameter
- Hardness: 220-250 BHN
- Heat treatment: 820-850 °C

2.3.2. Machines and Equipment

The welding process uses a vertical milling machine. The vertical milling machine is to be used with the following specifications:

- Brand: RRC Qinghai Universal lifting table milling machine.
- Model name: X61W
- Machine type: conventional
- Table size: 1000 x 250 mm
- Speed: 65 to 1800 pm
- Feeding: 12 to 980 mm/min

2.3.3. Setting Process Parameters

The process parameters used in this vertical milling machine are spindle rotation (to rotate the shoulder) of 900, 1200, and 1500 rpm. Because of spot welding, the welding is only local, or the shoulder does not move. The following test process variable is pin length, three (3) types: without pin, 5, and 7 mm, with a shoulder diameter of 18 mm. Figure 2 is the VCN material before the turning process, which will be used as a tool in the friction stir spot welding process, and Figure 3, Figure 4 and Figure 5 is a tool that has been turned.



Figure 2. VCN material before turning.



Figure 3. Tool shoulder with 7 mm pin (after turning).



Figure 4. Tool shoulder with 5 mm pin (after turning).



Figure 5. Tool shoulder without pin (after turning).

2.3.4. Sample Preparation using Friction Stir Spot Welding

2.3.4.1. Preparing Test Samples

The materials used are aluminum and copper sheets with a thickness of 5 mm. The sheet is then cut to 150 mm x 50 mm x 5 mm, as shown lap joint in Figure 6.

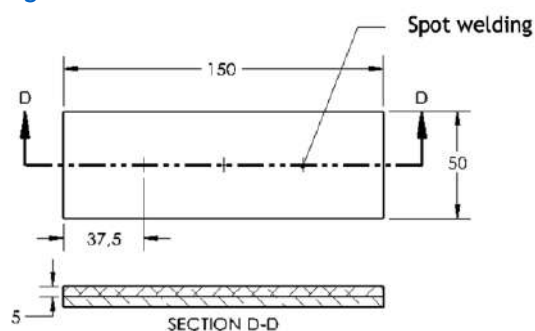


Figure 6. Lap joint aluminum and copper.

The material is used when cut into a predetermined size, as shown in Figure 7 and Figure 8.

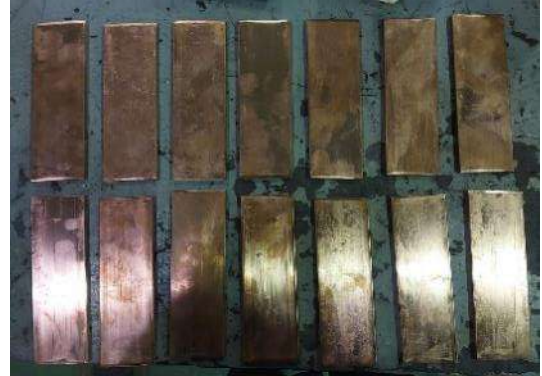


Figure 7. Copper material 150x50x5 mm.



Figure 8. Aluminum material 150x50x5 mm.

2.3.4.2. Creating Tools

The VCN steel tool used has the initial shape of a solid cylinder widely available on the market. Tool making is done according to Figure 9, Figure 10 and Figure 11. The tool has several pin length variations of without pin, 5, and 7 mm, with the pin diameter made the same at 5 mm and the shoulder diameter of 20 mm.

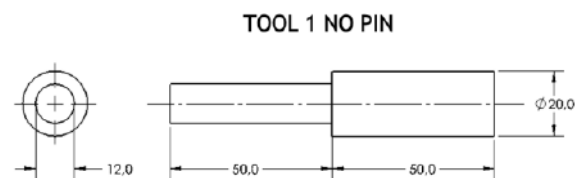


Figure 9. Pinless shoulder.

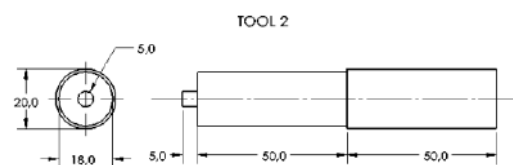


Figure 10. Shoulder with 5 mm x 5 mm pin.

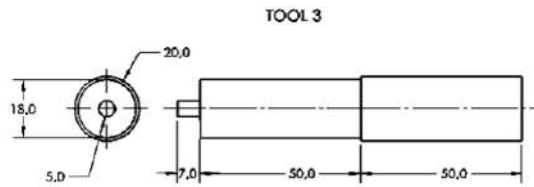


Figure 11. Shoulder with pin size 7 mm x 5 mm.

2.3.4.3. Jig Manufacturing Process

The design of jigs and fixtures is adjusted and specialized to hold and support certain workpieces. The fixture usage plan used in this research process is clamping. Figure 12 is the clam kit used in the machining process, and Figure 13 is the base kit.



Figure 12. Clamping Kit used in the FSW process.



Figure 13. Base Kit used in the FSW process.

2.3.4.4. Heat isolator

Gaskets are inserted on all surfaces between the bottom surface of the base kit and the milling machine table. Gaskets or packing used are non-asbestos gaskets or gaskets with a mixture of aramid/Kevlar/twain materials. Figure 14 shows the gasket before use and Figure 15 after use.



Figure 14. Gaskets used in the FSW process.

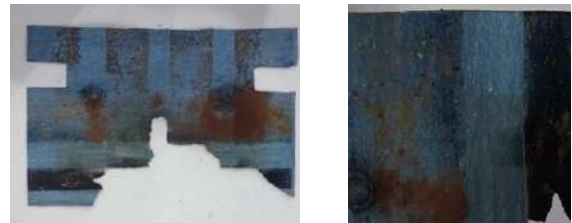


Figure 15. Condition of the gasket after being used in the FSW process.

2.3.4.5. Proses Friction Stir Spot Welding

Friction stir spot welding uses a vertical milling machine with a 900, 1200, and 1500 rpm rotation.

2.3.5. Hardness Testing and Microstructure

2.3.5.1. Preparation of Specimens for Testing

Before testing, the research specimens were cut and cross-section into three parts. The cut parts are leveled using a file, and the welding results are smoothed using sandpaper.

2.3.5.2. Hardness Testing

Hardness testing uses the Vickers method with a Universal Hardness Tester machine. This method is appropriate for soft materials such as Aluminum. The standard used in this test is ASTM E384. The indenter used is a pyramid-shaped diamond with a loading of 294 Nf (Newton Force) or equivalent to 29.9797 kgf (kilogram-force) with a loading time (dwell time) of 15 seconds (ASTM, 2017). Figure 16 is one of the hardness test shots of FSW material.

2.3.5.3. Microstructure Image

This test is carried out based on the intensity of the reflected light from the metal surface to the inside of the microscope, which causes different images to be seen (bright, slightly bright, dark) (Akramifard et al., 2014).

Before micro photos, the material that has undergone the FSSW process is smoothed (polished) and then etched with a Nitric acid (HN03) chemical solution. Determination of parts taken for micro photos are determined in Figure 17.



Figure 16. Hardness testing.

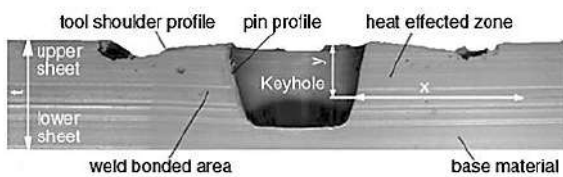


Figure 17. Microphoto position of the test sample (Bilici, 2012).

3. RESULTS AND DISCUSSION

The results and discussion present a description of the research data equipped with tables and figures. The result data obtained is analyzed and explained in detail the causes and effects of the data obtained and related to relevant reference sources.

3.1. Visual Observation of Friction Stir Spot Welding Results

The welding results with the friction stir spot welding method make different top appearances due to the influence of different rotational speeds and pin dimensions given in the welding process, which is also already stated and supported in the article that Friction stir spot welding (FSSW) is a variation of linear Friction Stir Welding (FSW) along the surface (Shen, Ding and Gerlich, 2020), as shown in Figures 18, Figure 19, and Figure 20.



Figure 18. Samples A1, A2, and A3 top view of FSSW welding results with 5 mm pin 5.1 mm welding depth.

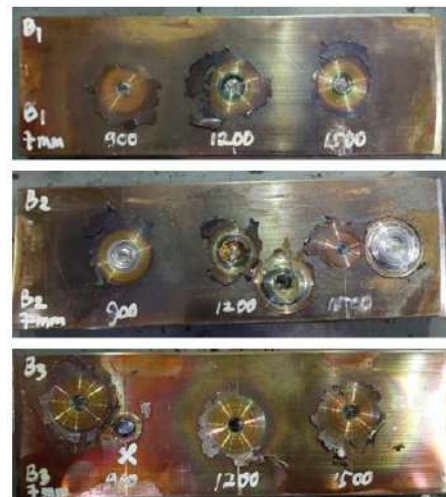


Figure 19. Samples B1, B2, and B3 top view of FSSW welding results with 7 mm pin welding depth of 7.1 mm.















Figure 20. Samples C1, C2, and C3 top view of FSSW welding without pin (0 mm) welding depth of 2 mm.

3.2. Results of Macro Photographs of Weld Cross Sections

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 1, Test sample C1 was the first trial before determining the depth of ingestion during the FSSW process, so the resulting depth differed from the other test samples as described in article that carbon galvanized steel using friction stir spot welding. Three conical pins with varying lengths (short, medium, and long) were utilized, along with different dwell times and rotation speeds of the tool. The objective of this research was to compare the simultaneous effects of several important process parameters on mechanical and welding properties (Feizollahi and Moghadam, 2023).













Table 1. Samples with tool without pin (0 mm).

Replication Code	Pin Length		
	0 mm		
	900 rpm	1200 rpm	1500 rpm
C1 Cu-Al			
C2 Cu-Al			
C3 Cu-Al			
Cu-Cu			

This different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial penetration of the tool in the welded area so that the sheet widens due to the tool's pressure. This is shown in the pictures in Table 1. Starting from C1 (Cu-Al), C2 (Cu-Al), C3 (Cu-Al), Cu-Cu and Al-Al. In Figure C1 (Cu-Al), with

a rotation speed of 900 rpm and a pressing depth of 6 mm, the perfect mixing of copper and aluminum is seen compared to other parameters. Along the joint, it does not connect perfectly with the visible gap from the two sides of the sheet that has been welded.













Table 2. Sample with 5 mm pin length tool.

Replication Code	Pin Length		
	5 mm		
	900 rpm	1200 rpm	1500 rpm
A1 Cu-Al			
A2 Cu-Al			
A3 Cu-Al			
Cu-Cu			

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 2, which is different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial penetration of the tool in the welded area due to the pressure of the tool, which is shown in the pictures in Table 2 starting from A1 (Cu-Al), A2 (Cu-Al), A3 (Cu-Al), Cu-Cu, Al-Al, and Al-Cu. Comparison of welding results between all specimens can be seen visually. There is perfect and less perfect diffusion in each test specimen, such as in test specimens rotated 900 rpm A1 (Cu-Al), A2 (Cu-Al) shows mixing between copper and aluminum, which is arguably quite good, and in test specimens with 1200 rpm on A3 (Cu-Al) shows mixing between copper and aluminum which is arguably quite good.

Meanwhile, the different parameters show fusion imperfections in the welding mixture area, which is not perfectly stirred to form a joining, which is visible in the picture in Table 2 where the welding area is included. This is because the mixture should melt and stir upwards to join and form a surface on the welded sheet.

Table 3. Sample with 7 mm pin length tool.

Replication Code	Pin Length		
	7 mm		
	900 rpm	1200 rpm	1500 rpm
B1 Cu-Al			
B2 Cu-Al			
B3 Cu-Al			
Cu-Cu			

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 3, which is different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial tool penetration in the welded area due to the tool's pressure. This is shown in the images in Table 3, starting from A1 (Cu-Al), A2 (Cu-Al), A3 (Cu-Al), Cu-Cu, Al-Al, and Al-Cu. These results are different compared to the previous results using the tool without a pin (0 mm) and the tool with a 5 mm pin. For the results of stirring with a pin length of 7 mm, there is a perfection of fusion in the weld mixture area as shown in Table 3. The size of the pin affects the perfect stirring to form the joining, which is visible in the figure in Table 3, where the weld area is formed.

3.3. Microstructure Observation

The determination of parts taken for micro photos are determined in position 1, namely the base metal (BM), position 2, namely the stir zone, position 3, namely the HAZ section as described in Figure 21 from the Cu-Al, Cu-Cu, Al-Al, and Al-Cu.

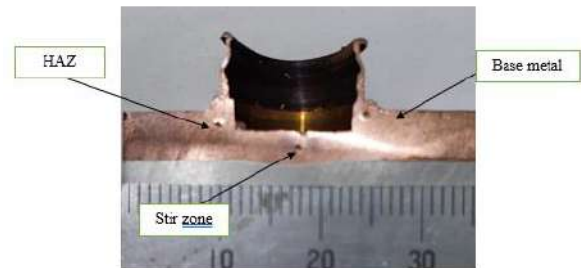


Figure 21. Position for a micro photo of the test sample.

3.3.1. Base Metal

Base metal is an area that is not affected by the welding heat of either the mortar or the heat generated.

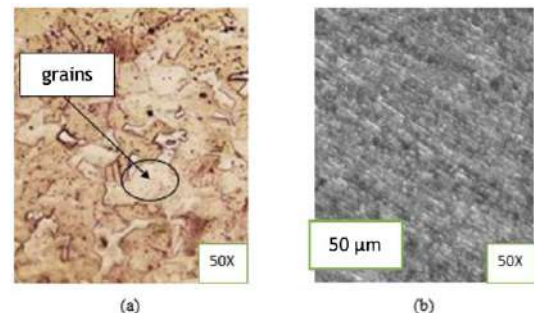


Figure 22. Microstructure of base metal material (a) Copper, (b) Aluminum.

In Figure 22, (a) the base copper base metal the black particles and square grains are Cu₂O, while in an image (b) shows aluminum base metal, and the evenly distributed black particles are FeAl₃.

3.3.2. HAZ (Heat Affected Zone)

The HAZ region is an area that undergoes a thermal cycle but does not undergo plastic deformation, in this area there are also changes in microstructure. The HAZ area will change grain size, where the size is influenced by material characteristics, temperature, welding process, and cooling rate.

In Figure 23, the HAZ grain size of Cu-Cu welding experiences a slight change in grain size getting bigger compared to the base metal Cu material. While in the Cu-Al and Al-Al welding HAZ area the size of the copper grain structure is smaller than the grain size in the base metal area.

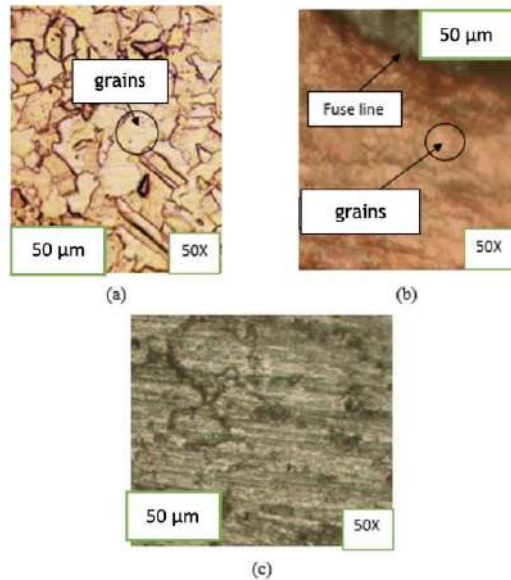


Figure 23. Microstructure of HAZ (a) Cu-Cu, (b) Cu-Al and (c) Al-Al.

The study aimed to investigate the heat generation in FSSW (Friction Stir Spot Welding) of aluminum and copper alloys. This was done by creating bead spot welds on plates using both pinless and pinned tools with the same diameter and varying rotational speeds. The results showed that tool diameter is the main process parameter governing heat generation for rotational rates higher than 600 rpm. The rotating tool transfers heat to the surface of the aluminum and copper plate material. Welding temperature thresholds were identified, depending on the rotational speed and the aluminum alloy being welded, with respect to the tool diameter. It was found that the temperature in FSSW can be controlled by using an appropriate combination of rotational speed and tool dimensions for aluminum and copper alloys subjected to temperature rise (Andrade *et al.*, 2021).

3.3.3. Stir Zone

The Stir Zone is the area directly affected by the heat generated during welding and the deformed area due to the stirring process of the

pin tool. Welding and the deformed area due to the stirring process of the pin tool.

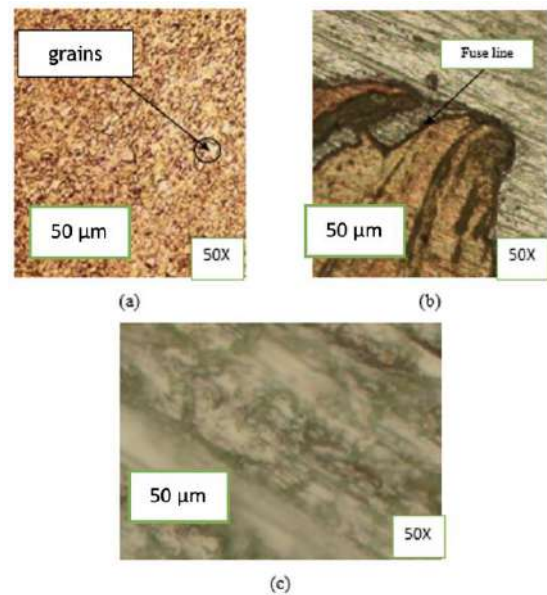


Figure 24. Microstructure of Stir Zone Region, (a) Cu-Cu welding, (b) Cu-Al welding, (c) Al-Al welding

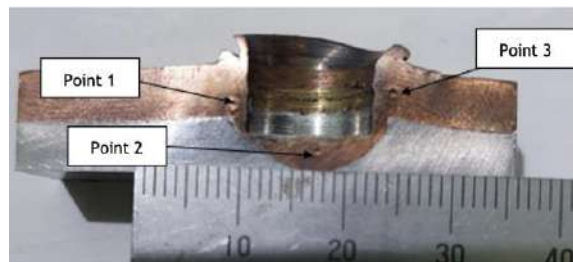
In Figure 24, it can be seen that the microstructure of the stir zone area of all welding results has changed the grain size to be very small and looks smooth compared to the HAZ and base metal areas, and also in welding Cu-Cu, Al-Al materials, this is due to the influence of high temperatures by the pin tool as a stirrer and shoulder as preheating during the welding process and for different Cu-Al materials, the grain boundaries are not very visible due to the lack of polishing so that only the stretch marks are visible in the material mixture.

3.4. Hard Test on Welded Cross Sections


Microstructure testing was carried out at the Metallurgical Laboratory of Trisakti University. The determination of parts taken for microphotographs are determined in position 1, namely the point 1 section, position 2, namely the point 2 section, position 3, namely the point 3 section as described in Figure 25.

3.5. Hardness Test Results


The following are the results of hardness testing on the welding results at indentation points 1, 2 and 3 with the friction stir spot welding method in Table 4 and Table 5.



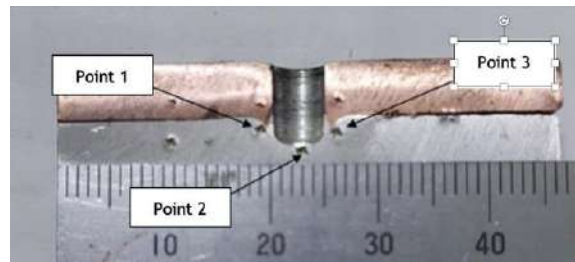
(a) Indentation points on Cu-Al material without pins



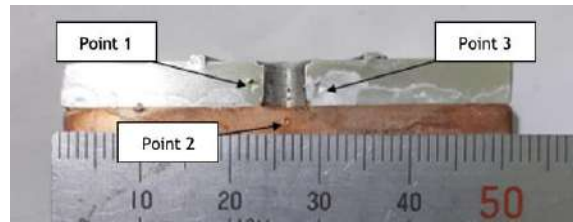(b) Indentation point on 7 mm Cu-Al material



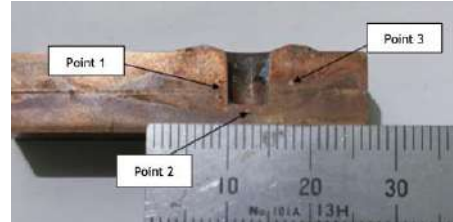(c) Indentation point on 5 mm Al-Cu pin material



(d) Indentation point on 7 mm Cu-Cu pin material

Figure 25. Indentation points of samples.

Table 4 is the average hardness value obtained from several indentation points, namely at points 1, 2, and 3, each of which is taken from Cu-Cu, Cu-Al, and Al-Cu materials. Then, the average value is taken to produce a value as in Table 5.



Table 4. Hard test values of test samples in Cu-Cu, Cu-Al, Al-Cu materials.

Zone	HVN Hardness Value in Materials		
	Cu-Cu	Cu-Al	Al-Cu
Point 1	83.3	70.2	69.7
Point 1	78.1	71.4	66.1
Point 1	76	70.8	67,4
Point 3	67.8	71.7	71.1
Point 3	72.1	72.5	69.5
Point 3	71.3	72.7	73.1
Point 2	90.9	77.2	74.1
Point 2	105.9	76.6	73.5
Point 2	108.1	79.4	72.4
Point 3	73.9	50.4	66.6
Point 3	71.7	51.2	68.5
Point 3	67.5	49.6	71.2
Point 1	75.86	48.7	64.2
Point 1	75.72	48.1	65.4
Point 1	72.4	48.3	64.7

Table 5. Average values of hard test on test samples in Cu-Cu, Cu-Al, and Al-Cu materials

Materials	Point 1	Point 3	Point 2	Point 3	Point 1
Cu-Cu	79.16	70.4	101.63	71.03	74.66
Cu-Al	70.8	72.3	85.07	50.4	48.37
Al-Cu	67.73	71.23	73.3	68.76	64.76

Figure 26 as shown histogram of hard test results in the welding process produces a distribution of hardness in Vickers testing as in Figure 27 as a graph of the average value of hard test on test samples in Cu-Cu, Cu-Al, and Al-Cu materials. The average hardness test results show that the point 2 areas all have the highest hardness value compared to other areas, namely point 1 and point 3 area.

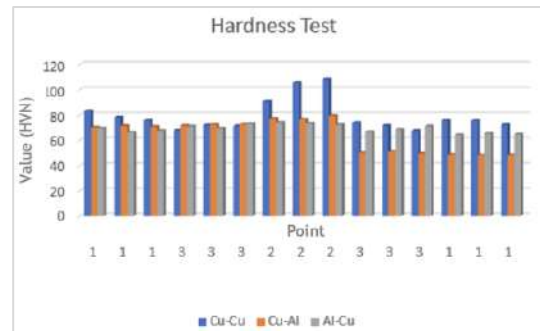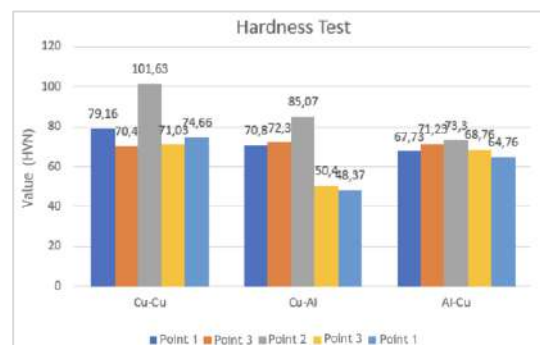**Figure 26.** Histogram of hardness test.**Figure 27.** Average hard test results.

In the Cu-Cu specimen, there is a slight decrease in hardness from the base metal to the HAZ area, and this is because it experiences softening, which is influenced by the heat from the welding process. It can be seen from the results of the micro photo that the grain size looks more significant than the base metal grains because the smaller the grain size, the greater the hardness value and vice versa. In Figure 27 the highest hardness value is found in Cu-Cu welding, with an average hardness value of 101.63 HVN at point 2. The lowest hardness value is found in aluminum material, with an average hardness value of 48.37 HVN in point 1 area.

4. CONCLUSION

FSSW can be applied to sheets with several parameters that need to be considered. Based on observations of FSSW welding joints variations in pin tool length are very influential, the use of pin tools that are too short or without pins results in a less-than-optimal connection.

Pin tool with a length of 7 mm found the welding results are quite optimal. The rotational speed of 1500 rpm obtained the largest hook compared to the rotational speed of 900 to 1200 rpm in the pinless FSSW welding results. Then the more the rotational speed increases, the greater the Vickers hardness value on the aluminum part closest to the center of the nugget.

From the results of the distribution of hardness values, the lowest hardness was obtained by test sample A (5mm pin) at A1 900 rpm, namely 72.91 HV30, while the highest hardness value was obtained by test sample A (5 mm pin) at A3 1500 rpm, namely 76.94 HV30. The lowest hardness was obtained by test sample B (7 mm pin) at B1 900 rpm, 72.89 HV30, while the highest hardness value was obtained by test sample B3 1500 rpm, 79.33 HV30. The test result for test sample C (0 mm pin) at C1 900 rpm, namely 65.80 HV30, while the highest hardness value was obtained by test sample C (0mm pin) at C3 1500 rpm, namely 69.12 HV30.

Based on the results of hardness testing, the highest hardness value is found in Cu-Cu welding with an average hardness value of 101.63 HVN at point 2. The lowest hardness value is found in

aluminum material with an average hardness value of 48.37 HVN in point 1.

REFERENCES

- Akramifard, H.R. *et al.* (2014) 'Microstructure and mechanical properties of Cu/SiC metal matrix composite fabricated via friction stir processing', *Materials & Design* (1980-2015), 54, pp. 838-844.
- Almaxco, A. (2015) *Aluminium Alloy 1100 - H18*, Almaxco. Available at: <https://almaxco.com/wp-content/uploads/2023/06/Aluminium-Alloy-AA-1100.pdf> (Accessed: 15 May 2023).
- Andrade, D.G. *et al.* (2021) 'Shoulder Related Temperature Thresholds in FSSW of Aluminium Alloys', *Materials*, 14(16), p. 4375.
- ASTM, A. (2017) 'ASTM E384-17: Standard Test Method for Microindentation Hardness of Materials'. Available at: <https://www.astm.org/e0384-17.html> (Accessed: 9 January 2023).
- Benyerou, D. *et al.* (2021) 'Parametric Study Of Friction Stir Spot Welding (FSSW) For Polymer Materials Case Of High Density Polyethylene Sheets: Experimental And Numerical Study', *Frattura ed Integrità Strutturale*, 15(55).
- Bilici, M.K. (2012) 'Effect of tool geometry on friction stir spot welding of polypropylene sheets', *EXPRESS Polymer Letters*, 6(10), pp. 805-813.
- Çam, G., Javaheri, V. and Heidarzadeh, A. (2023) 'Advances in FSW and FSSW of dissimilar Al-alloy plates', *Journal of Adhesion Science and Technology*, 37(2), pp. 162-194.
- Esmaili, A., Givi, M.K.B. and Rajani, H.R.Z. (2011) 'A metallurgical and mechanical study on dissimilar Friction Stir welding of aluminum 1050 to brass (CuZn30)', *Materials Science and Engineering: A*, 528(22), pp. 7093-7102.
- Feizollahi, V. and Moghadam, A.H. (2023) 'Effect of pin geometry, rotational speed, and dwell time of tool in dissimilar joints of low-carbon galvanized steel and aluminum 6061-T6 by friction stir spot welding', *Results in Materials*, 20, p. 100483.

- Lewis, K.A.S. and Dhas, J.E.R. (2022) 'FSSW process parameter optimization for AA2024 and AA7075 alloy', *Materials and Manufacturing Processes*, 37(1), pp. 34-42.
- Li, W. et al. (2014) 'Improving mechanical properties of pinless friction stir spot welded joints by eliminating hook defect', *Materials & Design (1980-2015)*, 62, pp. 247-254.
- Meschut, G., Janzen, V. and Olfermann, T. (2014) 'Innovative and Highly Productive Joining Technologies for Multi-Material Lightweight Car Body Structures', *Journal of Materials Engineering and Performance*, 23(5), pp. 1515-1523.
- Nugroho, A.W., Saputra, M.R.D. and Budiyanoro, C. (2019) 'Pengaruh Kecepatan Putar Tool dan Sudut Shoulder Sambungan Friction Stir Spot Welding pada Bahan Polypropylene', *Semesta Teknika*, 22(2), pp. 183-193.
- Saputra, L.A., Sukarno, N.A. and Zulaehah, S. (2021) 'Pengaruh Interlayer Elektroplating Zinc pada Kekuatan Mekanik Friction Stir Spot Welding Aa1100-Ss400', *Semesta Teknika*, 24(2), pp. 93-101.
- Sehono and Ardianto, H. (2021) 'Efek Friction Stir Spot Welding Dalam Pemasangan Rivet Terhadap Sifat Mekanik Material Almunium Seri 2024', *Teknika STTKD: Jurnal Teknik, Elektronik, Engine*, 7(2), pp. 184-192.
- Shen, Z. et al. (2021) 'Refill Friction Stir Spot Welding Al Alloy to Copper via Pure Metallurgical Joining Mechanism', *Chinese Journal of Mechanical Engineering*, 34(1), p. 75.
- Shen, Z., Ding, Y. and Gerlich, A.P. (2020) 'Advances in friction stir spot welding', *Critical Reviews in Solid State and Materials Sciences*, 45(6), pp. 457-534.
- Tiwan, Ilman, M.N., and Kusmono (2021) 'Microstructure and mechanical properties of friction stir spot welded AA5052-H112 aluminum alloy', *Heliyon*, 7(2), p. e06009.
- Venukumar, S. et al. (2014) 'Microstructural and Mechanical Properties of Walking Friction Stir Spot Welded AA 6061-T6 Sheets', *Procedia Materials Science*, 6, pp. 656-665.

Analysis of Mechanical Properties and Microstructure of Aluminum and Copper Sheet Welding Using Friction Stir Spot Welding Method

by Sofia Debi Puspa Debi Puspa

Submission date: 10-Jun-2024 03:29PM (UTC+0700)

Submission ID: 2399432592

File name: ASIIMETRIK_Spot_Welding_Method_Adit.pdf (1.2M)

Word count: 5954

Character count: 30110



Analysis of Mechanical Properties and Microstructure of Aluminum and Copper Sheet Welding Using Friction Stir Spot Welding Method

Analisis Sifat Mekanik dan Struktur Mikro Hasil Pengelasan Lembaran Aluminium dan Tembaga Menggunakan Metode Friction Stir Spot Welding

Adit Waisal, Hary Munandar*, Sofia Debi Puspa, Achdianto, Triyono

Mechanical Engineering Study Program, Faculty of Industrial Technology, Universitas Trisakti, Jakarta 11440, Indonesia

Article information:

Received:

07/10/2023

Revised:

06/11/2023

Accepted:

21/11/2023

Abstract

Welding aluminum and copper materials using friction stir spot welding (FSSW) is widely practiced. Although strong enough, it still produces keyhole and shoulder marks, which are quite large due to the large shoulder and pin sizes. This study investigates the joining of aluminum and copper panels using the FSSW technique using smaller shoulders and pins in different shoulder shapes. The study began by cutting aluminum and copper panels 150 mm long, 50 mm wide, and 5 mm thick. The joining process was carried out at rotational speeds of 900, 1200, and 1500 rpm with tools with several variations in pin length. Pin lengths of 0, 5 and 7 mm with pin diameters made the same at 5 mm, shoulder diameter 20 mm. The connection was observed for macrostructure, microstructure, and hardness. Different tool geometries have the potential to be applied in FSSW joints, especially for sheets. The highest hardness is found in Cu-Cu material welding, with an average hardness value of 101.63 HVN in the stir zone area. The lowest hardness value is located in the base metal of aluminum material, with an average hardness value of 48.37 HVN.

Keywords: FSSW, microstructure, mechanical, spot welding.

SDGs:



Abstrak

Penyambungan material aluminium dan tembaga dengan menggunakan metode *Friction Stir Spot Welding* (FSSW) telah banyak digunakan. Meski memiliki tenaga yang cukup besar, namun tetap menimbulkan lubang kunci dan bekas bahu yang cukup besar karena penggunaan ukuran bahu dan pin yang besar. Penelitian ini menyelidiki sambungan panel aluminium dan tembaga menggunakan teknik FSSW menggunakan bahu yang lebih kecil dan pin dengan bentuk yang berbeda. Penelitian diawali dengan pemotongan panel aluminium dan tembaga dengan panjang 150 mm, lebar 50 mm, dan tebal 5 mm. Proses penyambungan dilakukan pada putaran 900, 1200, 1500 rpm dengan tool yang memiliki beberapa variasi panjang pin. Panjang pin 0, 5, dan 7 mm dengan diameter pin dibuat sama yaitu 5 mm, diameter shoulder 20 mm. Sambungan diamati struktur makro, struktur mikro dan kekerasan. Geometri tool yang berbeda berpotensi untuk dapat diaplikasikan dalam sambungan FSSW terutama untuk lembaran (*sheet*). Dan nilai kekerasan tertinggi terdapat pada saat pengelasan material Cu-Cu dengan nilai kekerasan rata-rata sebesar 101,63 HVN pada *stir zone*. Nilai kekerasan terendah terdapat pada material logam dasar aluminium dengan nilai kekerasan rata-rata sebesar 48,37 HVN.

Kata Kunci: FSSW, mikrostruktur, mekanik, spot welding.

*Correspondence Author

email : hary.munandar@trisakti.ac.id



22

This work is licensed under a Creative Commons Attribution-NonCommercial 4.0 International License

1. INTRODUCTION

The technology known as Friction Stir Welding (FSW) is currently being utilized to weld different types of metals together. By joining dissimilar metals, like aluminum and steel, aluminum with magnesium, aluminum with copper, and steel with nickel, it is possible to maximize the strengths of both materials. This technique is beneficial in industries such as power generation, military, and electrical, where combining different materials can help reduce weight, improve corrosion resistance, and increase ductility. Fusion welding methods, which involve high heat and can lead to solidification defects and intermetallic compounds, are not ideal for dissimilar materials. However, FSW welding can reduce or eliminate these defects by utilizing a lower welding temperature than the melting point of the base metal (Esmaeili, Givi and 5 jani, 2011).

During the welding process, aluminum welds can experience various welding defects like porosity, solidification, and liquida⁵tion cracking. These defects can also occur after the welding process. To overcome the lack of fusion welding, one can use friction-based solid-state welding methods such as Friction Stir Spot Welding (FSSW). FSSW replaces Resistance Spot Welding (RSW), challenging to implement on aluminum due to its high electrical conductivity, low electrical resistance, and an aluminum oxide⁵ layer on the surface with a high melting point. FSSW is a friction-based spot-welding method performed in a solid condition to avoid defects such as porosity, solidification, and liquidation cracking on the weld. This method is highly suitable for welding aluminum materials susceptible to melting (Tiwan, Ilman, and Kusmono, 2021).

Friction Stir Spot Welding (FSSW) is a process that involves generating frictional heat through the interaction of the tool pin with the material¹⁸. This causes the material to become pasty and extrude vertically. The tool shoulder then applies an upsetting action on the stirred material to form the weld nut. In the case²³ of FSSW of thermoplastics, the process consists of four phases: plunging, stirring, solidifying, and retracting. The friction between the tool and the

plates generates the heat required to weld the plates (Benyerou *et al.*, 2021).

The FSSW process is a three-stage process that involves plunging, stirring, and drawing out. During the plunging stage, the rotating tool experiences high resistance from the workpiece. This resistance causes the workpiece to soften due to plastic deformation and frictional heat. In the dwell period, the heat generated by friction increases, allowing the material to flow in the weld zone. Finally, in the last stage, the rotating tool is drawn out from the weld zone. Overall, this process is a highly effective method for welding materials together, and it is widely used in various industries (Lewise and D⁹s, 2022). The pinless friction stir spot welding (FSSW) process is similar to the conventional FSSW method. The welding process involves plunging the pinless tool slightly into the top sheet material, agitating it for a short dwell time, and then backing off (Li *et al.*, 2014). The tool retracts quickly and precisely once it reaches a specific depth and pause time (Venukumar *et al.*, 2014).

Research conducted by Çam *et al.* on advances in FSSW and FSSW plates of different Al alloys shows that applying the FSW/FSSW process on different Al alloys is relatively more accessible compared to FSW on various combinations of materials with different properties, such as alloys of Al with steel or Al alloy with steel. The primary challenge in joining different alloys with FSW/FSSW is discontinuing the mechanical and technological properties (like high-temperature strength, plastic deformation capacity, viscosity, etc.) of the materials to be welded at the abutting surfaces. This discontinuity, along with the inherent asymmetry in heat generation and material flow in the FWS/FSSW process, leads to higher asymmetry in material flow behavior in different welding (Çam, Javaheri and Heid³zadeh, 2023).

A study was conducted by Andrade *et al.* on shoulder-related temperature thresholds in FSSW of aluminum alloys. The research results indicate that the temperature in FSSW can be regulated by using an appropriate combination of rotation speed and tool dimensions for aluminum alloys (Andrade *et al.*, 2021). The heat generation in aluminum alloy FSSW was assessed by producing

bead-on-plate ¹ot welds with a pinless tool. The study tested coated and uncoated tools with varying diameters and rotation speeds. Heat-treatable (AA2017, AA6082, and AA7075) and non-heat-treatable (AA5083) aluminum alloys were welded to analyze the possible influence of base ¹aterial properties on heat generation. The study found that for rotation speed ¹higher than 600 rpm, the tool diameter was the main process parameter governing heat generation. ²

Shen et al. researched refilling FSSW Al alloy to copper ² a pure metallurgical joining mechanism. Defect-free Al/copper dissimilar welds were successfully created using backfilled FSSW. The process involved inserting a tool into the top Al alloy sheet. It identified two types of continuous and ultra-thin intermetallic compound (IMC) layers across the Al/copper interface. The local area also showed strong ²vidence of liquefaction and solidification. The peak temperature obtained at the center of the Al/copper interface ²during the penetration phase of the sleeve was 591 °C, and the heating rate reached up to 916 °C/s. The FSSW backfill process ³roduced a softened weld area, visible through the W-sha²d appearance of the hardness profile along the middle thickness of the upper Al alloy. The weld lap shear load was not sensitive to the welding conditions, and the load distribution was relatively small. Under external rotational shear loading, fracture paths exclusively propagated along the Cu₉Al₄ IMC layer. The fracture surface on the copper side showed the presence of ²th CuAl₂ and Cu₉Al₄. This study demonstrated that acceptable weld strength can be achieved via a purely metallurgical joining mechanism, which has significant potential for industrial applications (Shen et al., 2021).

As a relatively new welding technique, the current development of FSSW is still extensive in scope. The variables studied are very varied and exciting to develop. Aluminum (Al) and Copper (Cu) are two common materials that are widely used in the automotive and electrical industries, one of which was proposed by Mazda Motor Company Japan and then applied in its production (Shen, Ding and Gerlich, 2020). In making car bodies and batteries, several methods combine the material using welding, rivet, and adhesive

bonding technology to connect different materials. Utilizing this welding technology, researchers can find out the material's mechanical properties and the lifetime of the material so that it can be applied to the body and aircraft manufacturing industry. For this reason, researchers took the connection method with the Friction Stir Spot Welding process on aluminum material (Meschut, Janzen and Olfermann, 201⁴).

The connection process was tested at rotational speeds of 985, 1660, and 2350 rpm with two type⁴ of tooling (shoulder angle 0° and 5°). Research results showed that all joints had brittle fractures. As the shoulder angle of the tool rotation speed increases, the size of the welding spot and welding area increases, so the tensile load capacity increases to 2116 N (Nugroho, Saputra and Budiyanoro, 2019). A joint without hook defects showed a shear-tensile load of 12 kN, higher than 6.9 kN in a joint with hook defects (Li et al., 2014). Meanwhile, a study was also conducted from the use of Zn electroplating interlayer and gave optimal results in tensile testing on friction stir spot welding results of 3.8 kN while for the connection value without electroplating interlayer of 2.5 kN, as well as hardness testing which resulted in a more excellent value of 63 HV greater than without using electroplating interlayer (Saputra, Sukarno and Zulaehah, 2021). In previous research, the ³results of microstructure testing showed that the friction stir spot welding method could change the dimensions of the grains in the welding area (Sehono and Ardianto, 2021).

The focus of this research is to investigate the strength of welded joints made from different materials, specifically copper and aluminum. The research will involve measuring hardness and examining the microstructure. By using the FSSW process, we hope to determine how the joined material affects its mechanical properties and microstructure.

2. METHODOLOGY

2.1. Flowchart

The research flow chart is presented in Figure 1. This flow chart generally shows the steps

that will be taken in this research. From the literature study, determining the materials and machines to be used, the process parameters, and the number of samples to be used. Then, the sequence of implementation of the friction stir spot welding process is followed by taking complex test data and microstructure. The last stage is to analyze the data and discuss the results of this research.

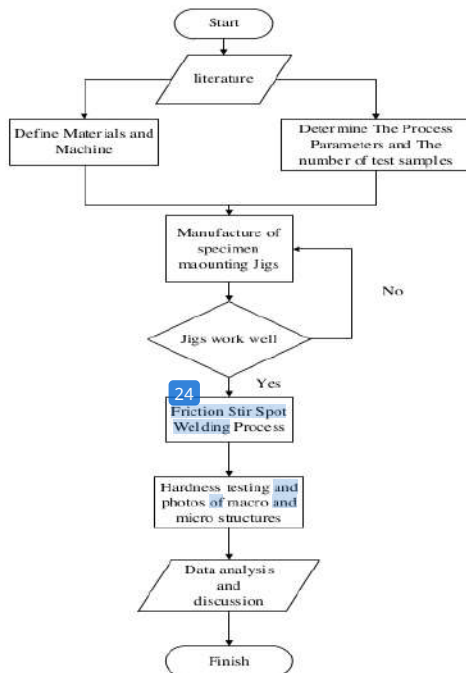


Figure 1. Research flowchart.

2.2. Research Location

In this research, the lathe and welding processes and data collection were conducted in the Production Process Laboratory and Physical Metallurgy Laboratory of the Department of Mechanical Engineering, Faculty of Industrial Technology, Trisakti University.

2.3. Research Equipment and Materials

2.3.1. Specifying Material

The materials to be welded were selected using Aluminum and Copper. Both sheets have dimensions of 150 mm x 50 mm x 5 mm in length. As for the specifications (Almaxco, 2015):

a) Aluminum:

- Material: Aluminum Alloy 1100-H14
- Density: 2.71 g/dm³
- Hardness: 23 (500 g load; 10 mm ball)
- Tensile Stress: 75-105 MPa (Ultimate), ≥ 20 Mpa (Yield)
- Elongation: 15-28%
- Modulus of Elasticity: 68.9 GPa
- Size: 150 mm x 50 mm x 5 mm

b) Copper:

- Material: Copper Alloy
- Purity: 98%
- Density: 89.6 g/cm³

Friction Stir Spot Welding requires tools, such as a Shoulder and Pin made of VCN steel material with specifications:

- Material: VCN 150 Steel
- Dimensions: ø20 mm (shoulder), 5 mm pin diameter
- Hardness: 220-250 BHN
- Heat treatment: 820-850 °C

2.3.2. Machines and Equipment

The welding process uses a vertical milling machine. The vertical milling machine is to be used with the following specifications:

- Brand: RRC Qinghai Universal lifting table milling machine.
- Model name: X61W
- Machine type: conventional
- Table size: 1000 x 250 mm
- Speed: 65 to 1800 rpm
- Feeding: 12 to 980 mm/min

2.3.3. Setting Process Parameters

The process parameters used in this vertical milling machine are spindle rotation (to rotate the shoulder) of 900, 1200, and 1500 rpm. Because of spot welding, the welding is only local, or the shoulder does not move. The following test process variable is pin length, three (3) types: without pin, 5, and 7 mm, with a shoulder diameter of 18 mm. Figure 2 is the VCN material before the turning process, which will be used as a tool in the friction stir spot welding process, and Figure 3, Figure 4 and Figure 5 is a tool that has been turned.



Figure 2. VCN material before turning.



Figure 3. Tool shoulder with 7 mm pin (after turning).



Figure 4. Tool shoulder with 5 mm pin (after turning).



Figure 5. Tool shoulder without pin (after turning).

2.3.4. Sample Preparation using Friction Stir Spot Welding

2.3.4.1. Preparing Test Samples

The materials used are aluminum and copper sheets with a thickness of 5 mm. The sheet is then cut to 150 mm x 50 mm x 5 mm, as shown lap joint in Figure 6.

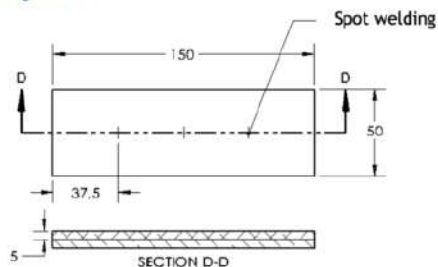


Figure 6. Lap joint aluminum and copper.

The material is used when cut into a predetermined size, as shown in Figure 7 and Figure 8.

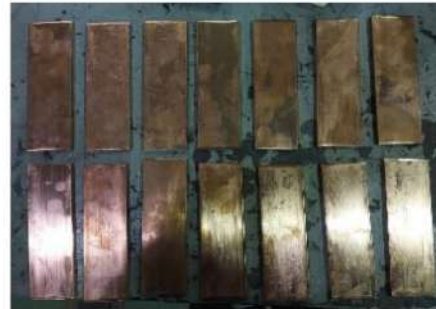


Figure 7. Copper material 150x50x5 mm.



Figure 8. Aluminum material 150x50x5 mm.

2.3.4.2. Creating Tools

The VCN steel tool used has the initial shape of a solid cylinder widely available on the market. Tool making is done according to Figure 9, Figure 10 and Figure 11. The tool has several pin length variations of without pin, 5, and 25 mm, with the pin diameter made the same at 5 mm and the shoulder diameter of 20 mm.

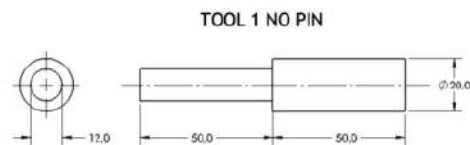


Figure 9. Pinless shoulder.

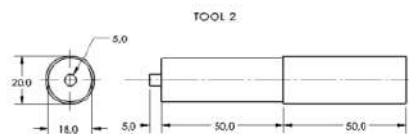


Figure 10. Shoulder with 5 mm x 5 mm pin.

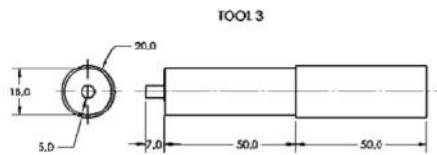


Figure 11. Shoulder with pin size 7 mm x 5 mm.

2.3.4.3. Jig Manufacturing Process

The design of jigs and fixtures is adjusted and specialized to hold and support certain workpieces. The fixture usage plan used in this research process is clamping. Figure 12 is the clam kit used in the machining process, and Figure 13 is the base kit.



Figure 12. Clamping Kit used in the FSSW process.



Figure 13. Base Kit used in the FSSW process.

2.3.4.4. Heat isolator

Gaskets are inserted on all surfaces between the bottom surface of the base kit and the milling machine table. Gaskets or packing used are non-asbestos gaskets or gaskets with a mixture of aramid/Kevlar/twain materials. Figure 14 shows the gasket before use and Figure 15 after use.

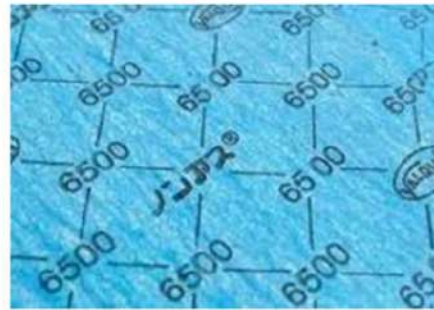


Figure 14. Gaskets used in the FSSW process.

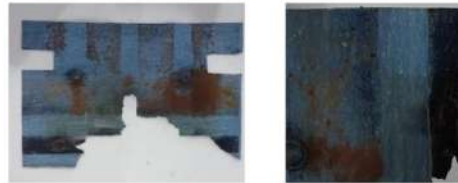


Figure 15. Condition of the gasket after being used in the FSSW process.

2.3.4.5. Proses Friction Stir Spot Welding

Friction stir spot welding uses a vertical milling machine with a 900, 1200, and 1500 rpm rotation.

2.3.5. Hardness Testing and Microstructure

2.3.5.1. Preparation of Specimens for Testing

Before testing, the research specimens were cut and cross-section into three parts. The cut parts are leveled using a file, and the welding results are smoothed using sandpaper.

2.3.5.2. Hardness Testing

Hardness testing uses the Vickers method with a Universal Hardness Tester machine. This method is appropriate for soft materials such as Aluminum. The standard used in this test is ASTM E384. The indenter used is a pyramid-shaped diamond with a loading of 294 Nf (Newton Force) or equivalent to 29.9797 kgf (kilogram-force) with a loading time (dwell time) of 15 seconds (ASTM, 2017). Figure 16 is one of the hardness test shots of FSSW material.

2.3.5.3. Microstructure Image

This test is carried out based on the intensity of the reflected light from the metal surface to the inside of the microscope, which causes different images to be seen (bright, slightly bright, dark) (Akramifard et al., 2014).

Before micro photos, the material that has undergone the FSSW process is smoothed (polished) and then etched with a Nitric acid (HNO₃) chemical solution. Determination of parts taken for micro photos are determined in Figure 17.



Figure 16. Hardness testing.

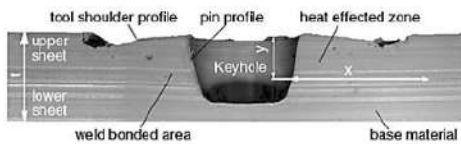


Figure 17. Microphoto position of the test sample (Bilici, 2012).

3. RESULTS AND DISCUSSION

The results and discussion present a description of the research data equipped with tables and figures. The result data obtained is analyzed and explained in detail the causes and effects of the data obtained and related to relevant reference sources.

3.1. Visual Observation of Friction Stir Spot Welding Results

The welding results with the friction stir spot welding method make different top appearances due to the influence of different rotational speeds and pin dimensions given in the welding process, which is also ready stated and supported in the article that Friction stir spot welding (FSSW) is a variation of linear Friction Stir Welding (FSW) along the surface (Shen, Ding and Gertich, 2020), as shown in Figures 18, Figure 19, and Figure 20.



Figure 18. Samples A1, A2, and A3 top view of FSSW welding results with 5 mm pin 5.1 mm welding depth.

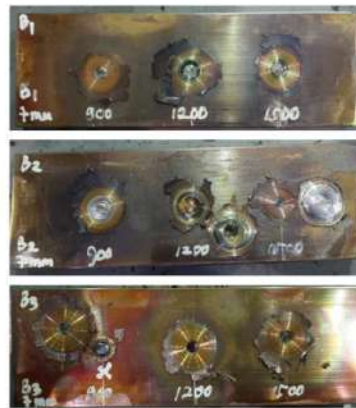


Figure 19. Samples B1, B2, and B3 top view of FSSW welding results with 7 mm pin welding depth of 7.1 mm.

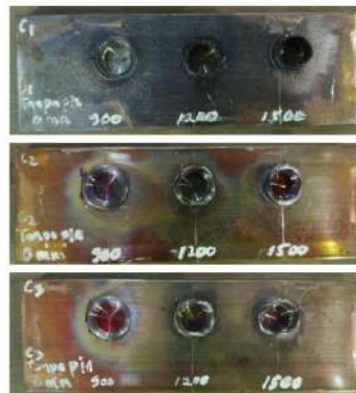














Figure 20. Samples C1, C2, and C3 top view of FSSW welding without pin (0 mm) welding depth of 2 mm.

3.2. Results of Macro Photographs of Weld Cross Sections

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 1, Test sample C1 was the first trial before determining the depth of ingestion during the FSSW process, so the resulting depth differed from the other test samples as described in article that carbon galvanized steel using friction stir spot welding. Three conical pins with varying lengths (short, medium, and long) were utilized, along with different dwell times and rotation speeds of the tool. The objective of this research was to compare the simultaneous effects of several important process parameters on mechanical and welding properties (Feizollahi and Moghadam, 2023).













Table 1. Samples with tool without pin (0 mm).

Replication Code	Pin Length		
	0 mm		
	900 rpm	1200 rpm	1500 rpm
C1 Cu-Al			
C2 Cu-Al			
C3 Cu-Al			
Cu-Cu			

This different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial penetration of the tool in the welded area so that the sheet widens due to the tool's pressure. This is shown in the pictures in Table 1. Starting from C1 (Cu-Al), C2 (Cu-Al), C3 (Cu-Al), Cu-Cu and Al-Al. In Figure C1 (Cu-Al), with

a rotation speed of 900 rpm and a pressing depth of 6 mm, the perfect mixing of copper and aluminum is seen compared to other parameters. Along the joint, it does not connect perfectly with the visible gap from the two sides of the sheet that has been welded.













Table 2. Sample with 5 mm pin length tool.

Replication Code	Pin Length		
	5 mm		
	900 rpm	1200 rpm	1500 rpm
A1 Cu-Al			
A2 Cu-Al			
A3 Cu-Al			
Cu-Cu			

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 2, which is different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial penetration of the tool in the welded area due to the pressure of the tool, which is shown in the pictures in Table 2 starting from A1 (Cu-Al), A2 (Cu-Al), A3 (Cu-Al), Cu-Cu, Al-Al, and Al-Cu. Comparison of welding results between all specimens can be seen visually. There is perfect and less perfect diffusion in each test specimen, such as in test specimens rotated 900 rpm A1 (Cu-Al), A2 (Cu-Al) shows mixing between copper and aluminum, which is arguably quite good, and in test specimens with 1200 rpm on A3 (Cu-Al) shows mixing between copper and aluminum which is arguably quite good.

Meanwhile, the different parameters show fusion imperfections in the welding mixture area, which is not perfectly stirred to form a joining, which is visible in the picture in Table 2 where the welding area is included. This is because the mixture should melt and stir upwards to join and form a surface on the welded sheet.

Table 3. Sample with 7 mm pin length tool.

Replication Code	Pin Length		
	7 mm		
	900 rpm	1200 rpm	1500 rpm
B1 Cu-Al			
B2 Cu-Al			
B3 Cu-Al			
Cu-Cu			

The results of welding with the friction stir spot welding method after cutting and sanding produce an appearance as in Table 3, which is different for each parameter imposed on the welding process. All welding processes show that at the initial point of welding, there are traces of initial tool penetration in the welded area due to the tool's pressure. This is shown in the images in Table 3, starting from A1 (Cu-Al), A2 (Cu-Al), A3 (Cu-Al), Cu-Cu, Al-Al, and Al-Cu. These results are different compared to the previous results using the tool without a pin (0 mm) and the tool with a 5 mm pin. For the results of stirring with a pin length of 7 mm, there is a perfection of fusion in the weld mixture area as shown in Table 3. The size of the pin affects the perfect stirring to form the joining, which is visible in the figure in Table 3, where the weld area is formed.

3.3. Microstructure Observation

The determination of parts taken for micro photos are determined in position 1, namely the base metal (BM), position 2, namely the stir zone, position 3, namely the HAZ section as described in Figure 21 from the Cu-Al, Cu-Cu, Al-Al, and Al-Cu.

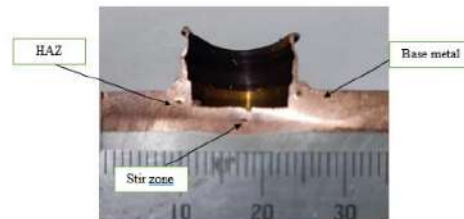


Figure 21. Position for a micro photo of the test sample.

3.3.1. Base Metal

Base metal is an area that is not affected by the welding heat of either the mortar or the heat generated.

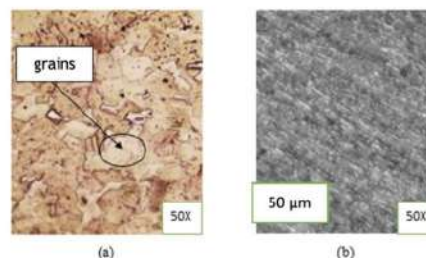


Figure 22. Microstructure of base metal material (a) Copper, (b) Aluminum.

In Figure 22, (a) the base copper base metal the black particles and square grains are Cu_2O , while in an image (b) shows aluminum base metal, and the evenly distributed black particles are FeAl_3 .

3.3.2. HAZ (Heat Affected Zone)

The HAZ region is an area that undergoes a thermal cycle but does not undergo plastic deformation, in this area there are also changes in microstructure. The HAZ area will change grain size, where the size is influenced by material characteristics, temperature, welding process, and cooling rate.

In Figure 23, the HAZ grain size of Cu-Cu welding experiences a slight change in grain size getting bigger compared to the base metal Cu material. While in the Cu-Al and Al-Al welding HAZ area the size of the copper grain structure is smaller than the grain size in the base metal area.

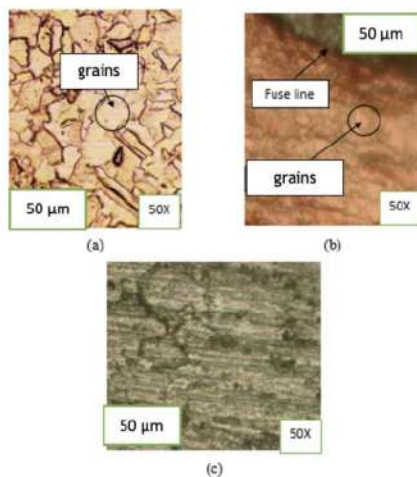


Figure 23. Microstructure of HAZ (a) Cu-Cu, (b) Cu-Al and (c) Al-Al.

The study aim²¹ to investigate the heat generation in FSSW (Friction Stir Spot Welding) of aluminum and copper alloys. This was done by creating bead spot welds on plates using both pinless and pinned tools with the same diameter and varying rotational¹ speeds. The results showed that tool diameter is the main¹ process parameter governing heat generation for rotational rates higher than 600 rpm. The rotating tool transfers heat to the surface of the aluminum and copper plate material. Welding temperature¹ thresholds were identified, depending on the rotational speed and the aluminum alloy being welded, with respect to the tool diameter. It was found that the temperature in FSSW can be controlled by using an appropriate combination of rotational speed and tool dimensions for aluminum and copper alloys subjected to temperature rise (Andrade et al., 2021).

3.3.3. Stir Zone

The Stir Zone is the area directly affected by the heat generated during welding and the deformed area due to the stirring process of the

pin tool. Welding and the deformed area due to the stirring process of the pin tool.

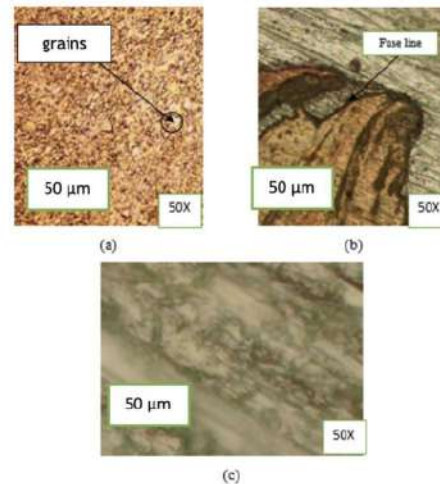


Figure 24. Microstructure of Stir Zone Region, (a) Cu-Cu welding, (b) Cu-Al welding, (c) Al-Al welding

In Figure 24, it can be seen that the microstructure of the stir zone area of all welding results has changed the grain size to be very small and looks smooth compared to the HAZ and base metal areas, and also in welding Cu-Cu, Al-Al materials, this is due to the influence of high temperatures by the pin tool as a stirrer and shoulder as preheating during the welding process and for different Cu-Al materials, the grain boundaries are not very visible due to the lack of polishing so that only the stretch marks are visible in the material mixture.

3.4. Hard Test on Welded Cross Sections

Microstructure testing was carried out at the Metallurgical Laboratory of Trisakti University. The determination of parts taken for microphotographs are determined in position 1, namely the point 1 section, position 2, namely the point 2 section, position 3, namely the point 3 section as described in Figure 25.

3.5. Hardness Test Results

The following are the results of hardness testing on the welding results at indentation points 1, 2 and 3 with the friction stir spot welding method in Table 4 and Table 5.

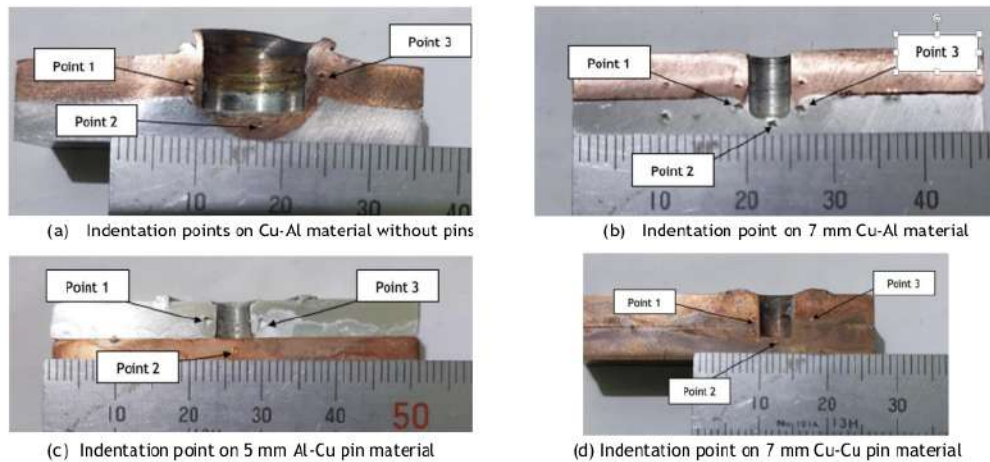


Figure 25. Indentation points of samples.

Table 4 is the average hardness value obtained from several indentation points, namely at points 1, 2, and 3, each of which is taken from Cu-Cu, Cu-Al, and Al-Cu materials. Then, the average value is taken to produce a value as in Table 5.

Table 4. Hard test values of test samples in Cu-Cu, Cu-Al, Al-Cu materials.

Zone	HVN Hardness Value in Materials		
	Cu-Cu	Cu-Al	Al-Cu
Point 1	83.3	70.2	69.7
Point 1	78.1	71.4	66.1
Point 1	76	70.8	67.4
Point 3	67.8	71.7	71.1
Point 3	72.1	72.5	69.5
Point 3	71.3	72.7	73.1
Point 2	90.9	77.2	74.1
Point 2	105.9	76.6	73.5
Point 2	108.1	79.4	72.4
Point 3	73.9	50.4	66.6
Point 3	71.7	51.2	68.5
Point 3	67.5	49.6	71.2
Point 1	75.86	48.7	64.2
Point 1	75.72	48.1	65.4
Point 1	72.4	48.3	64.7

Table 5. Average values of hard test on test samples in Cu-Cu, Cu-Al, and Al-Cu materials

Materials	Point 1	Point 3	Point 2	Point 3	Point 1
Cu-Cu	79.16	70.4	101.63	71.03	74.66
Cu-Al	70.8	72.3	85.07	50.4	48.37
Al-Cu	67.73	71.23	73.3	68.76	64.76

Figure 26 as shown histogram of hard test results in the welding process produces a distribution of hardness in Vickers testing as in Figure 27 as a graph of the average value of hard test on test samples in Cu-Cu, Cu-Al, and Al-Cu materials. The average hardness test results show that the point 2 areas all have the highest hardness value compared to other areas, namely point 1 and point 3 area.

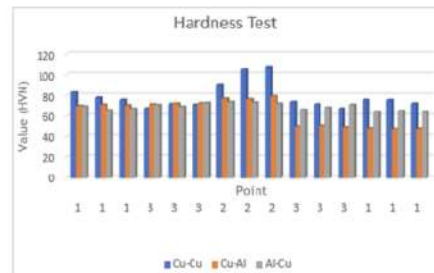


Figure 26. Histogram of hardness test.

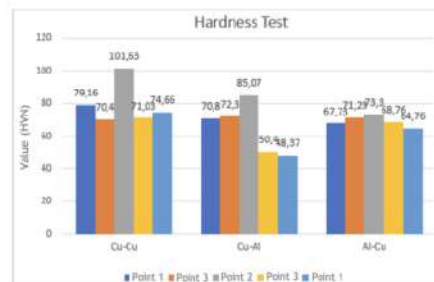


Figure 27. Average hard test results.

In the Cu-Cu specimen, there is a slight decrease in hardness from the base metal to the HAZ area, and this is because it experiences softening, which is influenced by the heat from the welding process. It can be seen from the results of the micro photo that the grain size looks more significant than the base metal grains because the smaller the grain size, the greater the hardness value and vice versa. In Figure 27 the highest hardness value is found in Cu-Cu welding, with an average hardness value of 101.63 HVN at point 2. The lowest hardness value is found in aluminum material, with an average hardness value of 48.37 HVN in point 1 area.

4. CONCLUSION

FSSW can be applied to sheets with several parameters that need to be considered. Based on observations of FSSW welding joints variations in pin tool length are very influential, the use of pin tools that are too short or without pins results in a less-than-optimal connection.

Pin tool with a length of 7 mm found the welding results are quite optimal. The rotational speed of 1500 rpm obtained the largest hook compared to the rotational speed of 900 to 1200 rpm in the pinless FSSW welding results. Then the more the rotational speed increases, the greater the Vickers hardness value on the aluminum part closest to the center of the nugget.

From the results of the distribution of hardness values, the lowest hardness was obtained by test sample A (5mm pin) at A1 900 rpm, namely 72.91 HV30, while the highest hardness value was obtained by test sample A (5 mm pin) at A3 1500 rpm, namely 76.94 HV30. The lowest hardness was obtained by test sample B (7 mm pin) at B1 900 rpm, 72.89 HV30, while the highest hardness value was obtained by test sample B3 1500 rpm, 79.33 HV30. The test result for test sample C (0 mm pin) at C1 900 rpm, namely 65.80 HV30, while the highest hardness value was obtained by test sample C (0mm pin) at C3 1500 rpm, namely 69.12 HV30.

Based on the results of hardness testing, the highest hardness value is found in Cu-Cu welding with an average hardness value of 101.63 HVN at point 2. The lowest hardness value is found in

aluminum material with an average hardness value of 48.37 HVN in point 1.

REFERENCES

- Akramifard, H.R. et al. (2014) 'Microstructure and mechanical properties of Cu/SiC metal matrix composite fabricated via friction stir processing', *Materials & Design* (1980-2015), 54, pp. 838-844.
- Almaxco, A. (2015) *Aluminium Alloy 1100 - H18*, Almaxco. Available at: <https://almaxco.com/wp-content/uploads/2023/06/Aluminium-Alloy-AA-1100.pdf> (Accessed: 15 May 2023).
- Andrade, D.G. et al. (2021) 'Shoulder Related Temperature Thresholds in FSSW of Aluminium Alloys', *Materials*, 14(16), p. 4375.
- ASTM, A. (2017) 'ASTM E384-17: Standard Test Method for Microindentation Hardness of Materials'. Available at: <https://www.astm.org/e0384-17.html> (Accessed: 9 January 2023).
- Benyerou, D. et al. (2021) 'Parametric Study Of Friction Stir Spot Welding (FSSW) For Polymer Materials Case Of High Density Polyethylene Sheets: Experimental And Numerical Study', *Frattura ed Integrità Strutturale*, 15(55).
- Bilici, M.K. (2012) 'Effect of tool geometry on friction stir spot welding of polypropylene sheets', *EXPRESS Polymer Letters*, 6(10), pp. 805-813.
- Çam, G., Javaheri, V. and Heidarzadeh, A. (2023) 'Advances in FSW and FSSW of dissimilar Al-alloy plates', *Journal of Adhesion Science and Technology*, 37(2), pp. 162-194.
- Esmaili, A., Givi, M.K.B. and Rajani, H.R.Z. (2011) 'A metallurgical and mechanical study on dissimilar Friction Stir welding of aluminum 1050 to brass (CuZn30)', *Materials Science and Engineering: A*, 528(22), pp. 7093-7102.
- Feizollahi, V. and Moghadam, A.H. (2023) 'Effect of pin geometry, rotational speed, and dwell time of tool in dissimilar joints of low-carbon galvanized steel and aluminum 6061-T6 by friction stir spot welding', *Results in Materials*, 20, p. 100483.

- Lewis, K.A.S. and Dhas, J.E.R. (2022) 'FSSW process parameter optimization for AA2024 and AA7075 alloy', *Materials and Manufacturing Processes*, 37(1), pp. 34-42.
- Li, W. et al. (2014) 'Improving mechanical properties of pinless friction stir spot welded joints by eliminating hook defect', *Materials & Design (1980-2015)*, 62, pp. 247-254.
- Meschut, G., Janzen, V. and Olfermann, T. (2014) 'Innovative and Highly Productive Joining Technologies for Multi-Material Lightweight Car Body Structures', *Journal of Materials Engineering and Performance*, 23(5), pp. 1515-1523.
- Nugroho, A.W., Saputra, M.R.D. and Budiyanoro, C. (2019) 'Pengaruh Kecepatan Putar Tool dan Sudut Shoulder Sambungan Friction Stir Spot Welding pada Bahan Polypropylene', *Semesta Teknika*, 22(2), pp. 183-193.
- Saputra, L.A., Sukarno, N.A. and Zulaehah, S. (2021) 'Pengaruh Interlayer Elektroplating Zinc pada Kekuatan Mekanik Friction Stir Spot Welding Aa1100-Ss400', *Semesta Teknika*, 24(2), pp. 93-101.
- Sehono and Ardianto, H. (2021) 'Efek Friction Stir Spot Welding Dalam Pemasangan Rivet Terhadap Sifat Mekanik Material Almunium Seri 2024', *Teknika STTKD: Jurnal Teknik, Elektronik, Engine*, 7(2), pp. 184-192.
- Shen, Z. et al. (2021) 'Refill Friction Stir Spot Welding Al Alloy to Copper via Pure Metallurgical Joining Mechanism', *Chinese Journal of Mechanical Engineering*, 34(1), p. 75.
- Shen, Z., Ding, Y. and Gerlich, A.P. (2020) 'Advances in friction stir spot welding', *Critical Reviews in Solid State and Materials Sciences*, 45(6), pp. 457-534.
- Tiwan, Ilman, M.N., and Kusmono (2021) 'Microstructure and mechanical properties of friction stir spot welded AA5052-H112 aluminum alloy', *Heliyon*, 7(2), p. e06009.
- Venukumar, S. et al. (2014) 'Microstructural and Mechanical Properties of Walking Friction Stir Spot Welded AA 6061-T6 Sheets', *Procedia Materials Science*, 6, pp. 656-665.

Analysis of Mechanical Properties and Microstructure of Aluminum and Copper Sheet Welding Using Friction Stir Spot Welding Method

ORIGINALITY REPORT

19%

SIMILARITY INDEX

13%

INTERNET SOURCES

17%

PUBLICATIONS

2%

STUDENT PAPERS

PRIMARY SOURCES

1

www.ncbi.nlm.nih.gov

Internet Source

2%

2

cjme.springeropen.com

Internet Source

2%

3

Mukuna Patrick Mubiayi, Esther Titilayo Akinlabi, Mamookho Elizabeth Makhatha. "Current Trends in Friction Stir Welding (FSW) and Friction Stir Spot Welding (FSSW)", Springer Science and Business Media LLC, 2019

Publication

1%

4

journal.umy.ac.id

Internet Source

1%

5

Tiwan, M. Noer Ilman, Kusmono. "Microstructure and mechanical properties of friction stir spot welded AA5052-H112 aluminum alloy", Heliyon, 2021

Publication

1%

6	Nitin Panaskar, Ravi Prakash Terkar. "Optimization of friction stir welding process parameters for AA6063-ETP copper using central composite design", World Journal of Engineering, 2020 Publication	1 %
7	www.morpac.com Internet Source	1 %
8	Vahid Feizollahi, Ali Heidary Moghadam. "Effect of pin geometry, rotational speed, and dwell time of tool in dissimilar joints of low-carbon galvanized steel and aluminum 6061-T6 by friction stir spot welding", Results in Materials, 2023 Publication	1 %
9	www.tandfonline.com Internet Source	1 %
10	R. Suryanarayanan, V.G. Sridhar. "Studies on the influence of process parameters in friction stir spot welded joints – A review", Materials Today: Proceedings, 2020 Publication	1 %
11	jultika.oulu.fi Internet Source	1 %
12	worldwidescience.org Internet Source	1 %

13	psasir.upm.edu.my Internet Source	<1 %
14	www.cell.com Internet Source	<1 %
15	Shen, Zhikang, Xinqi Yang, Zhaohua Zhang, Lei Cui, and Tielong Li. "Microstructure and failure mechanisms of refill friction stir spot welded 7075-T6 aluminum alloy joints", Materials & Design, 2013. Publication	<1 %
16	repository.ums.ac.id Internet Source	<1 %
17	eprints.ums.ac.id Internet Source	<1 %
18	Ajit Kumar Pattanaik, Kamal Pal, Debadutta Mishra. "Tribiological investigation and optimization of friction stir spot welding of dissimilar metals by LSSM-ANN method", Mechanics Based Design of Structures and Machines, 2020 Publication	<1 %
19	www-s3-live.kent.edu Internet Source	<1 %
20	Gurel Çam, Vahid Javaheri, Akbar Heidarzadeh. "Advances in FSW and FSSW of	<1 %

21

Majid Elyasi, Javad Taherian, Morteza Hosseinzadeh, Andrzej Kubit, Hamed Aghajani Derazkola. "The effect of pin thread on material flow and mechanical properties in friction stir welding of AA6068 and pure copper", Heliyon, 2023

Publication

<1 %

22

assets.researchsquare.com

Internet Source

<1 %

23

www.fracturae.com

Internet Source

<1 %

24

Karunakaran Devarajan, Venkatachalapathy Vellaiyappan Sangli Karuppanan, Thirumalaikumarasamy Duraisamy, Srinivasa Kumar Bhavirisetty et al. "Experimental Investigation and Characterization of Friction Stir Spot-Welded Dissimilar Aluminum Copper Metallic Lap Joints", ACS Omega, 2023

Publication

<1 %

25

Aris Widyo Nugroho, O. H. Dadang Dika, Cahyo Budiyanoro, Rela Adi Himarosa. "Characterization of Polypropylene Sheet Friction Stir Spot Welded Joint", Journal of Physics: Conference Series, 2021

Publication

<1 %

26 Yan Zhang, DeShui Yu, JianPing Zhou, DaQian Sun. "A review of dissimilar welding for titanium alloys with light alloys", Metallurgical Research & Technology, 2021 $<1\%$
Publication

27 ieomsociety.org $<1\%$
Internet Source

28 journals.uran.ua $<1\%$
Internet Source

Exclude quotes On

Exclude matches < 10 words

Exclude bibliography On